

Progress in Ultrasonic Spray Pyrolysis for Condensed Matter Sciences Developed From Ultrasonic Nebulization Theories since Michael Faraday

Bonex W. Mwakikunga^{1,2}

¹DST/CSIR National Centre for Nano-Structured Materials, P.O. Box 395, Pretoria 0001, South Africa

²Department of Physics, University of Malawi-The Polytechnic, Private Bag 303, Chichiri, Blantyre 0003, Malawi

Abstract – *This review outlines briefly the history of the phenomenon of ultrasonic nebulization of liquids since the discovery of such an effect by Michael Faraday and the explanation of the phenomenon by capillary wave mechanism and “cavitation” hypothesis. Ultrasonic spray pyrolysis for materials processing and the theory that predicts the final particle are discussed. The popularity of the technique is shown by the rising number of research groups in the world processing various materials by this method due to its cost-effectiveness, purity of its products and controllability of particle size and final properties.*

Keywords: *Pyrolysis, Ultrasonic Spray, Surface Tension, Chemical Vapor Deposition, Viscosity*

1. Introduction

Chemical vapour thermal deposition form one of the largest groups of techniques for realising a variety of materials in condensed matter science. The starting material is either a gas or liquid carefully chosen to end up into a stoichiometric material desired. The general process entails a source of chemical vapours/droplets which are carried into a heated zone for evaporation and decomposition and finally ending up either on a substrate (for thin films) or a filter (for powders) [see schematic in Fig. 1]. When dealing with vapours/gases as starting materials, the method is usually referred to as chemical vapour deposition (CVD); there are many forms of CVD. The term “spray pyrolysis” (SP) is used when dealing with liquid droplets or powders as precursor materials.

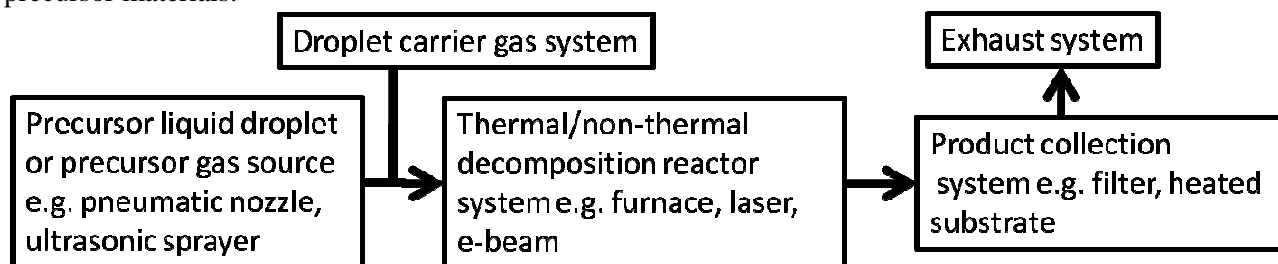


Fig. 1 Generalised schematic of chemical vapor deposition systems on which ultrasonic spray pyrolysis is based

The word pyrolysis is taken from a Greek word “pyre” which means “a pile of fuel or pile of wood” with specific reference to heating by flame [1]. Since such heating raises the precursor material to a plasma state where radicals, electrons and ions prevail, this process can be used in *in-situ* spectral analysis of elemental composition of the precursors in addition to the decomposition mechanisms, reaction kinetics and formation of new condensed matter. The source of heat can be a furnace (thermal CVD), a hot wire/filament (HWCVD, HFCVD), an intense light source such as an I.R. CO₂ laser or a UV excimer laser (laser pyrolysis LP), plasma source (plasma enhanced PE-CVD), an I. R. lamp or, simply, a heated substrate.

A number of previous review articles have been presented on different forms of CVD: thermal CVD [2-11], plasma enhanced PE-CVD [12-19], hot-wire or hot filament (HWCVD or HFCVD) [20-28] and not many of them have been as exhaustive in their respective areas. Pyrolysis, although classified under CVD in some text, has become a wide area of research and technology covering synthesis of new products, qualitative and quantitative spectroscopic analysis of fluids and, lately, alternative route to production of debris-free x-ray sources; these aspects are elaborated further in the sections that follow. In spray pyrolysis the droplets or vapours can be generated either by pneumatic nozzles in whistle-type sprayers or ultrasonic nebuliser.

In the former the process is simply called spray pyrolysis (SP) and in the latter case, the process assumes the name “ultrasonic spray pyrolysis” (USP). An article on the versatility of spray pyrolysis by Pramod Patil [28] among other aspects tabulated publications up to early 1999 listing materials and spray pyrolysis parameters. Other reviews have been on specific materials employing spray pyrolysis as one of the wide range of methods used in producing such materials: superconductors [29], carbon nanostructures [30], ceramic nano-composites [31], diamond [32], semi-coke [33], and semiconductors [34]. The present review chapter will restrict its discussion to ultrasonic spray (USP) technique on a wide range of materials especially from 1999 to the present and on laser spray (LP) pyrolysis. This is a period that has seen a lot of improvements to pyrolysis techniques to the extent that structures with new shapes and novel growth dimensionality have been produced in a controlled manner.

The scarcity of specific review papers in a period like this one where numerous publications pertaining to materials synthesis by various versions of pyrolysis was the main motivation of the present compilation. First, a historical outline of the droplet generation phenomenon by ultrasonic nebulisation is given. This has not been covered in most previous reviews except by Yule *et al.* [35], Barreras *et al.* [36] and Nevolin [37]. These reviews have not covered pyrolysis but restricted themselves to the nebulisation phenomenon. The triumphs and challenges in ultrasonic spray pyrolysis are also presented. A tabulated literature survey and data-base from 1988 to 2008 is given and some unsolved problems in pyrolysis for materials processing with regard to droplet and particle size under different pyrolysis parameters are discussed.

2. Ultrasonic nebulization phenomenon

Ultrasonic atomization is a very effective method for production of ultra-small droplets and, after the droplets are pyrolyzed, the realisation of nano-sized materials. Quantum dots have been produced by spray pyrolysis [38]. Three approaches are common in the droplet production: (1) passing the liquid across a standing ultrasonic wave, (2) depositing the liquid over an ultrasonic transducer and (3) immersing a focussing ultrasonic transducer in the liquid in such a way that the liquid depth is equal to the focal length of the ultrasound lenses in the transducer.

Generation of droplets by means of ultrasonic waves was first reported in 1927 by Wood and Lomis [39]. A number of mechanisms have been proposed to explain this phenomenon. At low excitation frequencies (20 – 100 kHz), we can imagine that only surface molecules respond to form droplets; such waves are called *capillary waves*. At higher excitation frequencies (0.1- 5 MHz) and intensities, bulk atoms of the liquids come into play and this effect is called *cavitation*.

2.1. Capillary Wave Mechanism

The capillary wave proposal enjoyed intense research interest from the first known studies by Faraday [40] in 1831 to the present. It was Lord Kelvin, as elaborated in Rayleigh’s book [41] in 1871, who derived the well-known equation for the wavelength of capillary waves as

$$\lambda = \left(\frac{2\pi\sigma}{\rho f^2} \right)^{1/3} \quad (1)$$

Here, λ is the wavelength, σ is the surface tension, ρ is the liquid density and f is the frequency of the surface waves. This equation was later modified by Rayleigh [41,42] to give

$$\lambda = \left(\frac{8\pi\sigma}{\rho F^2} \right)^{1/3} \quad (2)$$

Note that F which is equal to $2f$ is not the frequency of the surface waves but rather the frequency of the forcing sound. The fact that the frequency of the surface waves is *half* the exciting frequency was empirically obtained from experimental measurements. A number of experimental workers in the 1950's [43-48] pointed to unstable surface capillary waves as the origin of droplet formation relying on the simplified linear instability analysis. The 1962 experimental determination by Robert Lang [49] of the relationship between the wavelength of the capillary waves and the size of the droplets so formed spurred the capillary wave mechanism to greater heights. Lang showed that the droplet size, D_L , and the capillary wave length λ were related by the empirical equation

$$D_L = 0.34\lambda \quad (3)$$

The subscript L in Eq. 3 signifies the Lang's droplet diameter in distinction from other droplet diameter symbols to follow. Extra support from Sindayihubura & Bolle [50] in 1998 brought more assurance that capillary waves were probably the main mechanism. How drop formation may occur by unstable surface capillary waves was illustrated schematically as reproduced in Fig. 2 and this phenomenon is usually called the Taylor instability [52]. In the Taylor instability the liquid capillary waves are composed of crests (peaks) and troughs. Atomization takes place when unstable oscillations tear off the crests of the capillary waves away from the bulk of the liquid. Thus the droplets are produced at the crests whose size is proportional to the wavelength.

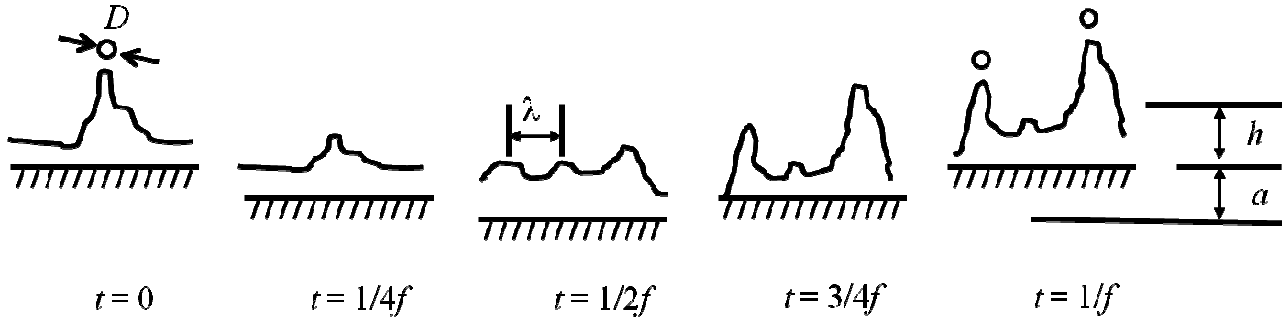


Fig. 2 A sketch showing idealized droplet formation from standing-wave crests showing one period of wall vibration.

A major revision to the Lang's equation was done by Peskin & Raco [52] in 1963 and later, 1996, by Jokanovic *et al.* [53] who, rather than adopting an existing empirical equation, chose to derive a general equation from first principles. The analysis especially by Jokanovic *et al.* started from applying the Bernoulli's equation to an incompressible fluid of density, ρ , surface tension, σ , under pressure, p , due to an ultrasonic excitation, f , from a depth, y , and thereby generating a disturbance of amplitude, $\xi(x,t)$ given by

$$\rho gh + \rho \frac{\partial \phi}{\partial t} + \sigma \frac{\partial^2 \phi}{\partial x^2} = 0 \quad (4)$$

In this equation, ϕ is the rate potential. The boundary conditions employed were that when $y = -h$, $v = 0$ and $\partial^2 \phi / \partial x^2 = 0$ then

$$\phi = \frac{1}{h} \frac{dy}{dt} c_J h [k_J (y+x)] e^{ikh} \quad (5)$$

Here, c_J is a constant, k_J was taken to be the wave-number ($2\pi/D_J$) where in turn D_J is the Jokanovic's aerosol droplet diameter (again to distinguish it from that of Lang above). The Mathieu's

function was then adopted which was observed to explain the typical shape of the relationship between the amplitude of the oscillation of the meniscus surface and the wave-number. The Mathieu's function was given as

$$\frac{dy}{dt} + hk \left[\frac{\sigma k^3}{\rho} ht - kght \right] y = 0 \quad (6)$$

The solution of Eq. 2.6 for $h \gg \xi(x,t)$, that is, for small disturbances, found by Jokanovic was seen to be similar to that previous found by Peskin & Raco using a different analysis route (not reproduced here)

$$D_J = \left(\frac{\pi\sigma}{\rho f^2} \right)^{1/3} = \frac{1}{0.68} D_L \quad (7)$$

Note that the relationship between droplet diameter and the Kelvin relation for capillary wave length can also be derived from dimensional analysis as shown in by Mwakikunga *et al.* [55] given as

$$D = k_M \left(\frac{\sigma}{\rho f^2} \right)^{1/3} \quad (8)$$

where k_M is a dimensionless constant which according to Lang is $0.68\pi^{1/3}$ while, according to theoretical derivation by Peskin & Raco and Jokanovic, the constant k_M is equal to $\pi^{1/3}$. This means the droplet diameter as calculated by Lang's equation is smaller by the factor of 0.68 in comparison with that determined by Jokanovic's equation. Jokanovic *et al.* were able to show experimentally that their freshly derived equation yielded better agreement between calculated and experimentally determined droplet sizes. It must also be noted that Jokanovic *et al.* have arrived at Eq. 7 using various forms of the equation of motion of the liquid at the surface including one given by [54]

$$\frac{\partial\varphi}{\partial t} + g\xi - \frac{\sigma}{\rho} \left[\frac{\partial^2\xi}{\partial x^2} + \frac{\partial^2\xi}{\partial z^2} \right] = 0 \quad (9)$$

However, a number of more recent studies employing ultrasonic spray pyrolysis (an application to be discussed in the next section) and using either the Lang's empirical formula (Eq. 3 and/or the Jokanovic's revision Eq. 7) have shown that both equations have limitations. A serious conflict between theory and experiment reported by Nedeljkovic *et al.* [56] states: "Comparison of the theoretically [$d_J = 195$ nm, $d_L = 132$ nm] obtained results with the experimentally determined [$d_{exp} = 286$ nm] regardless of the equations being used for the determination of the aerosol droplets diameter undoubtedly shows that there is a substantial difference between the theory and the experiment, if the theoretical density of the particles packing was assumed..." And also according to Saponjic *et al.* [57] "Significant differences between the experimentally determined (285 nm) and the theoretically predicted values of the mean particle diameter (132 nm and 195 nm) were found indicating that the powder was highly porous..."

The reasons for this gross under-estimation by the theory of the experimentally determined particle size could be (1) the basic assumption in the Kelvin wavelength on which both the Lang's formula and that of Jokanovic *et al.* are based and (2) the absence of the dependence of droplet size on liquid viscosity and the volumetric flow rate which is contrary to experimental observations.

This calls for the consideration of the liquid's bulk properties in the models. These shortfalls are discussed in the unsolved problems in USP in section.

2.2. Cavitation Mechanism

Cavitation hypothesis is generally applied to high frequency and high energy intensity systems. When a liquid is irradiated with an intense ultrasound field, cavitation bubbles are formed. During the implosive

collapse of these bubbles near the surface of the liquid, high intensity hydraulic shocks are generated which in turn initiate disintegration into droplets. At such large intensities the excitation is beyond the liquid surface but extends into the liquid bulk contrary to the capillary hypotheses. Properties of the liquid bulk such as viscosity come into play as parameters affecting the nature of the final droplet. Sollner [58] was probably the first in 1936 to explain Wood & Loomis's ultrasonic atomization demonstration in terms of cavitation produced under the liquid film. While Lang and the other workers developed the capillary hypothesis, the cavitation hypothesis was almost abandoned thanks to Eknadiosynats and co-workers [59,60] who resumed this area in the mid-60's. Several studies after these tried to combine both hypotheses [61-64]. The effect of viscosity and surface tension on the Taylor instability has been studied [65], that the rate of growth of amplitude disturbance is affected by viscosity has been observed [66], the increasing importance of viscosity as surface tension decreases has been suggested [67] and the effects of density, viscosity, interfacial tension and relative fluid velocity on drop formation have been elaborated by Clark [68,69]. Another empirical equation for the prediction of the droplet size at high liquid flow rates was proposed in 1978 by Mochida [70] as

$$D = 31.7 \left(\frac{\sigma}{\rho} \right)^{0.354} \mu^{0.303} Q^{0.139} \quad (10)$$

In this equation, σ and ρ have the usual meanings, μ is the viscosity and Q is the volumetric flow rate of the liquid. However, this equation does not account for the excitation frequency. Clark found that the dependence of droplet size on viscosity roughly followed the proportionality

$$D \approx \mu^{0.166-0.303} \quad (11)$$

Tsai *et al.* [71] found in 1996 that droplet size and volumetric flow rate were correlating approximately thus

$$D \approx Q^{0.25-0.30} \quad (12)$$

This was quite in conflict with Mochida with his exponent being outside the range set in the Tsai *et al.* improved measurement.

2.3. A Combination of Capillary and Cavitation Hypotheses

More careful observations have shown that apart from the traditional parameters of surface tension, viscosity, density, forcing frequency and volumetric flow rate additional parameters such as geometry of the vibrating surface, the amplitude of the oscillations, the intensity of the ultrasound power or the energy density have a lot to do with the size of the droplet so produced. To this end Rajan and Pandit [72] in 1996 developed a new correlation equation to take into account some of these extraneous parameters and was found to be

$$D = \left(\frac{\pi\sigma}{\rho \cdot f^2} \right)^{1/3} \left[1 + A \cdot (We)^{0.22} (Oh)^{0.166} (I_N)^{-0.0277} \right] \quad (13)$$

The symbols A , We , Oh , I_N are respectively the surface area of the droplet, the Weber's number (the number that describes atomization), the Ohnesorge's number (or the viscous number) and the intensity number (the number affected by the geometry of the vibrating surface) defined in the following expressions:

$$We = \frac{fQ\rho}{\sigma} \quad (14)$$

$$Oh = \frac{\mu}{f \cdot A_m^2 \rho} \quad (15)$$

$$I_N = \frac{f^2 A_m^4}{v_s Q} \quad (16)$$

Most symbols have usual meaning but A_m is the amplitude, v_s is the speed of sound. Three alternate correlations to Eq. 13 were derived by Rajan and Pandit [72]: (1) using the Rayleigh instability criterion, (2) using the Walzel relation and (3) using Davies approach respectively

$$D = \frac{\mu Q k}{3.74 \sigma A_m} \quad (17)$$

$$D = \frac{1.06 k Q \frac{\mu}{\rho} \left(\frac{\rho}{\pi \sigma f} \right)^{1/3} \left(\frac{\rho f^2}{\pi \sigma} \right)^{2/3}}{f A_m \left[2 + 0.6 \frac{\mu}{f A_m^2 \rho} \right]^{1/3}} \quad (18)$$

$$D = k_1 \left[\sigma + \frac{1}{4} \mu (A_m \cdot f) \right]^{0.6} \rho^{-0.6} \left[\frac{1}{2} v_s A_m (2\pi \cdot f)^2 \right]^{-0.4} \quad (19)$$

A parity plot is one of the most convenient graphical techniques for evaluating the theoretically calculated quantity and the experimentally observed quantity. Rajan and Pandit [72] also presented parity plots for correlations in Eq. 13 and Eq. 19 and we reproduce them in Fig. 3

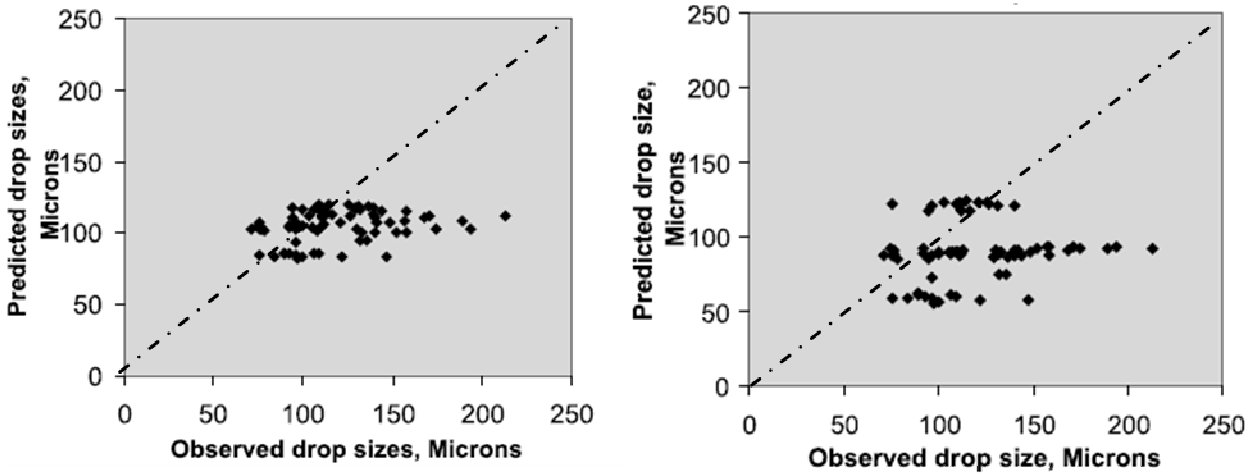


Fig. 3 Plots for correlations Eq. 13 and Eq. 19 for water droplets. The dotted line is a line that indicates the points where calculated quantity is exactly equal to the experimentally measured quantity.

From the parity plots one sees that most points are below the equality line signifying that the measured drop size is mostly less than the calculated drop size. This means that the Rajan-Pandit correlations are over-estimating the observed droplet size.

Avvaru *et al.* [73] have recently, in 2006, modified Eq. 13 to suit the so-called “Newtonian viscous liquids” given as

$$D = \left(\frac{\pi \sigma}{\rho f^2} \right)^{1/3} + 0.0013 (We)^{0.008} (Oh)^{-0.14/n} (I_N)^{-0.28} \quad (20)$$

In order to validate their theory, one of the Newtonian liquids — glycerine — was used in their study and the parity plots done using correlations in Eq. 13 and 19 were presented and are herein reproduced in Fig. 4.

In comparison with the Rajan-Pandit parity plots, one can clearly see a remarkable improvement in the alignment of the calculated –experimental points to the equality line.

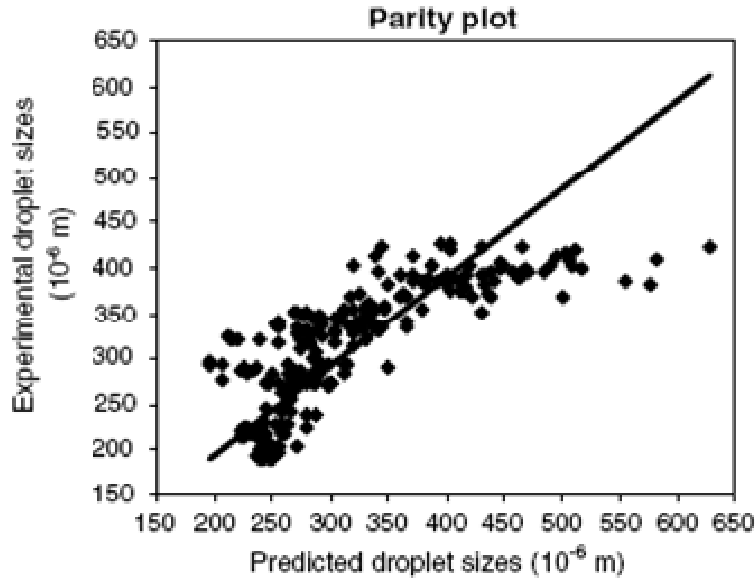


Fig. 4 A typical parity plot for a Newtonian liquid, glycerine (From Avvaru *et al* Ref. 117).

However, one can also see departure from the ideal equality line when droplet diameters exceed 400 μm . Therefore beyond this point the Avvaru correlation over-estimated the droplet sizes. Also even within the region where there is apparently good agreement, more points are above the equality line indicating that, in this region (200 – 350 μm), the Avvaru correlation under-estimated the droplet size. Overall, however, the Avvaru correlation is a big improvement over that of Rajan-Pandit. Avvaru *et al.* are also able to confirm and demonstrate the presence of cavitation in the droplet ejection by arranging an ingenious experiment. In this experiment, the ultrasonic generator is tilted horizontally and the force of droplet ejection is balanced with the environmental drag force from which the ejection velocity is determined. Using their so-derived differential equation, they are able to show that the Newtonian liquids such as glycerine yield an ejection velocity of 12.6 ms^{-1} whereas the non-Newtonian liquids yield an ejection velocity of 3.5 ms^{-1} . In both cases the ejection velocity is higher than the cavitation-less ejection velocity of 0.144 ms^{-1} which is attributed to capillary theory.

3. Effects of Pressure and Temperature on Surface Tension, Density and Viscosity of Fluids

With improvements of the theory, it is hoped that the future is bright with regard to understanding the phenomenon of ultrasonic generation of droplet from liquids. One of the many unsolved problems concerning the droplet size as a function of the liquid properties of surface tension, σ , viscosity, γ , density, ρ and so forth involves finding from thermodynamics how these properties vary when the liquid temperature and pressure change. In Mwakikunga *et al.* [Ref. 55], such a temperature–and–pressure dependent droplet size was dealt with by considering that droplet size took the expression in Eq. 8. Eq. 20 could also be re-written in the like manner as

$$D = \left(\frac{\pi\sigma(p,T)}{\rho(p,T)f^2} \right)^{1/3} + 0.0013(We(p,T))^{0.008}(Oh(p,T))^{-0.14/n}(I_N(p,T))^{-0.28} \quad (21)$$

3.1. Surface Tension as a Function of Temperature and Pressure

One of the earliest experimental studies on surface tension determination at varying pressure was carried out by Lynde [74] in 1906. In this study the surface tension at the interface between two liquids was determined via the derived equation

$$\sigma \cos \theta = \frac{1}{2} H_D r_{tube} (\rho_2 - \rho_1) \quad (22)$$

θ was the angle of contact, H_D was the difference in height between the two liquids in the manometer, r_{tube} was the radius of the capillary tube and ρ_2 , ρ_1 were densities of the two respective liquids. Taking a differential of Eq. 22 with respect to pressure p , Lynde got

$$\frac{\delta\sigma}{\delta p} = \frac{1}{2} r_{tube} (\rho_2 - \rho_1) \frac{\delta H_D}{\delta p} + \frac{1}{2} H_D r_{tube} \left(\frac{\delta\rho_2}{\delta p} - \frac{\delta\rho_1}{\delta p} \right) \quad (23)$$

By dividing Eq. 23 by Eq. 22, Lynde arrived at the following expression

$$\frac{1}{\sigma} \frac{\delta\sigma}{\delta p} = \frac{1}{H_D} \frac{\delta H_D}{\delta p} + \frac{1}{\rho_2 - \rho_1} \left(\frac{\delta\rho_2}{\delta p} - \frac{\delta\rho_1}{\delta p} \right) \quad (24)$$

The first term on the right hand side of Eq. 24 was measured experimentally by observing the change in height at varying pressure. The second term was determined from compressibility factors of the two liquids at varying pressure since $d\rho/dp$ is compressibility factor in the first place. With these measurements, Lynde was able to establish that a plot $(1/\sigma)(\delta\sigma/\delta p)$ versus p was a positive linear graph for mercury–water system and for mercury–ether system. The same was a negative linear plot for water – ether system and for chloroform–water system. However, for the carbon bi-sulphide – water system a parabolic line-shape was obtained. These results showed that the surface tension–pressure relation depends on not only on the liquid types but also on how the liquid densities vary with pressure which is discussed in the next few pages. For the case where the $(1/\sigma)(\delta\sigma/\delta p)$ versus p graphs are linear,

$$\frac{1}{\sigma} \frac{\delta\sigma}{\delta p} = \pm k_\sigma p \quad (25)$$

k_σ is a proportionality constant in Pa^{-2} . Surface tension can then be written in terms of pressure as follows:

$$\sigma(p) = \sigma_0 \exp\left(\pm \frac{1}{2} k_\sigma (p^2 - p_0^2)\right) \quad (26)$$

σ_0 is the surface tension at atmospheric pressure p_0 . Sachs *et al.* [75] in 1995 summarized all σ - p data from methane-water system up to that time [75-79] and their charts are reproduced in Fig. 5

For one to see the effect of temperature on surface temperature, one can turn to the important work of S. J. Palmer [80] in 1976. Palmer's theory based on (1) the calculation of the difference in energies of interaction between molecules in bulk and those on the surface or 'excess energy' (2) the minimum potential energy of these molecules due to a balance between attractive and repulsive forces at a critical temperature T_c .

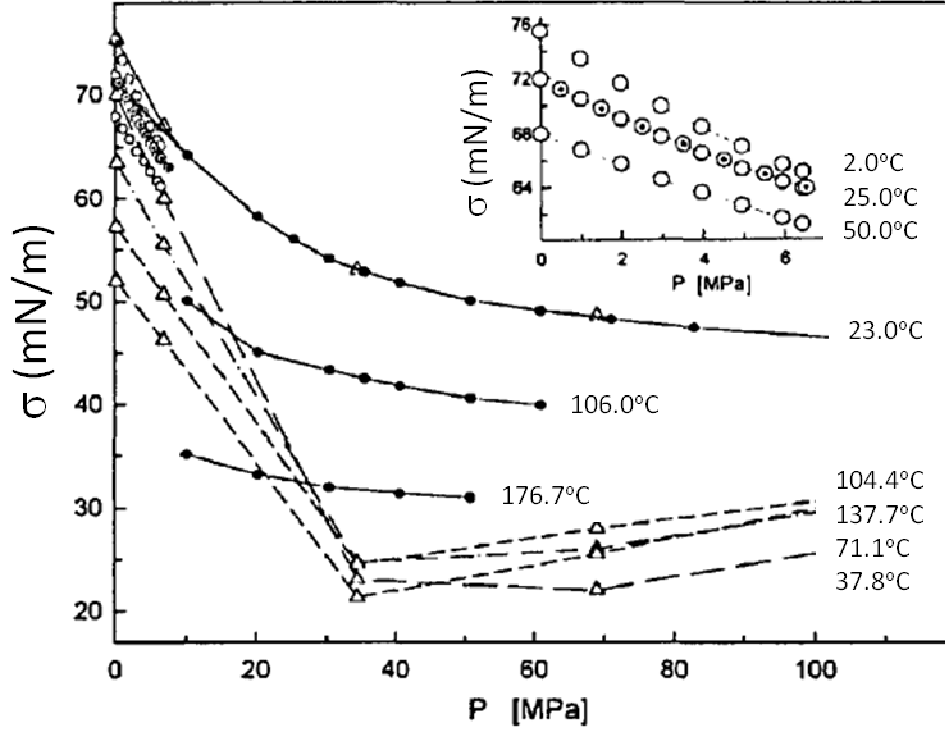


Fig. 5 Pressure and temperature dependence of the surface tension σ in the system methane-water; all data published in Ref. 119 until 1995. Δ , Ref. 120; \bullet , Ref. 121; \oplus , Ref. 122 and \circ , Ref. 123.

The derivation led to the following expression:

$$\sigma(T) \approx \frac{1}{4} n \left(\frac{N_0 \rho}{M} \right)^{2/3} k_B (T_c - T) \quad (27)$$

Where n and N_0 are the co-ordination numbers or the number of nearest neighboring molecules around one molecule in bulk and on the surface respectively, ρ is the density of the liquid, M is the molar mass of the liquid and k_B is the Boltzmann's constant.

It was shown in Mwakikunga *et al.* [Ref. 55] that based on fundamental thermodynamics, the general relationship between surface tension and temperature is given as [81-83]

$$\sigma(T) = H + T \frac{d\sigma}{dT} \quad (28)$$

where H is the energy required to increase the area of the liquid in contact with air by a unit area. It should be noted that H is always positive. Since σ always decreases as T increase, in accordance also with the Palmer equation in Eq. 27, then the derivative $d\sigma/dT$ is always negative. It can be shown that Eq. 28 carries the same meaning as Eq. 27 with $H = (n/4)(N_0\rho/M)^{2/3}k_B T_c$ and $d\sigma/dT = -(n/4)(N_0\rho/M)^{2/3}k_B$. Based on the two separate relationships of surface tension as a function of pressure according to the current generalization of Lynde's empirical study and temperature from Palmer's theory, one can write a combined relationship as follows

$$\sigma(p, T) \approx \frac{1}{4} n \left(\frac{N_0 \rho}{M} \right)^{2/3} k_B (T_c - T) \sigma_0 \exp\left(\pm \frac{1}{2} k_\sigma (p^2 - p_0^2)\right) \quad (29)$$

However, from Lynde's experiments, it is difficult to ascertain the σ - p relationship since the nature of dependence is also dependent on the ρ - p dependence which was not yet known but which will be shown in

the sections that follow. Also in Palmer's theory, density of the liquid is assumed constant with temperature. However, so far this could be the only equation that combines the effect of pressure and temperature on surface tension.

There have been other recent $\sigma(p, T)$ equations specific to some materials such as the one by Park and co-workers [83] who showed empirically the effect of surface tension of polystyrene droplets in supercritical carbon dioxide which was found to be

$$\sigma(p, T) = 38.7032 - 0.0559T - 0.01p + 2.596 \times 10^{-5} pT \quad (30)$$

And which was true only in the temperature range from 170°C to 210°C and from pressure of 500psi to 2500 psi. Their experimental results on $\sigma(p, T)$ were plotted on a chart which is reproduced in Fig. 6

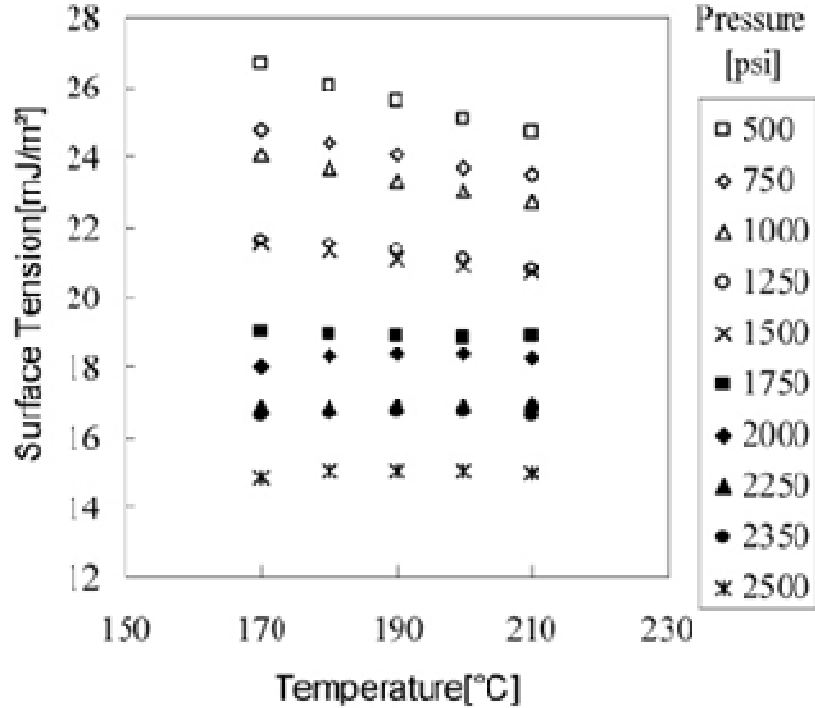


Fig. 6 Surface tension as a function of temperature and pressure for glycerine [From Park *et al.*, J. Phys. Chem. (2007)]

An article on surface tension given by Escobedo & Mansoori (1996) [84] based on the 1923 proposal by Macleod that surface tension of a liquid could be expressed in terms of its vapour ρ and liquid ρ_v densities thus:

$$\sigma = \Pi(\rho - \rho_v)^4 \quad (31)$$

where Π is called the parachor. Although it was thought to be a constant but, lately, it has been realized that parachor is in turn temperature dependent since both surface tension and density are temperature dependent. From statistical calculations, Boudh-Hir & Mansoori (1990) [85] derived an expression for Π of the following nature:

$$\Pi = \frac{1}{4} k_B T \left(1 - \frac{T}{T_c} \right)^{4-2B} \frac{z}{z_c} \zeta(\tau, \rho_l, \rho_v); \quad (32)$$

$$z = \left(\frac{2\pi m k_B T}{h^2} \right)^{1/2} \exp\left(\frac{\mu_c}{k_B T} \right)$$

where B is an exponent, the subscript c denotes the critical temperature values, z is the activity, μ_c is the chemical potential, h is the Planck's constant and $\zeta(\tau, \rho, \rho_v)$ is a statistical-mechanical function that shows liquid surface tension dependency on its liquid-state and vapour-state densities and temperature.

Another theoretical and empirical study of the surface tension data by Pandey [86] of ternary liquid system comprising liquid nitrogen, liquid oxygen and liquid argon revealed the relation to take the form a relation developed by Brock & Bird in 1955. This expression for non-polar liquids was derived by utilizing the power law concept applicable to temperature away from the critical point and is here given by

$$\sigma(T) = (P_c^2 T_c^2)^{1/3} \left(\frac{0.432}{Z_c} - 0.951 \right) \left(1 - \frac{T}{T_c} \right)^{11/9} \quad (33)$$

P_c , T_c and Z_c are respectively critical temperature, pressure and compressibility factor.

3.2. Liquid Density as a Function of Temperature and Pressure

When one needs to consider the effects of pressure on density, thermodynamical equations of state (EOS) are used. Wong *et al.* (1996) [87] used the van der Waal's EOS to study the pressure and temperature effects on density of liquid lubricants. They found that density increases with increasing pressure but decrease upon a raise in temperature as confirmed by their experiments. The van der Waal's equation of state for a real gases was used to find the $\rho(p, T)$ expression which was used to modify the droplet equation in Eq. 8 [55]. An improved and more appropriate EOS for liquids was proposed by Redlich & Kwong in 1949 [88] that accurately predicts densities of fluids thus

$$p = \frac{\rho RT}{1 - b\rho} - \frac{a\rho^2}{T^{1/2}(1 + \rho b)} \quad (34)$$

$$b = \frac{0.08664 RT_c}{P_c} \delta$$

δ is a parameter which further depends on temperature. By finding ρ as the subject of this equation,

$$\alpha_1 \rho^3 + \alpha_2 \rho^2 + \alpha_3 \rho + \alpha_4 = 0$$

$$\alpha_1 = ab$$

$$\alpha_2 = RT^{3/2}b + pT^{1/2}b^2 - a \quad (35)$$

$$\alpha_3 = RT^{3/2}$$

$$\alpha_4 = pT^{1/2}$$

one can find the expression of density as a function of temperature and pressure by solving the Eq. 35 and this variation of density is sketched in Fig. 7 (a) and (b)

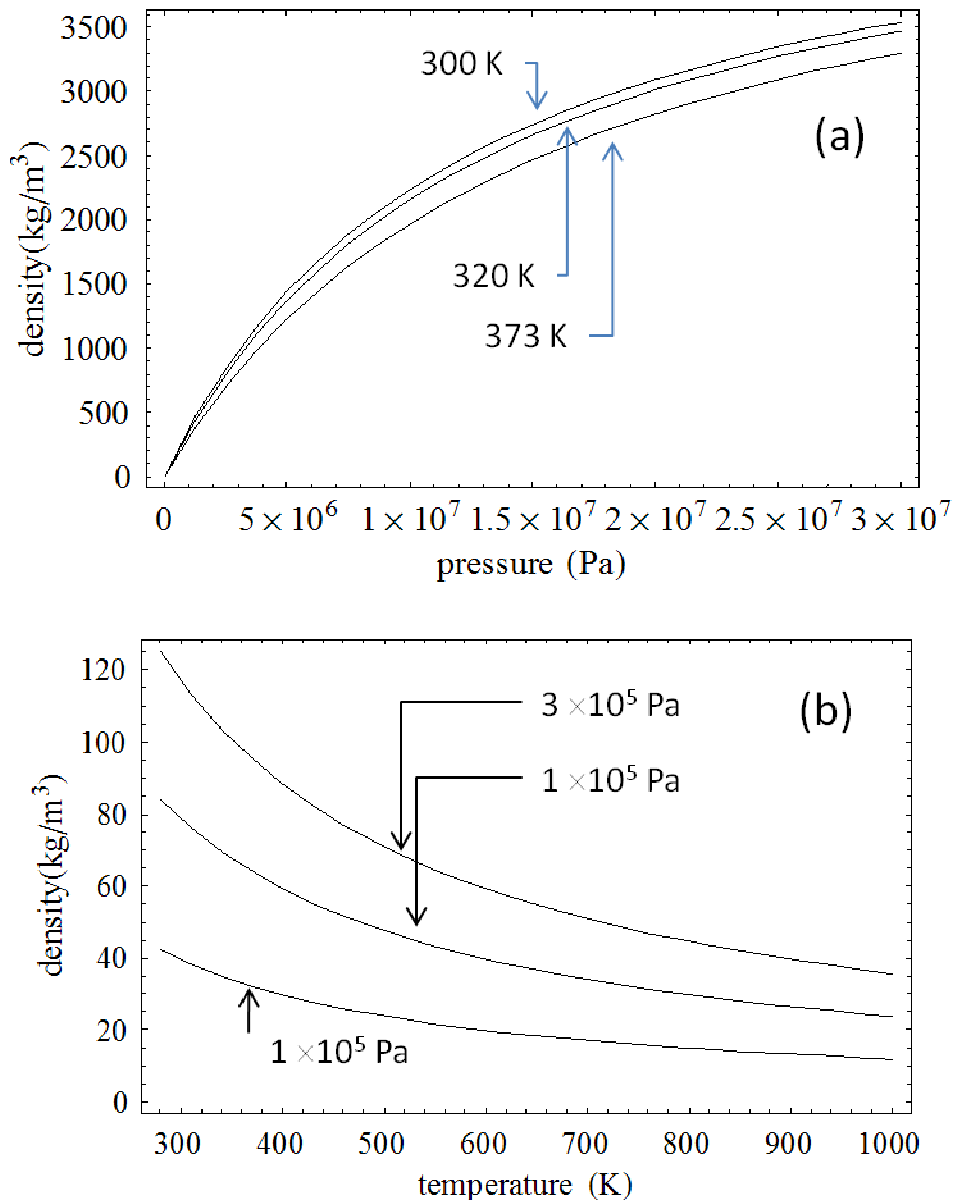


Fig. 7 Plots showing how density varies with (a) pressure and (b) temperature from Eq. 34 (Density values are not realistic and are not specific to any materials)

3.3. Effect of Temperature and Pressure on Liquid Viscosity

The principal observed qualitative facts are that (1) all gases at ordinary pressures become more viscous as the temperature is raised, (2) most liquids become less viscous as the temperature is raised, (3) highly compressed gases resemble liquids, they become less viscous and (4) for a few liquids (such as liquid helium and liquid sulphur).

There is a range of temperatures over which the viscosity increases as the temperature is raised. As was the case with surface tension, the variation of viscosity with pressure is expected to be one of the inverse nature.

It is known from Wright [89] that, as early as 1886, Reynolds proposed an expression for the change of viscosity with temperature for liquids and compressed gases given as $\mu \sim \exp(\text{const}/T)$. This was based on the observation of the similarity of viscous flow to diffusion (diffusion coefficient is given by D being $\propto \exp(\text{const}/T)$) and also by regarding the flow of molecules past each other as analogous to a chemical reaction (the effect of temperature on the rate of chemical reaction R being also $\propto \exp(E/RT)$ where E is the activation energy). The general form of the pressure [90] and temperature [91] dependence of viscosity has been

known for at least 50 years. Viscosity is now known to vary with temperature in a greater than exponential manner and temperature –viscosity equations generally allow for an unbounded viscosity at some characteristic temperature. At high pressure, the pressure-viscosity response is likewise greater than exponential, often following a less exponential response at low pressures [91].

Fein [92] considered that the low shear viscosity, μ , was an exponential of fluid density. Later, the so called “free volume model was developed [93]. A viscosity model that can describe the temperature and pressure response is the pressure modified equation introduced by Yasutomi *et al.* using the free volume model [94] given here as

$$\mu(p, T) = \mu_g e^{\frac{-2.3 \langle T - (T_{g0} + A_1 \ln 1 + A_2 p) \rangle (1 - B_1 \ln(B_2 p))}{C_2 + \langle T - (T_{g0} + A_1 \ln 1 + A_2 p) \rangle (1 - B_1 \ln(B_2 p))}} \quad (36)$$

μ_g is the viscosity at a glass transition temperature T_g given by the expression in the triangular brackets. The expression in curly brackets is the relative free volume expansivity and A_1 , A_2 , B_1 , B_2 , C_1 , C_2 and T_{g0} are parameters that are determined by fitting Eq. 36 to experimental data for a specific fluid. Eq. 36 suggests that increase in pressure raises viscosity whereas the raise in temperature drops viscosity as shown in Fig. 8

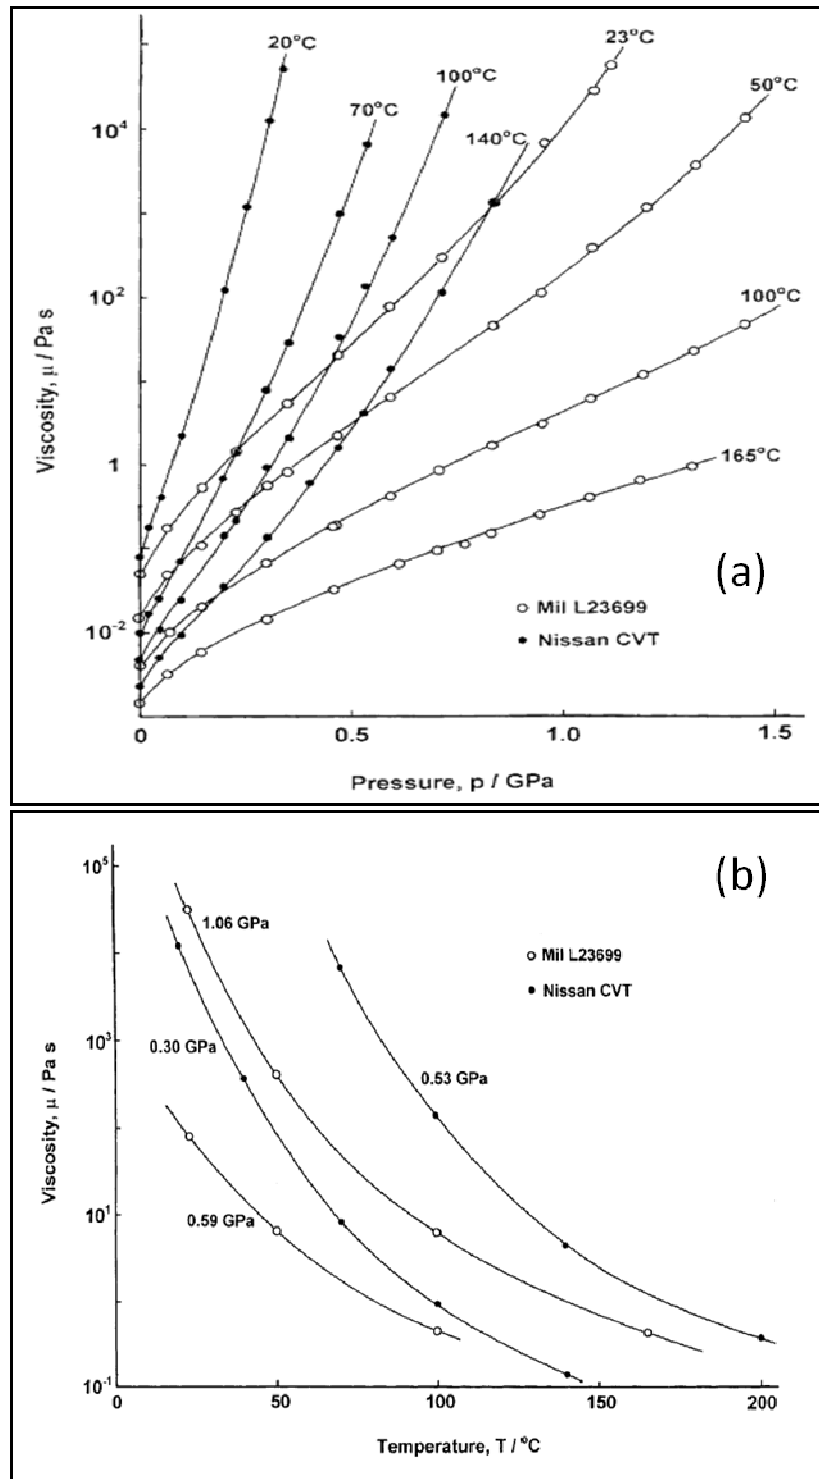


Fig. 8 Variation of viscosity with pressure and temperature (a) and temperature (b) for jet lube Mil L23699 (open circles) and a traction liquid (closed circles) [S. Bair *et al.* (2001)]

3.4. Final Droplet and Particle Size Formula

Every ultrasonic transducer/nebulizer generates heat into the liquid which it is intended to produce droplets from. Since ultrasonic spray pyrolysis set-ups are closed systems, an increase in the temperature accompanies an increase in pressure. The subsequent increases in temperature and pressure affect the density, surface tension and viscosity. As such the droplet size, which is heavily dependent on these parameters, is also affected. In this section, the study on how these changes in temperature and pressure in

the precursor liquid would affect the droplet size and hence the final particle sizes after pyrolysis are consolidated.

From sections 2.1 to 2.3 is seen that all the three parameters decrease as temperature is increased. However, as pressure is increased, only surface tension decreases; the other two parameter- density and viscosity- increase.

$$D = \left(\frac{\pi\sigma(p,T)}{\rho(p,T).f^2} \right)^{1/3} + \left[1 + 0.0013.(We(p,T))^{0.008} (Oh(p,T))^{-0.14} (I_N(p,T))^{-0.28} \right] \quad (37)$$

$$We = \frac{fQ\rho(p,T)}{\sigma(p,T)} \quad (38)$$

$$Oh = \frac{\mu}{f.Am^2\rho(p,T)} \quad (39)$$

$$I_N = \frac{f^2Am^4}{v_s.Q} \quad (40)$$

After substituting the pertinent parameters, the droplet size can be written in terms of the temperature and pressure dependent liquid density, viscosity and surface tension from Eqs. 29, 35 and 36 as

$$D = 1.14 \times 10^{-4} \left(\frac{\sigma}{\rho} \right)^{1/3} + 0.021 \frac{\left(\frac{\rho}{\sigma} \right)^{0.008}}{\left(\frac{\mu}{\rho} \right)^{0.14}} \quad (41)$$

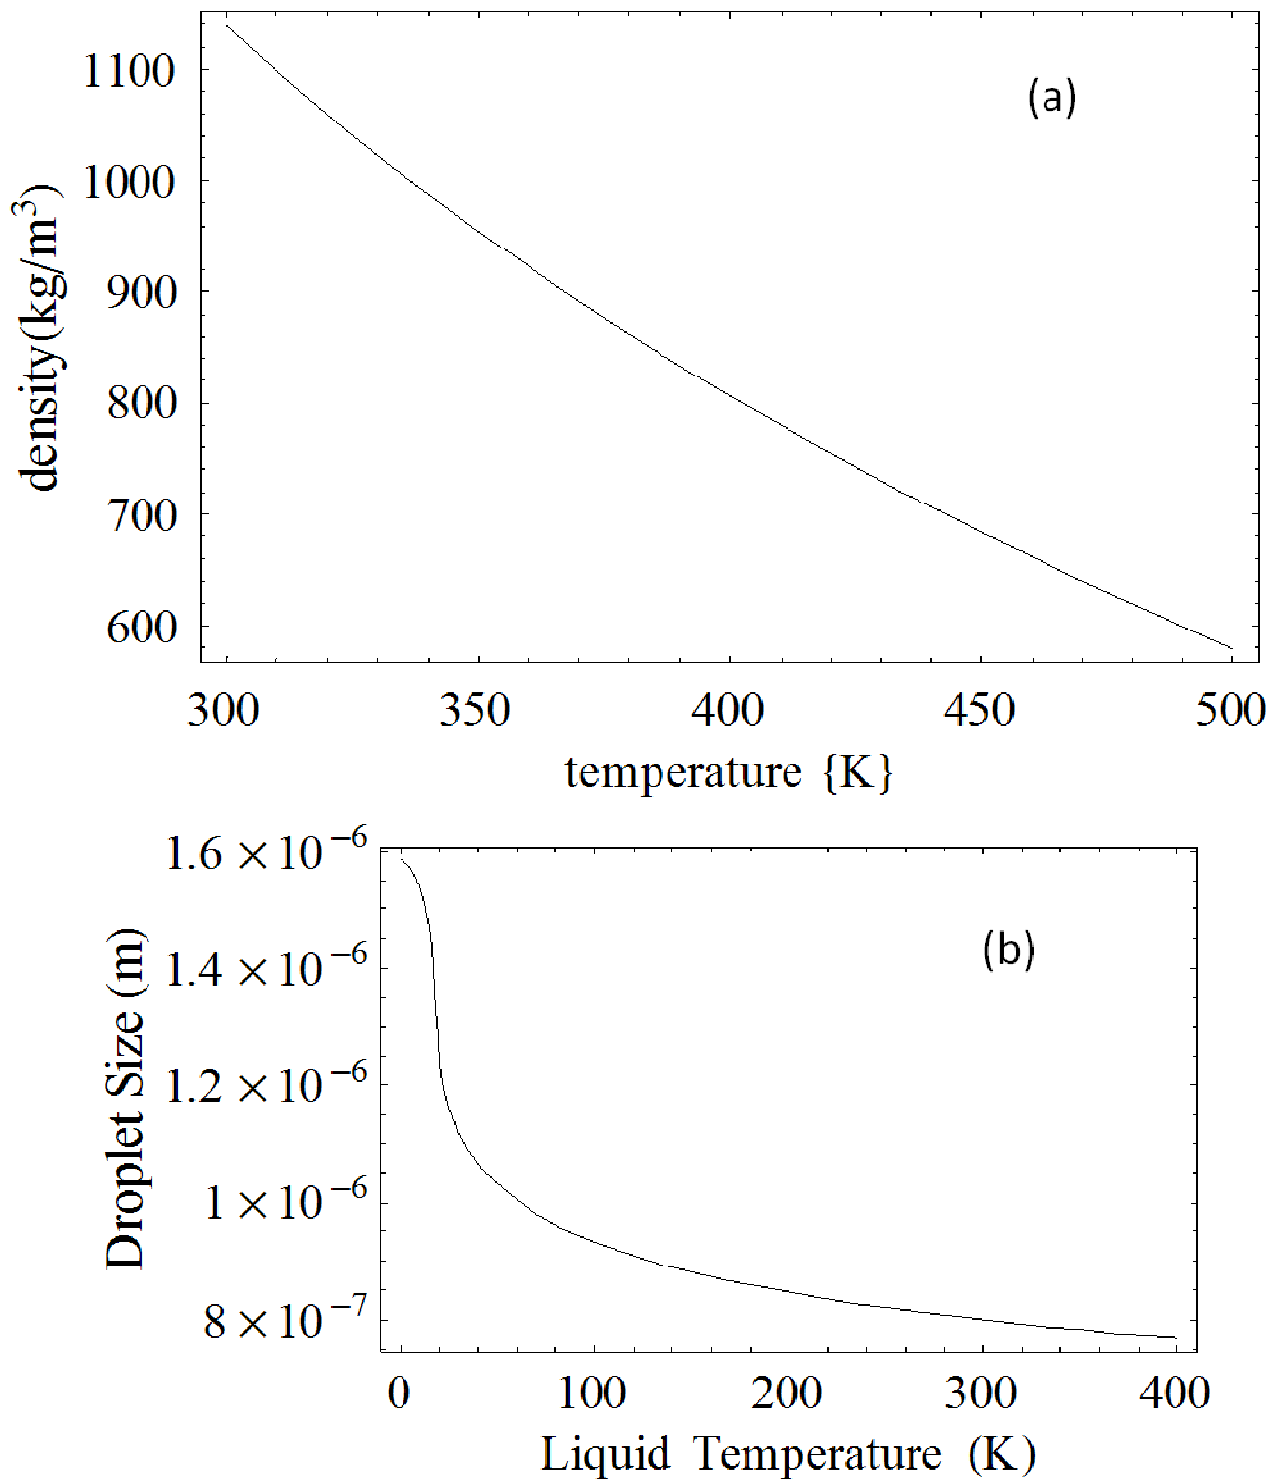


Fig. 9 A plot showing the variation of density (Eq. 35) and droplet size (Eq. 41) with liquid temperature

The density-temperature function was adopted from the Redlich-Kwong equation in Eq. 34, surface tension was taken from the presently derived expression from Lynde and Palmer theories given in Eq. 29 and viscosity-temperature profile was determined from Eq. 36, plotted in Fig. 9, shows the variation of droplet size as a function of liquid temperature. The droplet size decreases as temperature is increased.

The small changes in liquid pressure in a typical pyrolysis session lead to very small changes in surface tension, density and viscosity and hence on the droplet size. The droplet-size versus liquid pressure is therefore not shown.

4. Theory of Pyrolysis for Predicting Final Particle Size

Pyrolysis is an application of the phenomenon of droplet generation from liquids by ultrasound waves. It involves materials deposition by carrying the so-produced liquid droplets into a heated zone where the droplets undergo (1) evaporation, (2) decomposition (3) reaction into new products and (4) condensation of the new product onto a filter or a substrate [Fig. 10]

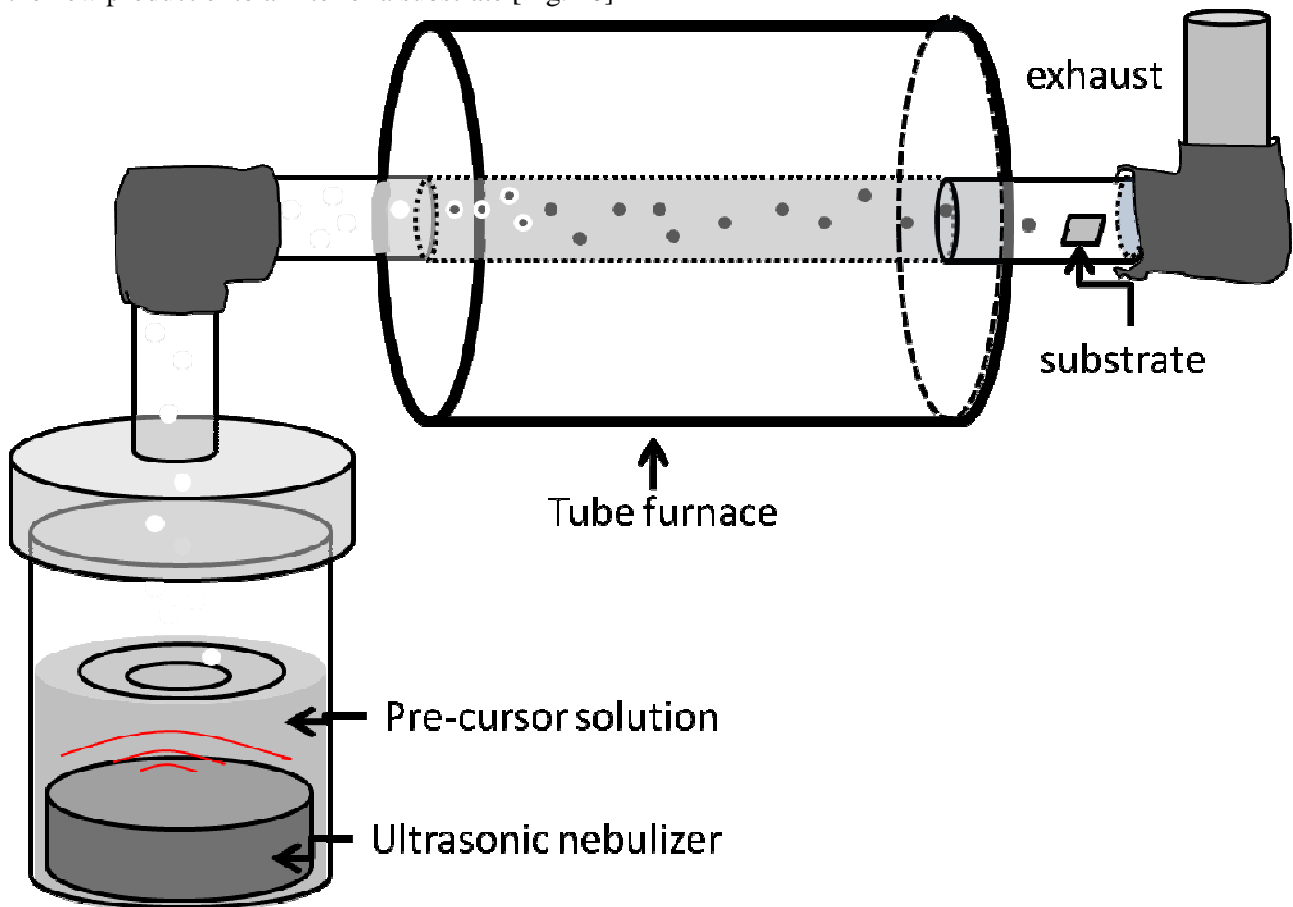


Fig. 10 Simple schematic of ultrasonic spray pyrolysis showing an ultrasonic nebulizer immersed in the precursor solution where droplets are generated and transport into a tube furnace for eventual pyrolysis and deposition onto substrates.

The theory of transitions of the liquid precursor droplet of initial diameter, D , in the heat field and the consequent transformation into a new material particle of diameter d is simple. During the preparation of the precursor solution suitable for spray pyrolysis, a precursor material of mass m_{pr} is dissolved in a solvent so that if the concentration of this precursor in the solvent is c_{pr} then

$$m_{pr} = c_{pr} \frac{4}{3} \pi D^3 \quad (42)$$

D is dependent on both frequency of the sound and the concentration of the precursor [348] as shown in the previous sections and as illustrated in Fig. 11 with data taken from Gurmen's group [348,353,391]

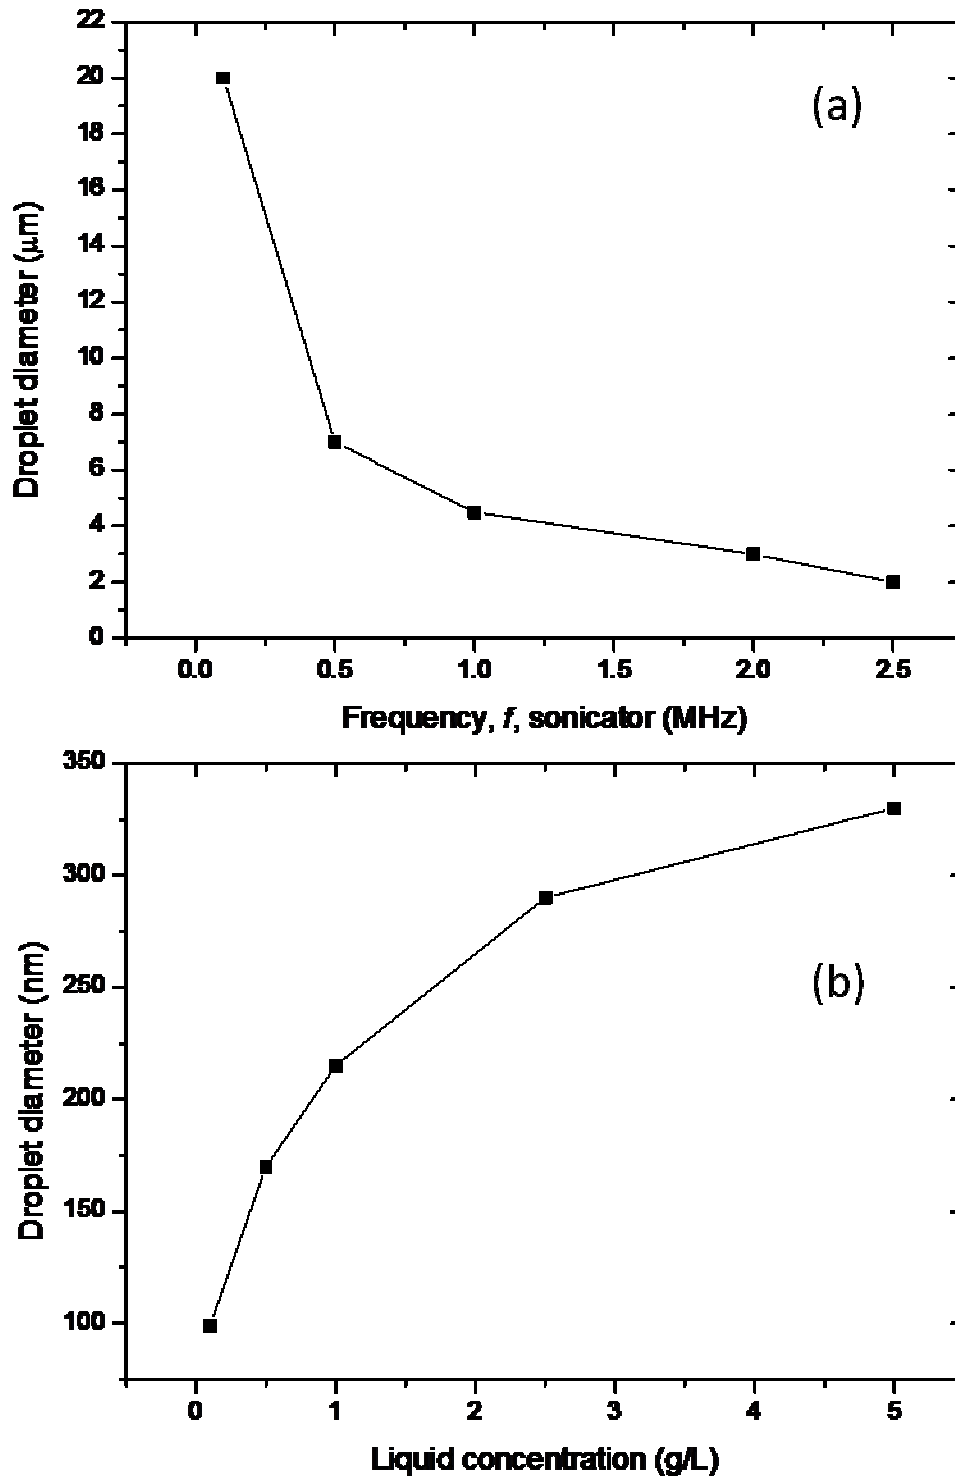


Fig. 11 Experimental observation of the dependency of droplet and hence particle size on nebuliser frequency (a) and precursor concentration (b). Data taken from S. Gurmen *et al.*, Mater. Res. Bull. (2006)

After pyrolysis–dissociation and decomposition – the precursor material, a remnant of evaporation, is further reduced to the final particulate of mass of m_p plus other species that mostly are in gaseous state and hence evaporate off without depositing. The particulate mass after assembly can be written as

$$m_p = \frac{M_p}{M_{pr}} m_{pr} \quad (43)$$

M_p and M_{pr} are the molecular masses of the final particle and the precursor material respectively. Assuming that the initial liquid precursor droplets and the final solid particles are spherical Eq. 42 and Eq. 43 can be combined to give

$$\frac{4}{3} \pi \rho_p d^3 = \frac{M_p}{M_{pr}} c_{pr} \cdot \frac{4}{3} \pi D^3 \quad (44)$$

d is the final particle diameter. This simplifies to the following equation

$$d = D \left(\frac{c_{pr} M_p}{\rho_p M_{pr}} \right)^{1/3} \quad (45)$$

Eq. 43 has been widely used by a number of authors employing ultrasonic spray pyrolysis in production of nano-particles to predict the final particle sizes.

5. Popularity of Ultrasonic Spray Pyrolysis

USP as an application of the ultrasonic droplet generation phenomenon has attractive features, like the traditional spray pyrolysis, of simplicity, economic viability, high deposition rate, possibility of coating over large areas and continuous operation [55]. But unlike other commonly known pneumatic atomizers, it has been described to possess the advantages of "... chemical purity and stoichiometry" and allows a narrow distribution of particle sizes. A large proportion of the droplets is below 20 μm and these are produced with low in-flight speed. This prevents the droplets from being removed from the gas phase by impact onto the walls of the reactor and through droplet-to-droplet collisions and consequent coalescence. The major disadvantages are potential for hollow structure or fractured particles which could be good for other applications and that the droplet production rate is typically low and highly dependent on the throughput of the nebulizer.

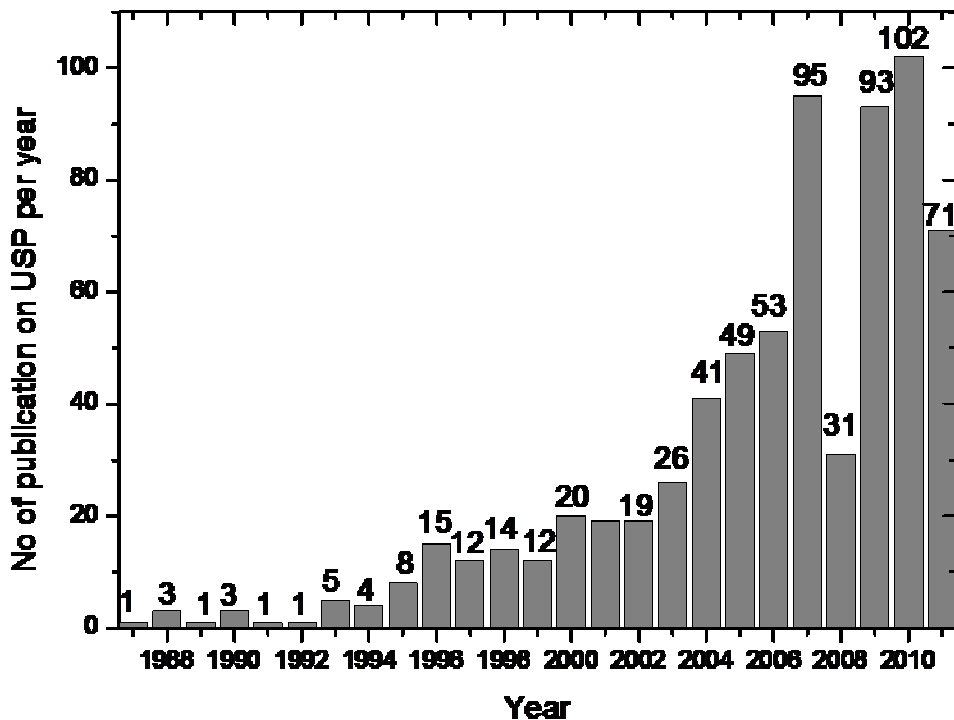


Fig. 12 Growing popularity of ultrasonic spray pyrolysis as measure by the number of publications (journal papers and conference proceedings) released per year since 1988 [96-512].

Since there are numerous publications, in the period from 1988 to the present (more than 730) [96-512], on materials processed using ultrasonic pyrolysis, it was seen as convenient to plot a time series graph as illustrated in Fig. 12.

6. Parameter Optimization in USP: Droplet Residence Time

One of the most important parameters for optimization of ultrasonic spray pyrolysis is flow rate of the precursor droplet. At extremely low flow rates, the throughput of the USP system is small at the benefit of obtaining truly nano-sized, nano-structured and completely-decomposed targeted materials. At extremely high flow rates, yield is high but complete decomposition of the precursor is compromised as the residence time of the precursor in the heated zone is small. An optimum flow rate is therefore necessary to obtain both high yield and pure materials. The relationship for residence time can be easily shown to be d and L are the diameter and length of the reactor respectively and Q_0 is the flow rate of the precursor assuming that the velocity of the carrier gas is the same as the velocity of the carried precursor droplets.

$$t_{residence} = \frac{\pi d^2 L}{4Q_0} \quad (46)$$

In the real case where the above assumption does not apply, temperature, T , and pressure, p , of the system are taken into account. In this case then the expression for residence time is given by C. Michel *et al.* (2006) [191] as

$$t_{residence} = \frac{\pi d^2 L}{4Q_0} \left(\frac{P_0}{P} \right) \left(\frac{T_0}{T} \right) \quad (47)$$

T_0 is room temperature, P_0 is the atmospheric pressure. In order to maximize t_{res} one can increase L to the maximum possible length. Increasing L has the disadvantage of an uneven temperature profile over a long distance.

One then needs to have several short heating zones whose temperature profiles are constant and manageable. Since the nature of products from USP depends in part on the control of the furnace temperature, Taniguchi and co-workers [137, 142,164,179,182,187,250,263,303,310,327,387] have made an elaborate setup with a furnace having several heating zones. A typical example of such multi-zone furnaces was well illustrated by Taniguchi's group [137]. This is illustrated in Fig. 13

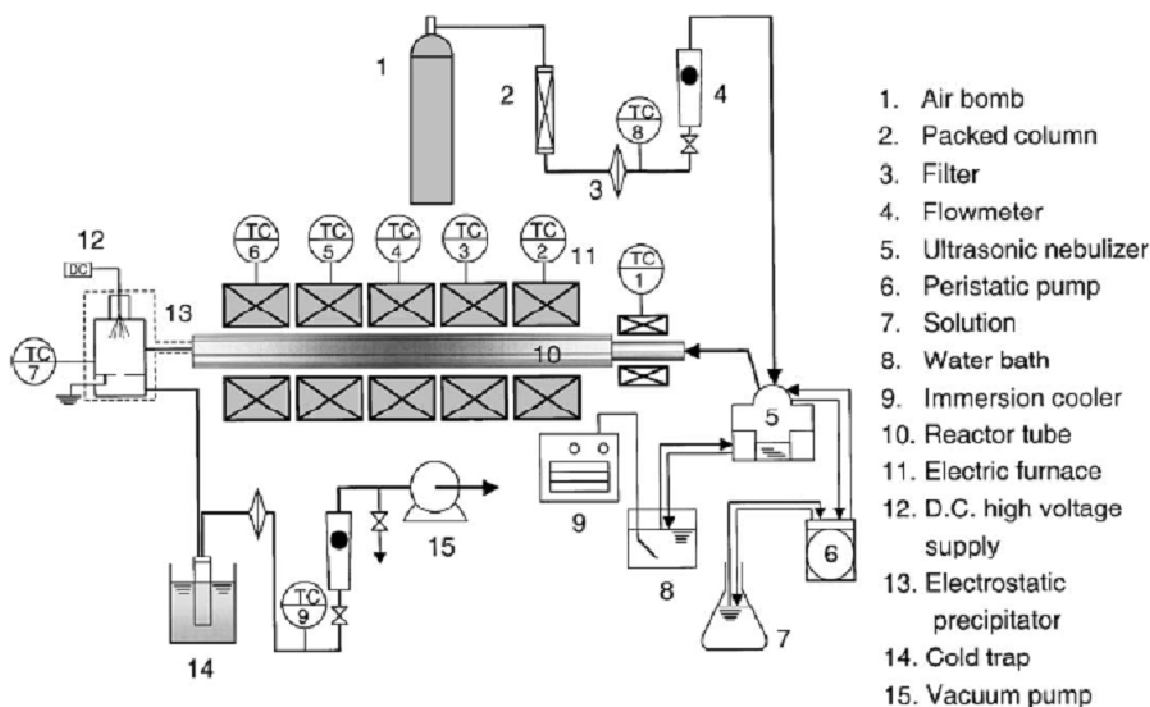


Fig. 13 A typical example of an ultrasonic spray pyrolysis employing a multi-zone furnace for control of product shape, particle size and other parameters. From Taniguchi's group.

7. Various Forms of USP

Worth noting are a few USP set-ups that have attracted attention through the years and the novel nano-structured materials they have produced. A setup by CNR Rao's group illustrated in Fig 14 had an ingenious provision for constant precursor liquid level apart from the usual USP components [97,99].

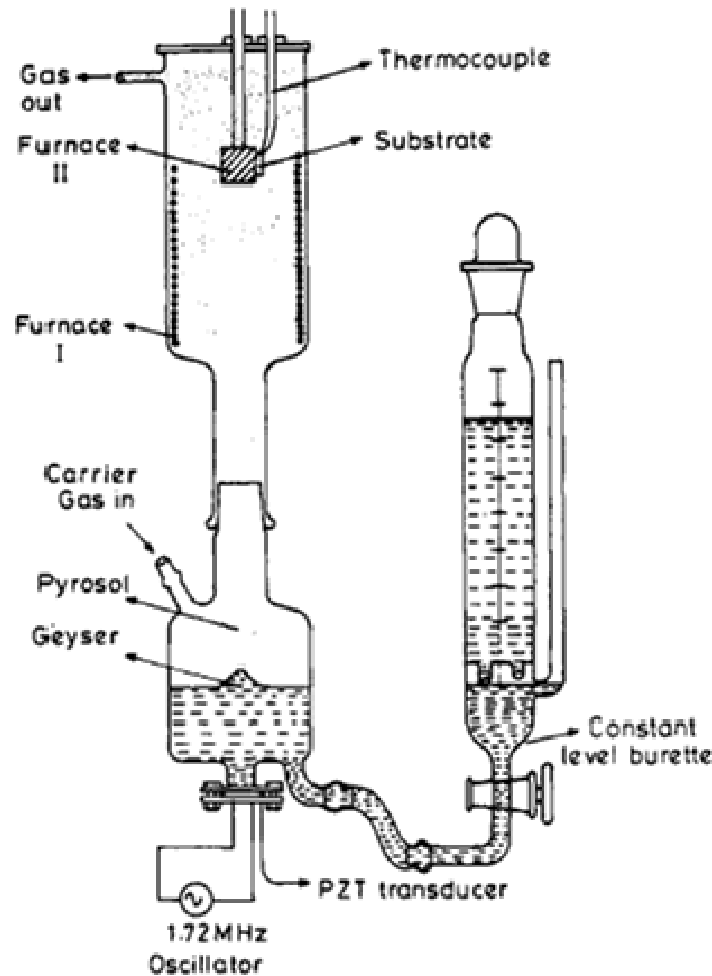


Fig. 14 A nebulised spray pyrolysis by C.N.R. Rao's group (from Ref. 97,99)

7.1. Asynchronous Pulse USP

The asynchronous-pulse ultrasonic spray pyrolysis (APUSP) is another interesting design suitable for growth of stacked films or controlled doping and development of superlattices [106,157,158,160]. In APUSP, two more ultrasonicator-containing chambers are harnessed. Each chamber contains the appropriate precursor solutions that are to be deposited – the host and the dopant etc. The “sonicators” in these chambers are controlled by a pulse generator one at a time in an asynchronous manner. The period of each chamber's pulse determines the level of doping, or the thickness of the layers in the superlattices.

In a typical APUSP (Michel Lopez and Zea 2006 Ref. 191) an inert gas is first introduced to the reaction chamber at relatively low and steady flow rate for about 30 minutes to drive the air out. The nebulised solutions – precursor and dopant are delivered to the substrates in pulses through the nozzles.

Each spray lasts 5 seconds for both but after the spray of the dopant is conducted, a delay of 2-4 seconds was employed to ensure that the introduced dopant was completely decomposed before conveying a pulse spray of the host. The deposition is carried out by repeatedly performing these spray processes. It took 12-14 s for each cycle and the deposition time lasted for 15 -30 mins for the preparation of one sample.

An appropriate interval between the pulse spray of dopant and host solutions play an important role in depositing high crystallinity films. There are cases where the precursor liquid to be sonicated passes through the ultrasonicator and introduced from the top rather than from the bottom.

This design has the advantage of high yield of final desired product. However, introducing droplets from below has the advantage of selecting on the small droplets with most of the large one returning to the precursor under gravity. In both the Lee *et al.* (1998) [106,157] set up and that of Patil & Patil (2000) [73,104,120,124,374,375,430,439,492] the substrate has its own special heater apart from the standard furnace. Contrary to heating substrates, Kang & Park (1999) [113,114,118,145,161,170,176,178,198,239,262], realised that subjecting the particle collector to coolants such as liquid nitrogen helped prevent Ag nano-particle agglomeration and they become well dispersed in ZnO.

Note that in their USP design, they included a temperature controlling water bath around the precursor container to prevent changes in temperature and pressure which in turn have an effect on droplet size as shown in the previous sections.

7.2. *Electrostatic Nebulizer USP*

Recently, another innovation to USP [Zaouk *et al* Ref. 206, Chen *et al* Ref 240, 249, Chang & Hwang, Ref. 304, Bin *et al* Ref. 332, Lee *et al*, Ref. 458 and Min *et al* Ref 502, 503] has been the manner in which droplets are produced from the precursor liquid. Apart from spraying with ultrasonic nebulisers, it has been realized from the days of Lord Kelvin that by applying a high potential difference to the liquid surface makes such a surface erupt into liquid droplets. In electrostatic assisted USP (EAUSP), a high tension is applied between the liquid and the substrate. There are cases where the precursor liquid to be sonicated passes through the ultra-sonicator and introduced from the top rather than from the bottom

This design has the advantage of high yield of final desired product. However, introducing droplets from below has the advantage of selecting on the small droplets with most of the large one returning to the precursor under gravity. If a liquid is forced to flow through a small nozzle which is subjected to an electric field, the liquid will exit the outlet in different forms or modes as a result of different electrodynamic mechanisms. These modes include among others dripping mode, cone mode, cone-jet mode and spindle mode [Zaouk *et al.*, 2000 Ref. 206]. The kind of mode the spray displays depends on the electrical potential applied to the nozzle, the flow rate, the conductivity and the surface tension.

For film deposition, the cone-jet mode is the most suitable, it is a continuous mode and the formation of a homogeneous fine spray is possible. In this mode, there exists the so-called "Taylor cone" with 49.3° half angle at the apex of the cone (see Taylor instability in the previous section). This cone is extended by a jet which breaks up into spray droplets to generate an aerosol of the precursor liquid. Chen *et al.* [140] final particle morphology has large particles and large flakes. This could be due to agglomeration of droplet as they descend.

The best way to select only the small droplets is to have the substrate above the spray. The large ones cannot make it to the substrate and therefore are forced to return to the ultrasonic nebuliser. As for Zaouk *et al.*, the potentials need to be optimized for self assembly.

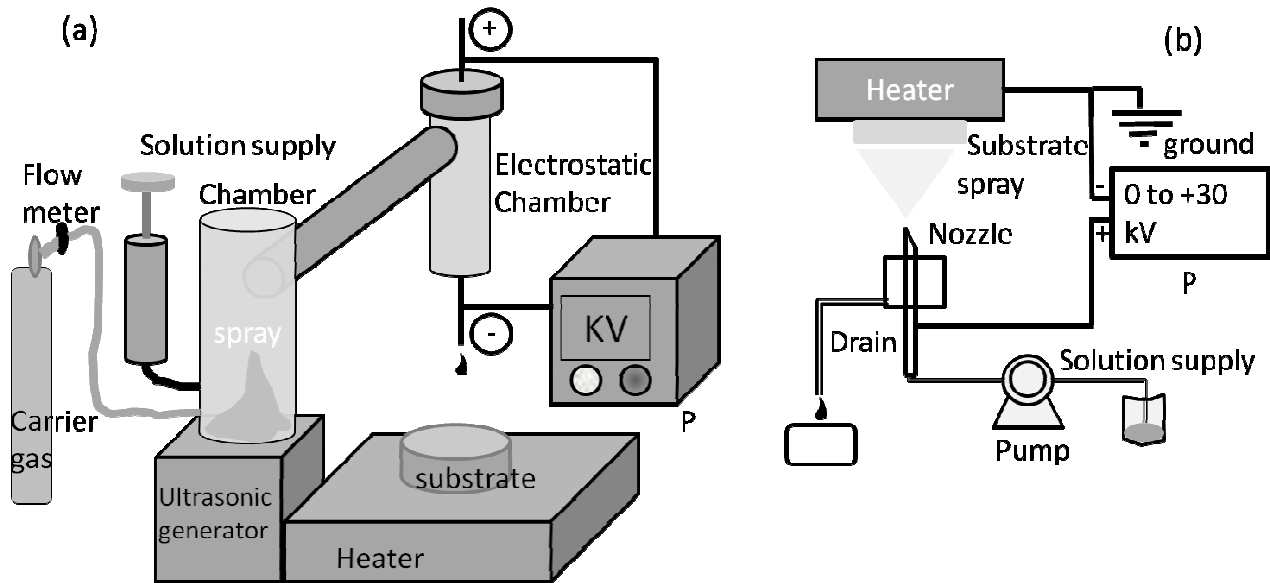


Fig. 15 (a) Electrostatic assisted USP (EAUSP), note that aerosol are directed onto the substrate from the top (Redrawn from Chen *et al.*, Mater. Res. Bul, 2007) (b) Electrostatic spray deposition (ESD); note that deposition is from bottom to top (Adapted from Zaouk *et al.*)

7.3. Infrared USP

An interesting USP system employing a novel heating source was reported by Matsuzaki and co-workers [117] when synthesizing yttria stabilized zirconia thin films. Their substrates temperatures were controlled by heating a “susceptor” with an infrared radiation heater.

The substrate temperature could be tuned from 873 K to 1023 K. It is interesting to note that grain size increases with substrate temperature, the Arrhenius plot shows that the activation energy for yttria stabilized zirconia is about 68 kJ mol^{-1} and grain size increases with increase in deposition rate. The particles obtained by this work were rather large in general. This could be due to (1) agglomeration at higher substrate temperatures an effect known as the Oswald’s ripening (2) spraying from the top as alluded to before.

The Oswald’s ripening observed here should be distinguished from the opposite effect which was observed recently and reported in Mwakikunga *et al.* [55,243-247,333,511].

Mwakikunga *et al.* found spheres of WO_3 obtained from USP to shrink in diameter as the furnace temperature was increased without heating the substrates where the perfect sphere would land. In the case of shrinkage in diameter as a function of surrounding temperature, it was found that the data was in agreement with the Tiller equation given as

$$d_c = \frac{4\sigma_e\Omega_M}{RT \ln(p/p^*)} \quad (48)$$

σ_e is the interfacial energy between the nucleating materials and the surrounding environment and Ω_M is the molar volume of the nucleating material. A number of authors have used this equation in explaining the growth of nano-wires by chemical vapour deposition [Tan *et al.*, APL (2003) Ref. 148]

7.4. Flame-Assisted USP

An interesting kind of pyrolysis is called flame assisted USP (FAUSP) [108,130,159,208,209,241,344]. FAUSP was developed in the 1980’s. It operates by injecting the spray of a precursor solution obtained from an aerosol generator into a combustion chamber where the individual droplets are rapidly combusted. Fuel such as natural gas or hydrogen is introduced in order to generate the appropriate high temperature. In some case, instead of external fuels, flammable alcoholic solutions are used as precursors.

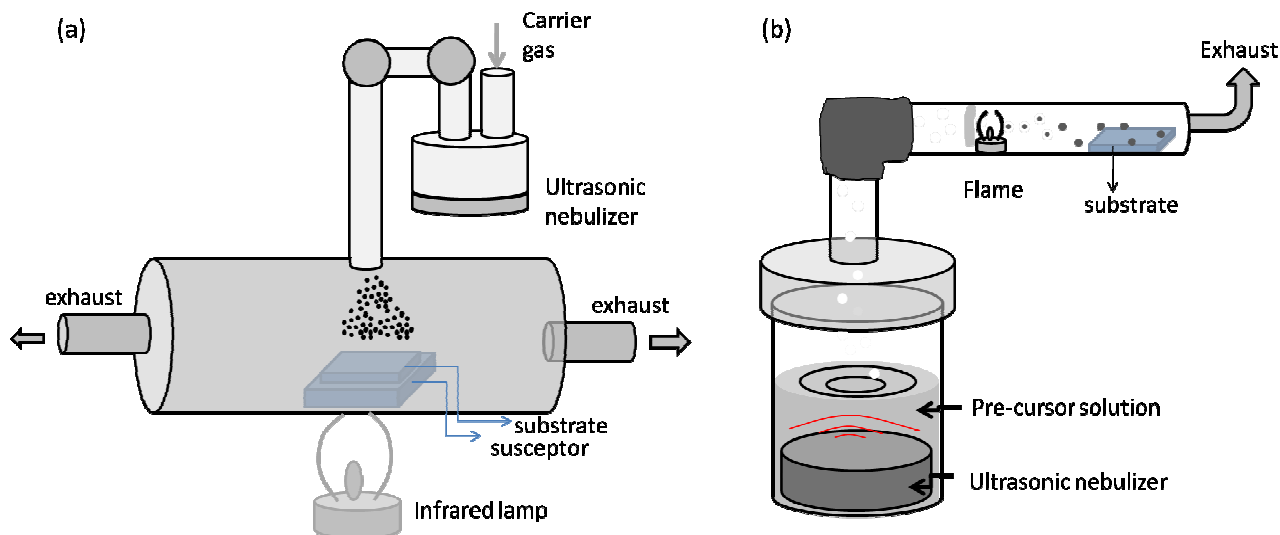


Fig. 16 (a) Infrared USP and (b) Flame assisted USP (FAUSP) Redrawn from: Chen *et al.*, Eur. J. Solid State & Inorg. Chem. (1998)

8. Morphology, Structural and Other Properties of Materials Obtained by USP

8.1. Solid and Hollow Spheres

The spherical shape of the particles definitely comes from the spherical droplets from the precursor liquid. When scanning electron microscopy is performed on these particles one can see the manifestation of spherical daughter particles from mother spherical liquid droplets. The particle size may be less than $3\ \mu\text{m}$ [see Fig. 18 from Oh *et al* Refs. 169,176,184,198,199,202,227,239,432,438] from the four SEM micrographs (a) but at higher magnification with TEM (bottom right) the morphology changes to one showing that the spheres are composed of numerous crystallites whose size as determined by the Scherrer equation from X ray diffraction shows they are nano-crystalline. The crystallite size increases as the calcinations temperature is increased. Bucko, Ref. 209]. This is equivalent to increasing substrate temperature and thereby increasing particle and crystallites sizes as seen above. However, this is to be contrasted from the in-situ furnace temperature increase which has the reverse effect of decreasing the particle and crystallite size as shown in Fig. 20 [from M Yuan *et al.* (1998) [Refs 108, 112] also found hollow spheres when preparing zirconia and yttria-stabilized- zirconia (YSZ) fine powders by flame- assisted ultrasonic spray pyrolysis. This was attributed to the presence of nitrates in the precursor.

Prior to this study, Messing *et al.* [96,98] had studied the spray pyrolysis of nitrate solutions and proposed a mechanism to explain the particle morphology. During the pyrolysis of spray droplets in the flame, the evaporation of the solvent and the reaction/decomposition of the solute proceed successively from the outer part to the inner part of the droplets. When a nitrate solute with a relatively low melting point is present, it melts to fill the pores of the structure. The molten salt will inhibit the removal of the trapped solvent in the inner parts of the droplets as a result of the reduction of the gas permeation. This leads to a build-up of internal gas pressure and, finally, explosion or foaming of the particles to form hollow particles or particle fragmentation with a broad size distribution.

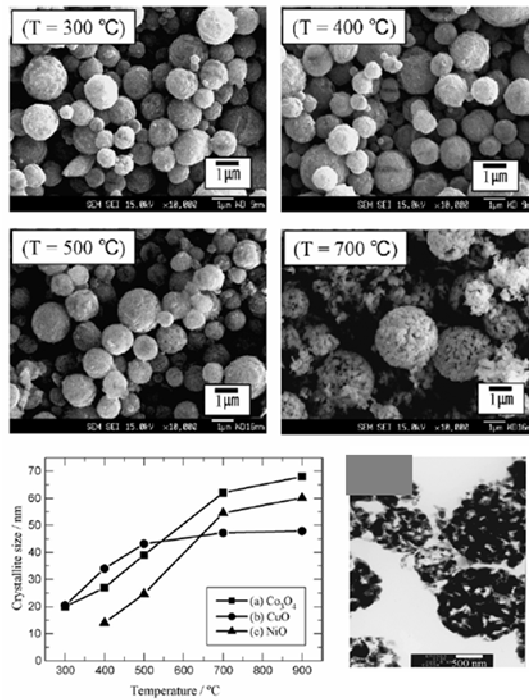


Fig. 17 The figure shows the effect of calcination temperature on morphology and crystallinity of Co_3O_4 , CuO and NiO . From S. W. Oh *et al.*

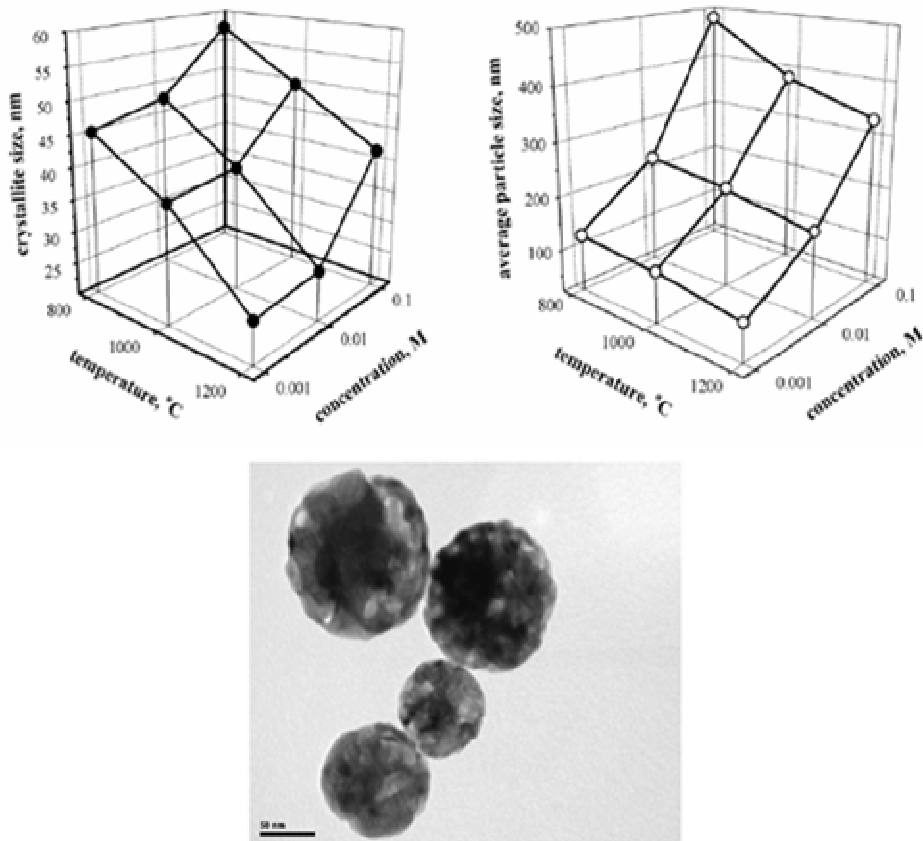


Fig. 18 Effect of furnace temperature during synthesis on the morphology and crystallinity of BZrO_3 nanopowders by USP (from M.M. Bucko & J. Obłakowski, *J Eur Ceram Soc.*, (2007) [Ref. 209])

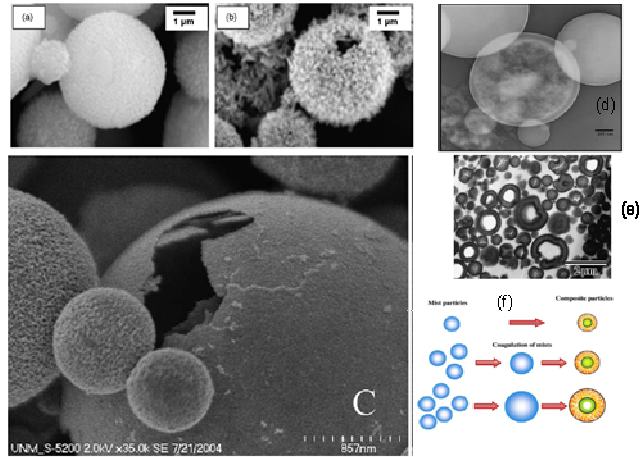


Fig. 19 (a) and (b) SEM images of hydroxyapatite (Hap) powders by the USP/SAD method showing the gaping hole in one of the spheres in (b) an indication of the possibly hollow nature of these spheres [From G.-H. An *et al.*, Mater. Sci. Eng. (2007) Ref. 163] (c) More vivid proof of hollow NiO–Sm_{0.2}Ce_{0.8}O_{1.9} composite spheres [S. Suda *et al.*, Solid State Ionics (2006) Ref. 196] (d) and (e) HRTEM image of LiFePO₄/C composite prepared at 450°C showing a shell structure and the intersection of the shells of other spheres [From M. R. Yang, J. Power Sources (2006) Ref. 201,204] (f) A conceptual model proposed by Yang *et al.* (2006) on how the hollow LiFePO₄/C composites form with or without voids.

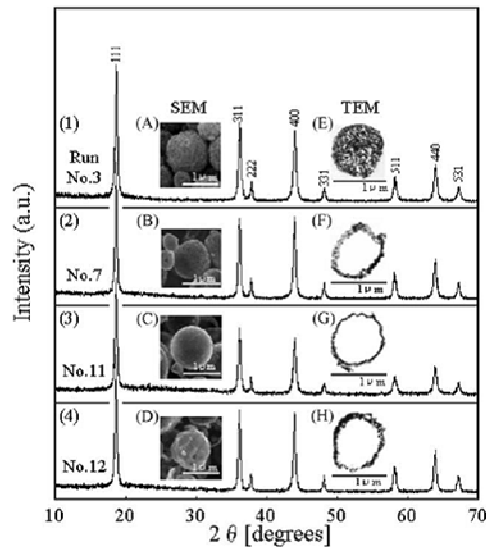


Fig. 20 Examples of XRD, SEM and TEM micrographs of LiMn₂O₄ particles prepared from various precursors (1) dense LiMn₂O₄ with porous surface structure (2) hollow LiMn₂O₄ particles with hybrid surface structure (3) hollow LiMn₂O₄ particles with smooth surface structure and (4) hollow LiMn₂O₄ with shrinkage surface structure. From Matsuda & Taniguchi, *Journal of Power Sources* (2004)

8.2. One-Dimensional Nanostructures from USP: Nanowires, Nanoribbons, Nanorods

Of interest, apart from the production of nano-particles by ultrasonic spray pyrolysis, has been the attainment of one-dimensional structures. Many of the one-dimensional structures have been micro-sized such as the ZnO nanorods grown almost at right angles to the substrate surface [212,214,233] as shown in Fig. 21. This one-dimensional growth only happens at specific conditions. Note that as furnace temperature is reduced that micro-rod diameter decreases.

Another interesting case of one dimensional growth by USP was observed by Htay *et al.* [242,254,317,367,477] who reported micro-sized platelets, wires and tips of ZnO obtained at controlled conditions. Temperature of synthesis was found to dictate the morphology of the micro and submicron-structures that they obtained. In this case different furnace temperatures yield different structures- rods, wires

or platelets. One-dimensional growth from spheres of WO_3 which transform themselves into W_xO_y nanowires after thermal annealing at 500°C in argon for 17 hours [Ref. 243-247,333,511] has been observed.

Recently dense one-dimensional nano-ribbons of VO_2 grown by USP at 700°C in argon carrier gas without the need for thermal annealing [Fig. 24 and 25] were also observed [unpublished]. Their electronic transition temperature at 70°C was confirmed using a four-point probe technique. It was found that for the same synthesis conditions, furnace temperature, precursor flow rate etc, vanadium oxides yielded mostly nanobelts, nanoribbons and sheets where tungsten oxides showed nanowires and nanorods.

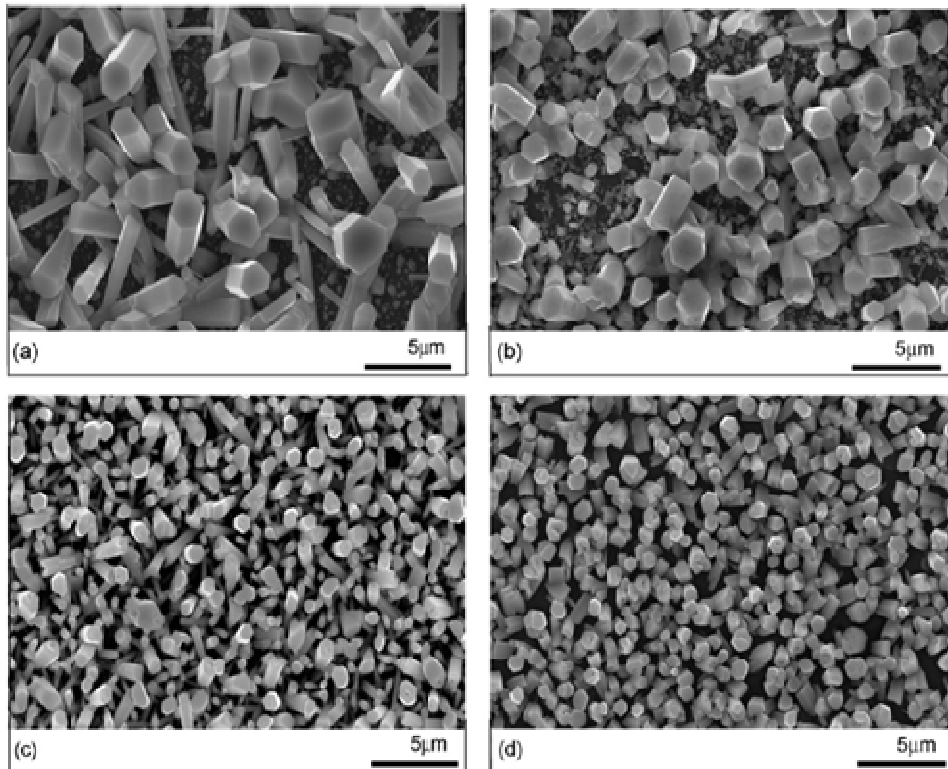


Fig. 21 SEM images of ZnO microrods deposited by USP at (a) 550°C (b) 500°C , (c) 450°C and (d) 400°C [From U. Alver *et al.*, Mater. Chem. Phys. (2007) Ref. 233]

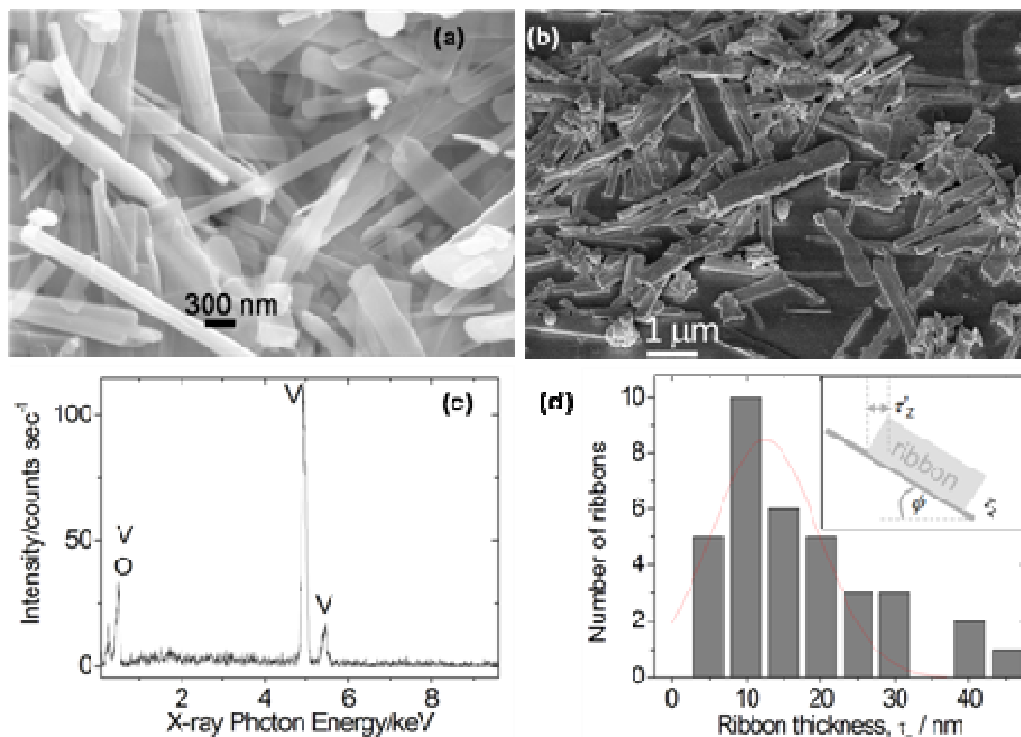


Fig. 22 (a) SEM micrograph of VO₂ nano-ribbons (b) tilted at $\phi = 54^\circ$ (c) an EDS spectrum showing the V and O peaks on a carbon adhesive tape substrate and (d) size (thickness) distribution histogram (thickness determined from $\tau_z = \tau'_z / \sin\phi$ as illustrated in the inset of (d))

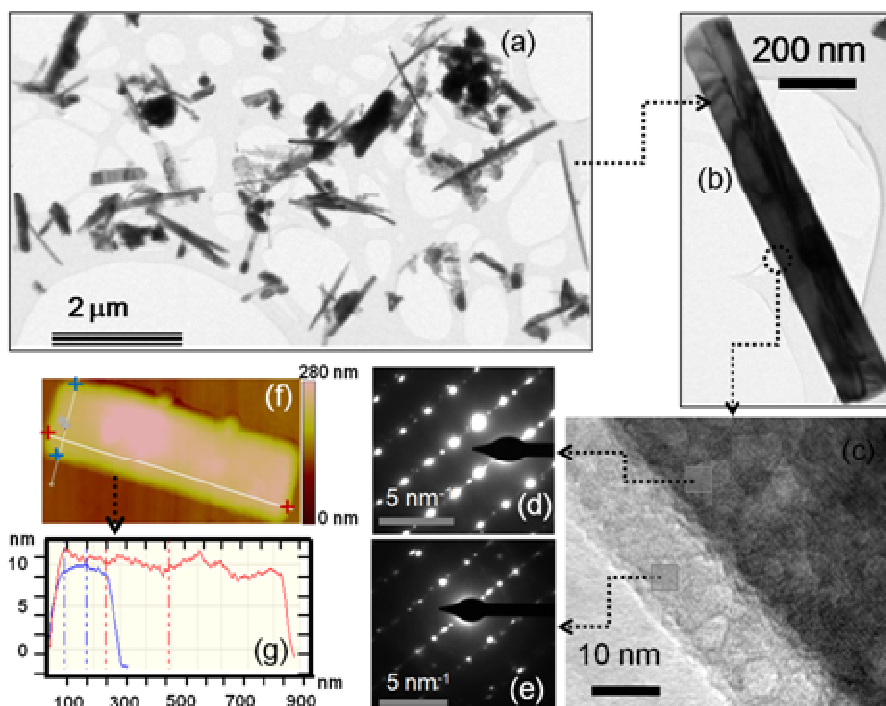


Fig. 23 Transmission electron microscopy (a) low resolution image (b) low resolution on a single ribbon (c) higher resolution on the edge of ribbon revealed bi-layered structure: V₂O₅ and VO₂ and in some ribbons a core-shell structure. (d) and (e) are SAED patterns for V₂O₅ and VO₂ regions respectively (f) AFM height image of a single VO₂ nano-ribbon. The profile (g) shows that the VO₂ ribbon is typically 10 nm thick.

9. Conclusion and Outlook

The review has shown the humble beginning of the ultrasonic spray pyrolysis: from the phenomenon of ejection of liquid droplets by high frequency sound waves called ultrasound since Michael Faraday to the highly sophisticated thin film and powder production technologies employing this phenomenon. Since then some theories and experiments have been performed to explain this phenomenon. One mechanism is the capillary wave mechanism where sound waves operate only on the liquid surface. Droplet size depends on surface tension, liquid density and the frequency of the sound. In the cavitation mechanism, sound waves may introduce turbulence in the bulk of the liquid leading to cavities which may also erupt to the surface in a random fashion but whose distribution is described by the Weber number, the Ohnesorge number and the so-called Intensity number. In this case, the liquid droplet size, apart from depending on surface tension, density and frequency of the ultrasound wave, also depends on the viscosity and the stated numbers.

We have also introduced the thermodynamics of how the droplet size should change when the temperature and pressure in the liquid changes in which case density, surface tension, density, viscosity and hence the Weber and other numbers also vary. The review also covers the applications of these phenomena which culminate into what has been branded ultrasonic spray pyrolysis. Publications reporting synthesis of various materials by this method are shown to increase very rapidly showing that there is this method is growing in popularity around the world. From the trend of publications per year, it has been demonstrated that USP will be a standard method in many labs in the next generations.

The success of any user of this method will depend on the understanding of the dynamics of particle generation from droplet formation to the deposited particles which is lacking in many texts.

Acknowledgements

This work was supported by the Joint Japan/World Bank Graduate Scholarship Programme. Useful discussions with Prof Malik Maaza and Prof Elias Sideras-Haddad are acknowledged.

References

1. Greek Lexicon, also from the Hebrew Lexicon, "a pile of fuel, pyre, a pile of wood"
2. E. Mendoza, S.J. Henley, C.H.P. Poa, G.Y. Chen, C.E. Giusca, A.A.D.T Adikaari, J.D. Carey and S.R.P. Silva, *Large area growth of carbon nanotube arrays for sensing platforms*, Sensors and Actuators B: Chemical 109 (1), 75-80 (2005).
3. C.X. Wang and G.W. Yang, *Thermodynamics of metastable phase nucleation at the nanoscale*, Mater. Sci. & Eng.: R: Reports 49 (6) 157 (2005). A. Dollet, Surf. & Coatings Technol. 177-178, 245 (2004)
4. F. Maury and F. Senocq, *Review of CVD technique*, Surf. Coat. Technol. 163-164, 208 (2003)
5. K. L. Choy, *Chemical vapour deposition of coatings*, Prog. Mater. Sci., 48, 57 (2003)
6. S. Stewart and R. Ahmed, *Rolling contact fatigue of surface coatings—a review*, Wear 253 (11-12) 1132 (2002)
7. D. Choudhary and J. Bellare, *Manufacture of gem quality diamonds: a review*, Ceramics International 26 (1) 73 (2000)
8. O. I. Buzhinskij and Yu. M. Semenets, *Thick boron carbide coatings for protection of tokamak first wall and divertor*, Fusion Eng. & Design 45(4) 343 (1999)
9. K.P de Jong, *Synthesis of supported catalysts*, Curr. Opinion Solid State & Mater. Sci. 4(1) 55 (1999)
10. M. Asmann, J. Heberlein and E. Pfender, *A review of diamond CVD utilizing halogenated precursors*, Diamond and Related Materials 8(1) 1 (1999)
11. S. Kaplan, *Plasma processes for wide fabric, film and non-wovens*, Surf. & Coatings Technol. 186(1-2) 214 (2004)
12. G. M. Ferreira, A. S. Ferlauto, Chi Chen, R. J. Koval, J. M. Pearce, C. Ross, C. R. Wronski and Robert W. Collins, *Kinetics of silicon film growth and the deposition phase diagram*, J. Non-Cryst. Solids 338-340, 13 (2004)
13. H. Matsumura, H. Umemoto and A. Masuda, *Cat-CVD (hot-wire CVD): how different from PECVD in preparing amorphous silicon*, J. Non-Cryst Solids 338-340, 19 (2004)
14. H. Fujiwara, M. Kondo and A. Matsuda, *Nucleation mechanism of microcrystalline silicon from the amorphous phase*, J. Non-Cryst Solids 338-340, 97 (2004)

15. B. Rech, O. Kluth, T. Repmann, T. Roschek, J. Springer, J. Müller, F. Finger, H. Stiebig and H. Wagner, *New materials and deposition techniques for highly efficient silicon thin film solar cells*, Solar Energy Mater. & Solar Cells 74(1-4), 439 (2002)
16. B. R. Rogers and T. S. Cale, *Plasma Processes in Microelectronic Device Manufacturing*, Vacuum 65(3-4), 267 (2002)
17. A. O. Sezer and J. I. Brand, *Chemical vapor deposition of boron carbide*, Mater. Sci. & Eng. B 79(3) 191 (2001)
18. A. G. Aberle, *Overview of SiN surface passivation of crystalline silicon solar cells*, Solar Energy Mater. & Solar Cells 65(1-4) 239 (2001)
19. S. Muhl and J. M. Méndez, *A review of the preparation of carbon nitride films*, Diamond and Related Mater 8(10), 1809 (1999)
20. H. Matsumura, H. Umemoto and A. Masuda, *Cat-CVD (hot-wire CVD): how different from PECVD in preparing amorphous silicon*, J. Non-Cryst Solids 338-340, 19 (2004)
21. R. E. I. Schropp, *Present status of micro- and poly-crystalline silicon solar cells made by hot-wire chemical vapour deposition*, Thin Solid Films 451-452, 455 (2004)
22. B. Schroeder, *Status report: solar cell related research and development using amorphous and microcrystalline silicon deposition by HW (Cat) CVD*, Thin Solid Films 430(1-2), 1 (2003)
23. A. Gallagher, *Some physics and chemistry of hot wire deposition*, Thin Solid Films 395(1-2), 25 (2001)
24. R. S. Crandall and X. Liu, *Elastic properties of amorphous and crystalline silicon*, Thin Solid Films 395(1-2) 78 (2001)
25. B. Schroeder, U. Weber, H. Seitz, A. Ledermann and C. Mukherjee, *Current status of the thermo-catalytic (hot wire) CVD of thin silicon films for photovoltaic applications*, Thin Solid Films 395(1-2) 298 (2001)
26. A.O. Sezer and J. I. Brand, *Chemical vapour deposition of boron carbide*, Mater. Sci. & Eng. B 79 (3), 191 (2001)
27. D. Choudhary and J. Bellare, *Manufacture of gem-quality diamonds: a review*, Ceramics International 26 (1), 73 (2000)
28. P. Patil, *Versatility of chemical spray pyrolysis*, Mater. Chem. & Phys. 59, 185 (1999)
29. A. Sheth, H. Schimdt and V. Lasrado, *Chemical vapour deposition of various silicides*, Appl. Supercond. 6 (10-12), 855 (1998)
30. H. Marsh, M. Martinez-Escandell, F. Rodriguez-Reinoso, *Synthesis of carbon nanostructures*, Carbon 37, 363 (1999)
31. M. Sternitzke, *Production of ceramics by spray pyrolysis*, J. Eur. Ceram. Soc. 17, 1061 (1997)
32. S. Muhl, J. M. Mendez, *Synthesis of diamond by CVD*, Diamond & Related Mater 8, 1809 (1999)
33. P. Tartaj, M. P. Morales, T. Gonzalez-Carreno, S. Veintemillas-Verdaguer, C. J. Serna, *Carbon cokes*, J. Magnetism & Magnetic Mater 290-291, 28 (2005)
34. P. Tartaj, M. P. Morales, S. Veintemillas-Verdaguer, T. Gonzalez-Carreno, C. J. Serna, *CVD for semiconductors*, J. Phys. D: Appl. Phys. 36, R182 (2003)
35. A. J. Yule and Y. Al-Suleimani, *Ultrasonic nebulisation and droplet generation*, Proc. R. Soc. Lond. A 456, 1069 (2000)
36. F. Barreras, H. Amaveda, A. Lozano, *Ultrasonic spray*, Experiments in Fluids 33, 405 (2002)
37. V. G. Nevolin, *Surface phenomena and droplet generation*, Inzhenerno-Fizicheskii Zhurnal 47 (6), 1028 (1984) Translated by Plenum Publishing Corporation UDC 532.59:532.501.34, 1482 (1985)
38. See for example some NASA Tech Briefs "Producing Quantum Dots by Spray Pyrolysis on <http://www.techbriefs.com/content/view/46/34> or <http://www.techbriefs.com/tsp>
39. R. W. Wood and A. L. Loomis, *Experimental generation of droplets by ultrasonic waves*, Phil. Mag. 7, 417 (1927)
40. M. Faraday, *Capillary waves due to sound*, Phil. Trans. R. Soc. Lond. 121, 319 (1831)
41. J. W. S. Rayleigh, *The Theory of Sound Vol.2*, Dover Publications, N.Y., 344 (1945)
42. H. Lamb, *Hydrodynamics*, Macmillan, London, 708 (1931)
43. T. K McCubbin Jr., *Instability in the Taylor agitation*, J. Acoust. Soc. Am. 25, 1013 (1953)
44. K. Bisa, K Dirnagl and R. Esche, *Taylor waves*, Siemens-Z. 28, 341 (1954)
45. T. B. Benjamin and F Ursell, *Is Taylor instability responsible for droplet generation?* Proc. R Soc London A 225, 505 (1954)

46. V. I. Sorokin, *Taylor instability from sound*, Soviet Phys. Acoust 3, 17 (1957)
47. W. Eisenmenger, *Acoustic phenomenon affects surface stability*, Acoustica 9, 327 (1959)
48. J. N. Antonevich, *Ultrasound waves and water*, TRE Trans. on Ultrasonic Eng. PGUE-7, 6 (1959)
49. R. Lang, *Diameter of droplets from ultrasound waves*, J. Acoust. Soc. Am. 34, 6 (1962)
50. D. Sindayihebura and L. Bolle, *Capillary waves and the diameter of the droplets*, Atomization Sprays 8, 217 (1998)
51. G. I. Taylor, *Instability of capillary waves*, Proc. R. Soc. A CCI 192 (1950)
52. R. L. Peskin and R. J. Raco, *On the modelling of droplet diameter from ultrasonic agitation*, J. Acoust. Soc. Am. 35, 1378 (1963)
53. V. Jokanovic, D. Janackovic, A. M. Spasic, D. Uskokovic, *Design of nanostructures of TiO₂*, Mater. Trans. JIM 37, 627 (1996)
54. V. Jokanovic, M. D. Dramicanin, Z. Andric, *TiO₂ production by spray pyrolysis*, Acta. Chim. Slov. 53, 23 (2006)
55. B. W. Mwakikunga, MSc Thesis, University of the Witwatersrand (2006) <http://8080-witsetd.wits.ac.za/innopac.wits.ac.za/dspace/handle/123456789/2082>
56. J. M. Nedeljkovic, Z. V. Saponjic, Z. Rakocevic, V. Jokanovic, D. P. Uskokovic, *Synthesis of novel oxides by ultrasonic spray pyrolysis*, Nanostructured Mater. 9, 125 (1999)
57. Z. V. Saponjic, Z. Rakocevic, N. M. Dimitrijevic, J. M. Nedeljkovic, V. Jokanovic and D. P. Uskokovic, *Calculated and experimental diameter of deposited TiO₂ particles*, Nanostructured Mater. 10(3), 333 (1998)
58. K. Söllner, *Explanation of the Wood & Loomis demonstration*, Trans. Faraday Soc. 32, 1537 (1936)
59. E. L. Gershenzon, O. K. Eknadiosyants, *Cavitation mechanism re-visited*, Sov. Phys. Acoust. 10, 127 (1964)
60. O. K. Eknadiosyants, *On the cavitation of fluid by turbulent sound waves*, Sov. Phys. Acoust. 14, 80 (1968)
61. H. S. Fogler, K. D. Timmerhaus, *Sound cavitation of liquid medium*, J. Acoust. Soc. Am. 39, 515 (1965)
62. Y. Y. Boguslaskii, O. K. Eknadiosyants, *On the sound agitation from the deep*, Sov. Phys. Acoust. 15, 341 (1969)
63. C Chiba, *Viscosity of a liquid and the cavitation*, Bull. J. Soc. Mech. Eng. 18, 376 (1975)
64. J. D. Bassett and W. W. Bright, *J. Aerosol Sci.* 7, 47 (1976)
65. R. Bellman, R. H. Pennington, *Effect of viscosity and surface tension on the Taylor instability*, Quant. Appl. Math. 12, 151 (1954)
66. V.M Entov, A. L. Yarin, *On the kinematics of liquids and their viscosity*, J. Fluid Mech. 140, 91 (1984)
67. J. O. Hinze, *Viscosity and surface tension*, A I Ch. E. J. 1, 289 (1955)
68. M. M. Clark, *Effects of surface tension and the relative fluid velocity on the droplet formation*, CES 43, 671 (1988)
69. M. M. Clark, *Effects of viscosity and density on the droplet formation* CES 43, 681 (1988)
70. T. Mochida, *Empirical study of droplet diameter as a function of surface tension, density and the flow rate*, Proc. ICLASS-78, 193 (1978)
71. S. C. Tsai, P. Childs, P. Luu, *Correlation between droplet diameter and viscosity*, AIChE. J. 42 (120, 3340 (1996)
72. R. Rajan, A. B. Pandit, *Correlations to predict the droplet size in ultrasonic atomization*, Ultrasonics 39, 235 (2001)
73. B. Avvaru, M. N. Patil, P. R. Gogate, A. B. Pandit, *Ultrasonic atomization: Effect of liquid phase properties*, Ultrasonics 44, 146 (2006)
74. C. J. Lynde, *The effect of pressure on surface tension*, Phys. Rev. (Series 1) 22, 181 (1906)
75. W. Sachs, V. Meyn, *Pressure and temperature dependence of the surface tension in the system natural gas/water*, Colloids & Surf A: Physicochemical Eng. Aspects 94, 291 (1995)
76. E. W. Hough, M. J. Rzasz and B. B. Wood, *Trans. AIME.* 192, 57 (1951)
77. H. Y. Jennings and G. H. Newman, Jr., *J. Soc. Pet. Eng.*, 171 (1971)
78. R. Massoudi and A. D. King, Jr., *J. Phys. Chem.* 78, 2262 (1974)
79. C. Jho, D. Nealon, S. Shogbola and A. D. King, Jr., *J. Colloid Interface Sci.*, 65, 141 (1978)
80. S. J. Palmer, *The effect of temperature on surface tension*, Phys. Ed 11, 119 (1976)
80. R. H. Fowler, *A tentative statistical theory of Macleod's equation for surface tension, and the parachor*, Proc. R. Soc. A159, 229 (1937)

81. H. S. Green, *The Molecular Theory of Fluids*, Dover Publications, NY, 194 (1969)
82. J. R. Henderson, *The surface tension compressibility relation*, Mol. Phys. 39, 709 (1980)
83. H. Park, R. B. Thompson, N. Lanson, C. Tzoganakis, C. B. Park, P. Chen, *Effect of temperature and pressure on surface tension of polystyrene in supercritical carbon dioxide*, J. Phys. Chem. B 111, 3859 (2007)
84. J. Escobedo, G. A. Mansoori, *Surface tension prediction for pure fluids*, AIChE. J. 42, 1425 (1996)
85. M. E. Boudh-Hir, G. A. Mansoori, *Statistical mechanics basis of Macleod's formula*, J. Phys. Chem. 94, 8362 (1990)
86. J. D. Pandey, V. Sanguri, S. B. Tripathi, R. K. Mishra, N. K. Soni, *Theoretical prediction of surface tension of ternary liquid system (nitrogen + oxygen + argon) at elevated temperature and different pressure*, J. Colloid & Interface Sci. 274, 331 (2004)
87. P. L. Wong, R. Wang, S. Lingard, *Pressure and temperature dependence of the density of liquid lubricants*, Wear 201, 58 (1996)
88. O Redlich and J N Kwong, *Chem Rev.* 44, 1197 (1949)
88. M. N. Topp, *Generation of droplets from below the liquid surface*, Aerosol. Sci. 4, 17 (1973)
89. P. G. Wright, *The variation of viscosity with temperature*, Phys. Ed. 12, 323 (1977)
90. P. W. Bridgman, *Viscosities to 30,000 kg/m³*, Proc. Am. Acad Arts Sci. 77, 117 (1949)
91. S. Bair, J. Jarzynski, W. O. Winer, *The temperature, pressure and time dependence of lubricant viscosity*, Tribology International 34, 461 (2001)
92. R. S. Fein, *Possible role of compressional viscoelasticity in concentrated contact lubrication*, ASME J Lubr Tech Ser F 89, 127 (1967)
93. G. Harrison, E. G. Trachman, *The role of compressional stress on free volume of lubricants*, ASME J Lubr Tech 94, 306 (1972)
94. S. Yasutomi, S. Bair, W. O. Winer, *An application of a free volume model to lubricant rheology*, ASME J Tribology 106, 291 (1984)
95. S. Gürmen, S. Stopić and B. Friedrich, *Synthesis of nanosized spherical cobalt powder by ultrasonic spray pyrolysis*, Mater. Res. Bulletin 41(10), 1882 (2006)
96. S. C. Zhang, G. L. Messing, *Size of particles after pyrolysis*, J. Am. Ceram. Soc. 73, 61 (1990)
97. M. Langlet and J. C. Joubert in *Chemistry of Advanced Materials* (C. N. R. Rao, Ed.), Blackwell, Oxford, p23-45 (1992)
98. G. L. Messing, S. C. Zhang, G. V. Jayanthi, *Modeling of particle morphology and size*, J. Am. Ceram. Soc. 76, 2707 (1993)
99. C. N. R. Rao, *Chemical approaches to the design of oxide materials*, Pure & Appl. Chem. 66, 1765 (1994)
100. J. M. Nedeljkovi , Z. V. Aponji, Z. Rako evi , V. Jokanovi and D. P. Uskokovi, *Effects of H₂O₂ on the morphology of ZrO₂ powder prepared by ultrasonic spray pyrolysis*, Nanostructured Mater. 9(1-8), 125 (1997)
101. E. Andrade, M. Jergel, J. C. Cheang-Wong, A. Conde-Gallardo and C. Falcony, *Ion beam analysis of HTc superconducting Tl-based films*, Nucl. Instrum. & Meth. Phys. Res. B: Beam Interactions with Materials and Atoms 122(4), 677 (1997)
102. Y. Harima, K. Matsumoto, Y. D. Wang and K. Yamashita, *Photoelectrolytic micelle disruption method for preparation of free patterns of pigment images*, Thin Solid Films 301(1-2), 95 (1997)
103. P. Fortunato, A. Reller and H. R. Oswald, *Generation of mixed metal oxides by use of an ultrasonic aerosol thermal decomposition process*, Solid State Ionics 101-103, 85 (1997)
104. P.S. Patil, E.A. Ennaoui, C.D. Lokhande, M. Müller, M. Giersig, K. Diesner and H. Tributsch, *Characterization of ultrasonic spray pyrolysed ruthenium oxide thin films*, Thin Solid Films 310(1-2), 57 (1997)
105. E. Djurado and M. Labeau, *Second phases in doped lanthanum gallate perovskites*, J. Eur. Ceram. Soc. 18(10), 1397 (1998)
106. Y.J. Lee, H.B. Kim, Y.R. Roh, H.M. Cho and S. Baik, *Development of a saw gas sensor for monitoring SO₂ gas*, Sensors & Actuators A: Physical 64(2), 173 (1998)
107. R. Abraham, F. Guenard, K. Lebbou, S. Trosset, M. T. Cohen-Adad, J. L. Jorda and M. Couach, *Elaboration of Tl_{0.5}Pb_{0.5}Sr₂CaCu₂O_x Superconducting Phases By an Ultrasonic Spray-Pyrolysis Process*, Mater. Res. Bulletin 33(2), 253 (1998)

108. C.H. Chen, F.L. Yuan and J. Schoonman, *Spray pyrolysis routes to electroceramic powders and thin films*, Eur. J. Solid State & Inorganic Chem. 35(2), 189 (1998)
109. Dj. Janackovic, V. Jokanovic, Lj. Kostic-Gvozdenovic and D. Uskokovic, *Synthesis of mullite nanostructured spherical powder by ultrasonic spray pyrolysis*, Nanostructured Mater. 10(3), 341 (1998)
110. H. K. Singh and O. N. Srivastava, *Cadmium induced growth of 2223 phase and Tc enhancement in TBCCO high Tc thin films*, Phys. Lett. A 240(4-5), 253 (1998)
111. D. Briand, M. Labeau, J. F. Currie and G. Delabouglise, *Pd-doped SnO₂ thin films deposited by assisted ultrasonic spraying CVD for gas sensing: selectivity and effect of annealing*, Sensors & Actuators B: Chemical 48(1-3), 395 (1998)
112. F. L. Yuan, C. H. Chen, E. M. Kelder and J. Schoonman, *Preparation of zirconia and yttria-stabilized zirconia (YSZ) fine powders by flame-assisted ultrasonic spray pyrolysis (FAUSP)*, Solid State Ionics 109(1-2), 119 (1998)
113. Y. C. Kang, S. B. Park, I. W. Lenggoro and K. Okuyama, *Preparation of non-aggregation YAG:Ce phosphor particles by spray pyrolysis*, J. Aerosol Sci. 29, S911 (1998)
114. S. B. Park, Y. C. Kang, I. W. Lenggoro and K. Okuyama, *Preparation of Y₂O₃:Eu phosphor without post-treatment by gas phase reaction*, J. Aerosol Sci. 29, S909 (1998)
115. V. Jokanovic, Dj. Janackovic, P. Spasic and D. Uskokovic, *Modeling of nanostructural design of ultrafine mullite powder particles obtained by ultrasonic spray pyrolysis*, Nanostructured Mater. 12(4), 349 (1999)
116. A. Ortiz, J. C. Alonso, V. Pankov and D. Albarran, *Violet-blue photoluminescence in aluminium oxide films prepared by ultrasonic spray pyrolysis*, J. Luminescence 81(1), 45 (1999)
117. Y. Matsuzaki, M. Hishinuma and I. Yasuda, *Growth of yttria stabilized zirconia thin films by metallo-organic, ultrasonic spray pyrolysis*, Thin Solid Films 340(1-2), 72 (1999)
118. Y. C. Kang and S. B. Park, *Preparation of zinc oxide-dispersed silver particles by spray pyrolysis of colloidal solution*, Mater. Lett 40(3), 129 (1999)
119. Y. C. Kang, I. W. Lenggoro, S. B. Park and K. Okuyama, *YAG:Ce phosphor particles prepared by ultrasonic spray pyrolysis*, Mater. Res. Bulletin 35(5), 789 (2000)
120. P. R. Patil and P. S. Patil, *Transient photoconductivity measurements of ultrasonic spray pyrolyzed tungsten oxide thin films*, Mater. Res. Bulletin 35(6), 865 (2000)
121. M. C. Baykul and A. Balcioglu, *AFM and SEM studies of CdS thin films produced by an ultrasonic spray pyrolysis method*, Microelectronic Eng. 51-52, 703 (2000)
122. S. Wang, Z. Qiao, W. Wang and Y. Qian, *XPS studies of nanometer CeO₂ thin films deposited by pulse ultrasonic spray pyrolysis*, J. Alloys & Compounds 305(1-2), 121 (2000)
123. L. Manic, O. Miloevic, B. Marinkovic, M. F. de Silva Lopes and F. Rizzo, *The influence of urea on the formation process of BiPbSrCaCuO superconducting ceramics synthesized by spray pyrolysis method*, Mater. Sci. & Eng. B 76(2), 127 (2000)
124. P. S. Patil, P. R. Patil and E. A. Ennaoui, *Characterization of ultrasonic spray pyrolyzed tungsten oxide thin films*, Thin Solid Films 370(1-2), 38 (2000)
125. S. Wang, W. Wang and Y. Qian, *Preparation of La₂O₃ thin films by pulse ultrasonic spray pyrolysis method*, Thin Solid Films 372(1-2), 50 (2000)
126. S. Wang, W. Wang and Y. Qian, *Preparation and characterization of Eu₂O₃ nanometer thin films by pulse ultrasonic spray pyrolysis method*, Mater. Res. Bulletin 35(12), 2057 (2000)
127. Y. C. Chang, D. H. Huang and K. Y. Cheng, *Morphological control of product powders in spray pyrolysis via chemical engineering approach*, J. Aerosol Sci. 31, 925 (2000)
128. Y. C. Chang, H. W. Chen, S. S. Yu and K. Y. Cheng, *Optimize the design and operation of ultrasonic nebulizer to maximize production rate in spray pyrolysis*, J. Aerosol Sci. 31, 923 (2000)
129. S. Wang, W. Wang, W. Wang, Z. Jiao, J. Liu and Y. Qian, *Characterization and gas-sensing properties of nanocrystalline iron(III) oxide films prepared by ultrasonic spray pyrolysis on silicon*, Sensors & Actuators B: Chemical 69(1-2), 22 (2000)
130. Z. V. Marinkovic, L. Mancic, R. Maric and O. Milosevic, *Preparation of nanostructured Zn-Cr-O spinel powders by ultrasonic spray pyrolysis*, J. Eur. Ceram Soc. 21(10-11), 2051 (2001)
131. A. K. Ivanov-Schitz, A. V. Nistuk and N. G. Chaban, *Li₃Fe₂(PO₄)₃ solid electrolyte prepared by ultrasonic spray pyrolysis*, Solid State Ionics 139(1-2), 153 (2001)

132. P. Veluchamy, M. Tsuji, T. Nishio, T. Aramoto, H. Higuchi, S. Kumazawa, S. Shibutani, J. Nakajima, T. Arita, H. Ohyama, *A pyrosol process to deposit large-area SnO₂:F thin films and its use as a transparent conducting substrate for CdTe solar cells*, Solar Energy Mater. & Solar Cells 67(1-4), 179 (2001)
133. A. Ferreri, J. A. G. Nelstrop, A. D. Caplin and J. L. MacManus-Driscoll, *Microstructure and superconducting properties of ultrasonically spray pyrolysed YBa₂Cu₃O_{7-x} films*, Physica C: Superconductivity 351(1), 58 (2001)
134. A. K. Ivanov-Schitz, A. V. Nistuk, L. N. Demianets and N. G. Chaban, *Li₃Sc_{2-x}Fe_x(PO₄)₃ thin films and powders prepared by ultrasonic spray pyrolysis*, Solid State Ionics 144(1-2), 133 (2001)
135. A. Huanosta, J. C. Alonso and A. Ortiz, *Spectroscopic impedance studies of Al₂O₃ films deposited by spray pyrolysis*, Thin Solid Films 401(1-2), 284 (2001)
136. K. H. Kim, J. K. Park, C. H. Kim, H. D. Park, H. Chang and S. Y. Choi, *Synthesis of SrTiO₃:Pr,Al by ultrasonic spray pyrolysis*, Ceram. Int. 28(1), 29 (2002)
137. I. Taniguchi, C. K. Lim, D. Song and M. Wakihara, *Particle morphology and electrochemical performances of spinel LiMn₂O₄ powders synthesized using ultrasonic spray pyrolysis method*, Solid State Ionics 146(3-4), 239 (2002)
138. Sheng-Yue Wang and You-Wei Du, *Preparation and characterization of highly oriented NiO(200) films by a pulse ultrasonic spray pyrolysis method*, J. Cryst. Growth 236(4), 627 (2002)
139. S.-Y. Wang, W. Wang, W.-Z. Wang and Y.-W. Du, Mater. Sci. & Eng. B 90(1-2), 133 (2002)
140. T. Y. Ma and D. K. Shim, *Effects of rapid thermal annealing on the morphology and electrical properties of ZnO/In films*, Thin Solid Films 410(1-2), 8 (2002)
141. M. Dj. Blesic, Z. V. Saponjis, J. M. Nedeljkovic and D. P. Uskokovic, *TiO₂ films prepared by ultrasonic spray pyrolysis of nanosize precursor*, Mater. Lett 54 (4), 298 (2002)
142. I. Taniguchi, D. Song and M. Wakihara, *Electrochemical properties of LiM₁/6Mn₁₁/6O₄ (M = Mn, Co, Al and Ni) as cathode materials for Li-ion batteries prepared by ultrasonic spray pyrolysis method*, J. Power Sources 109(2), 333 (2002)
143. S. Phok, Ph. Galez, J. L. Jorda, Z. Supardi, D. De Barros, P. Odier, A. Sin and F. Weiss, *Tl- and (Hg,Re)-1223 oxide films by spray pyrolysis for practical applications*, Physica C: Superconductivity 372-376 (Part 2), 876 (2002)
144. A. Ferreri, A. Berenov, Y. Bugoslavsky, G. Perkins and J. L. MacManus-Driscoll, *Li-ion battery cathode materials by ultrasonic spray pyrolysis method*, Physica C: Superconductivity 372-376 (Part 2), 873 (2002)
145. Y. C. Kang, H. S. Roh, H. D. Park and S. B. Park, *Optimization of VUV characteristics and morphology of BaMgAl₁₀O₁₇:Eu²⁺ phosphor particles in spray pyrolysis*, Ceram Int. 29(1), 41 (2003)
146. L. Castañeda, J. C. Alonso, A. Ortiz, E. Andrade, J. M. Saniger and J. G. Bañuelos, *Spray pyrolysis deposition and characterization of titanium oxide thin films*, Mater. Chem. & Phys. 77(3), 938 (2003)
147. K. T. Wojciechowski and J. Ob Kowski, *Preparation and characterisation of nanostructured spherical powders for thermoelectric applications*, Solid State Ionics 157(1-4), 341 (2003)
148. Y. T. Tan, N. Li, U. Gösele, *Is there a thermodynamic limit to the size of the nanowire?*, Appl. Phys. Lett. 83, 1199 (2003)
149. S.-Y. Wang and Z.H. Lu, *Preparation of Y₂O₃ thin films deposited by pulse ultrasonic spray pyrolysis*, Mater. Chem. & Phys. 78(2), 542 (2003)
150. M. Girtan, H. Cachet and G. I. Rusu, *On the physical properties of indium oxide thin films deposited by pyrosol in comparison with films deposited by pneumatic spray pyrolysis*, Thin Solid Films 427(1-2), 406 (2003)
151. M. Liu, M. L. Zhou, L. H. Zhai, D. M. Liu, X. Gao and W. Liu, *A newly designed ultrasonic spray pyrolysis device to fabricate YBCO tapes*, Physica C: Superconductivity 386, 366 (2003)
152. M. García-Hipólito, C. D. Hernández-Pérez, O. Alvarez-Fregoso, E. Martínez, J. Guzmán-Mendoza and C. Falcony, *Characterization of europium doped zinc aluminate luminescent coatings synthesized by ultrasonic spray pyrolysis process*, Opt. Mater. 22(4), 345 (2003)
153. F. Atay, S. Kose, V. Bilgin and I. Akyuz, *CdS:Ni films obtained by ultrasonic spray pyrolysis: effect of the Ni concentration*, Mater Lett 57(22-23), 3461 (2003)
154. F. Atay, V. Bilgin, I. Akyuz and S. Kose, *The effect of In doping on some physical properties of CdS films*, Mater Sci. Semicond Processing 6(4), 197 (2003)

155. M. Girtan and G. Folcher, *Structural and optical properties of indium oxide thin films prepared by an ultrasonic spray CVD process*, Surf. & Coatings Technol. 172(2-3), 242 (2003)
156. Yong-Ho Choa, Jae-Kyo Yang, Won-Jae Yang and Keun-Ho Auh, *Synthesis and characterization of isolated iron oxide nanoparticle dispersed in MgO matrix*, J. Magnetism & Magnetic Mater. 266(1-2), 20 (2003)
157. Y. -H. Choa, J. -K. Yang, B. -H. Kim, Y. -K. Jeong, J. -S Lee, T. Nakayama, T. Sekino and K. Niihara, *Preparation and characterization of metal/ceramic nanoporous nanocomposite powders*, J. Magnetism & Magnetic Mater. 266(1-2), 12 (2003)
158. S.-Y. Wang, W. Wang and Z.-H. Lu, *Asynchronous-pulse ultrasonic spray pyrolysis deposition of Cu_xS ($x=1, 2$) thin films*, Mater. Sci. & Eng. B 103(2), 184 (2003)
159. Z. V. Marinkovic, L. Mancic and O. Milosevic, *The nature of structural changes in nanocrystalline ZnO powders under linear heating conditions*, J. Eur. Ceram. Soc. 24(6), 1929 (2004)
160. J-H Lee and B-O Park, *Characteristics of Al-doped ZnO thin films obtained by ultrasonic spray pyrolysis: effects of Al doping and an annealing treatment*, Mater. Sci. & Eng. B 106(3), 242 (2004)
161. S. H. Park, C. S. Yoon, S. G. Kang, H. -S. Kim, S. -I. Moon and Y. -K. Sun, *Synthesis and structural characterization of layered $Li[Ni_{1/3}Co_{1/3}Mn_{1/3}]O_2$ cathode materials by ultrasonic spray pyrolysis method*, Electrochimica Acta 49(4), 557 (2004)
162. J. M. Bian, X. M. Li, T. L. Chen, X. D. Gao and W. D. Yu, *Preparation of high quality MgO thin films by ultrasonic spray pyrolysis*, Appl. Surf. Sci. 228(1-4), 297 (2004)
163. N. Khare, D. P. Singh, H. K. Singh, A. K. Gupta, P. K. Siwach and O. N. Srivastava, *Preparation and study of silver added $La_{0.67}Ca_{0.33}MnO_3$ film*, J. Physics & Chem. Solids 65(5), 867 (2004)
164. K. Matsuda and I. Taniguchi, *Relationship between the electrochemical and particle properties of $LiMn_2O_4$ prepared by ultrasonic spray pyrolysis*, J. Power Sources 132(1-2), 156 (2004)
165. J-H Lee and B-O Park, *Transparent conducting In_2O_3 thin films prepared by ultrasonic spray pyrolysis*, Surf. & Coatings Technol. 184(1), 102 (2004)
166. M. Girtan, *The influence of post-annealing treatment on the electrical properties of In_2O_3 thin films prepared by an ultrasonic spray CVD process*, Surf. & Coatings Technol. 184(2-3), 219 (2004)
167. Z. V. Marinkovic, L. Mancic, J. -F. Cribier, S. Ohara, T. Fukui and O. Milosevic, *Nature of structural changes in LSM-YSZ nanocomposite material during thermal treatments*, Mater. Sci. & Eng. A 375-377, 615 (2004)
168. J. Bian, X. Li, L. Chen and Q. Yao, *Properties of undoped n-type ZnO film and N-In codoped p-type ZnO film deposited by ultrasonic spray pyrolysis*, Chem. Phys. Lett. 393(1-3), 256 (2004)
169. S. W. Oh, S. H. Park, C. -W. Park and Y. -K. Sun, *Structural and electrochemical properties of layered $Li[Ni_{0.5}Mn_{0.5}]_{1-x}Co_xO_2$ positive materials synthesized by ultrasonic spray pyrolysis method*, Solid State Ionics 171(3-4), 167 (2004)
170. Y. S. Chung, S. B. Park and D.-W. Kang, *Magnetically separable titania-coated nickel ferrite photocatalyst*, Mater. Chem. & Phys. 86(2-3), 375 (2004)
171. C. Zhang, X. Li, J. Bian, W. Yu and X. Gao, *Structural and electrical properties of nitrogen and aluminum codoped p-type ZnO films*, Solid State Commun. 132(2), 75 (2004)
172. V. Jokanovic, A. M. Spasi and D. Uskokovi, *Designing of nanostructured hollow TiO_2 spheres obtained by ultrasonic spray pyrolysis*, J. Colloid and Interface Sci. 278(2), 342 (2004)
173. V. Bilgin, S. Kose, F. Atay and I. Akyuz, *The effect of Zn concentration on some physical properties of tin oxide films obtained by ultrasonic spray pyrolysis*, Mater. Lett 58(29), 3686 (2004)
174. S. -H. Park and Y. K. Sun, *Synthesis and electrochemical properties of 5 V spinel $LiNi_{0.5}Mn_{1.5}O_4$ cathode materials prepared by ultrasonic spray pyrolysis method*, Electrochimica Acta 50(2-3), 434 (2004)
175. V. Jokanović, B. Jokanović, J. Nedeljković and O. Milošević, *Modeling of nanostructured TiO_2 spheres obtained by ultrasonic spray pyrolysis*, Colloids and Surfaces A: Physicochemical and Engineering Aspects 249(1-3), 111 (2004)
176. S.-H. Park, S. W. Oh, S.T. Myung, Y.C. Kang and Y.K. Sun, *Effects of synthesis condition on $LiNi_{1/2}Mn_{3/2}O_4$ cathode material for prepared by ultrasonic spray pyrolysis method*, Solid State Ionics 176 (5-6), 481 (2005)
177. K. D. Kim, K. Y. Choi and J. W. Yang, *Formation of spherical hollow silica particles from sodium silicate solution by ultrasonic spray pyrolysis method*, Colloids & Surf. A: Physicochemical and Engineering Aspects 254(1-3), 193 (2005)

178. C. H. Lee, Y. C. Kang, K. Y. Jung and J. G. Choi, *Phosphor layer formed from the Zn₂SiO₄:Mn phosphor particles with spherical shape and fine size*, Mater. Sci. & Eng. B 117(2), 210 (2005)
179. Z. Bakenov and I. Taniguchi, *Electrochemical performance of nanostructured LiM_xMn_{2-x}O₄ (M = Co and Al) powders at high charge–discharge operations*, Solid State Ionics 176(11-12), 1027 (2005)
180. M. Girtan, *Investigations on the optical constants of indium oxide thin films prepared by ultrasonic spray pyrolysis*, Mater. Sci. & Eng. B 118(1-3), 175 (2005)
181. J. L. Zhao, X. M. Li, J. M. Bian, W. D. Yu and C. Y. Zhang, *Growth of nitrogen-doped p-type ZnO films by spray pyrolysis and their electrical and optical properties*, J. Cryst. Growth 280(3-4), 495 (2005)
182. I. Taniguchi, *Powder properties of partially substituted LiM_xMn_{2-x}O₄ (M = Al, Cr, Fe and Co) synthesized by ultrasonic spray pyrolysis*, Mater. Chem. & Phys. 92(1), 172 (2005)
183. C. Zhang, X. Li, J. Bian, W. Yu and X. Gao, *Synthesis and structural characterization of layered Li[Ni^{1/3+x}Co^{1/3}Mn^{1/3-2x}Mox]O₂ cathode materials by ultrasonic spray pyrolysis*, Surf. & Coatings Technol. 198(1-3), 253 (2005)
184. S. H. Park, S. W. Oh and Y. K. Sun, *Molybdenum disulfide made by ultrasonic spray pyrolysis*, J. Power Sources 146(1-2), 622 (2005)
185. W. Wang, S. Y. Wang and M. Liu, *Growth of rod-like crystal BiSI films by ultrasonic spray pyrolysis*, Mater. Res. Bulletin 40(10), 1781 (2005)
186. V. Bilgin, S. Kose, F. Atay and I. Akyuz, *The effect of substrate temperature on the structural and some physical properties of ultrasonically sprayed CdS films*, Mater. Chem. & Phys. 94(1), 103 (2005)
187. I. Taniguchi and Z. Bakenov, *Spray pyrolysis synthesis of nanostructured LiFexMn_{2-x}O₄ cathode materials for lithium-ion batteries*, Powder Technol. 159(2), 55 (2005)
188. X. Zhang, X. M. Li, T. L. Chen, J. M. Bian and C. Y. Zhang, *Nanostructured phosphorous tungsten bronzes from ultrasonic spray pyrolysis*, Thin Solid Films 492(1-2), 248 (2005)
189. V. Jakanović, U.B. Mioč and Z.P. Nedić, Solid State Ionics 176(39-40), 2955 (2005)
190. K. Y. Choi, K. D. Kim and J. W. Yang, *Optimization of the synthesis conditions of LiCoO₂ for lithium secondary battery by ultrasonic spray pyrolysis process*, J. Mater. Processing Technol. 171(1), 118 (2006)
191. C.R. Michel, E.R. López and H.R. Zea, *Synthesis of GdCo_{1-x}CuxO_{3-δ} (x = 0, 0.15, 0.30) perovskites by ultrasonic spray pyrolysis*, Mater. Res. Bulletin 41(1), 209 (2006)
192. W. Wang, S. Y. Wang and M. Liu, *Preparation of γ-Gd₂S₃ films by ultrasonic spray pyrolysis*, Mater. Chem. & Phys. 94(2-3), 182 (2006)
193. J-H Lee, S-Y Lee and B-O Park, *Fabrication and characteristics of transparent conducting In₂O₃-ZnO thin films by ultrasonic spray pyrolysis*, Mater. Sci. & Eng. B 127(2-3), 267 (2006)
194. H. S. Kang, Y. C. Kang, H. Y. Koo, S. H. Ju, D. Y. Kim, S. K. Hong, J. R. Sohn, K. Y. Jung and S. B. Park, *Nano-sized ceria particles prepared by spray pyrolysis using polymeric precursor solution*, Mater. Sci. & Eng. B 127(2-3), 99 (2006)
195. S. M. Abrarov, Sh. U. Yuldashev, T.W. Kim, Y.H. Kwon and T.W. Kang, *Deep level emission of ZnO nanoparticles deposited inside UV opal*, Optics Commun. 259(1), 378 (2006)
196. S. Suda, S. Takahashi, M. Kawano, H. Yoshida and T. Inagaki, *Effects of atomization conditions on morphology and SOFC anode performance of spray pyrolyzed NiO-Sm_{0.2}Ce_{0.8}O_{1.9} composite particles*, Solid State Ionics 177(13-14), 1219 (2006)
197. M. Wolborski, M. Bakowski, A. Ortiz, V. Pore, A. Schöner, M. Ritala, M. Leskelä and A. Hallén, *Characterisation of the Al₂O₃ films deposited by ultrasonic spray pyrolysis and atomic layer deposition methods for passivation of 4H-SiC devices*, Microelectronics & Reliability 46(95-6), 743 (2006)
198. S. H. Park, S. T. Myung, S. W. Oh, C. S. Yoon and Y. K. Sun, *Ultrasonic spray pyrolysis of nano crystalline spinel LiMn₂O₄ showing good cycling performance in the 3 V range*, Electrochimica Acta 51(19), 4089 (2006)
199. S-W Oh, S-H Park, J-H Kim, Y C Bae and Y-K Sun, *Improvement of electrochemical properties of LiNi_{0.5}Mn_{1.5}O₄ spinel material by fluorine substitution*, J. Power Sources 157(1), 464 (2006)
200. S. Y. Lee and B. O. Park, *Structural, electrical and optical characteristics of SnO₂:Sb thin films by ultrasonic spray pyrolysis*, Thin Solid Films 510(1-2), 154 (2006)
201. M-R Yang, T-H Teng and S-H Wu, *LiFePO₄/carbon cathode materials prepared by ultrasonic spray pyrolysis*, J. Power Sources 159(1), 307 (2006)
202. S. W. Oh, S. H. Park, K. Amine and Y. K. Sun, *Synthesis and characterization of spherical morphology [Ni_{0.4}Co_{0.2}Mn_{0.4}]₃O₄ materials for lithium secondary batteries*, J. Power Sources 160(1), 558 (2006)

203. H. J. Kim, J. Joo, S. G. Park, S. K. Hong, S. W. Lee, S. W. Lim, G. W. Hong and H. G. Lee, *Effects of deposition conditions on the phase formation of YBCO films prepared by spray pyrolysis method*, Physica C: Superconductivity 445-448, 598 (2006)
204. A. Kumar, P. Singh and D. Kaur, *Low cost synthesis of high-Tc superconducting films on metallic substrates via ultrasonic spray pyrolysis* Cryogenics 46(10), 749 (2006)
205. J. Bian, W. Liu, H. Liang, L. Hu, J. Sun, Y. Luo and G. Du, *Room temperature electroluminescence from the n-ZnMgO/ZnO/p-ZnMgO heterojunction device grown by ultrasonic spray pyrolysis*, Chem. Phys. Lett. 430(1-3), 183 (2006)
206. D. Zaouk, Y. Zaatar, R. Asmar and J. Jabbour, *Piezoelectric zinc oxide by electrostatic spray pyrolysis*, Microelectronics J. 37 (11), 1276 (2006)
207. J. L. Zhao, X. M. Li, J. M. Bian, W. D. Yu and C. Y. Zhang, *Comparison of structural and photoluminescence properties of ZnO thin films grown by pulsed laser deposition and ultrasonic spray pyrolysis*, Thin Solid Films 515(4), 1763 (2006)
208. I. Lj. Validžić, V. Jokanović, D.P. Uskoković and J.M. Nedeljković, *Formation of silver iodide particles from thermodynamically stable clusters using ultrasonic spray pyrolysis*, J. Eur. Ceram. Soc. 27, 927 (2007)
209. M. M. Bućko and J. Obłąkowski, *Preparation of BaZrO₃ nanopowders by spray pyrolysis method*, J. Eur. Ceram. Soc. 27, 3625 (2007)
210. G. Ye and T. Troczynski, *Hydroxyapatite coatings by pulsed ultrasonic spray pyrolysis*, Ceram. Int. 34, 511 (2007)
211. Zhang Xiaodan, Fan Hongbing, Zhao Ying, Sun Jian, Wei Changchun and Zhang Cunshan, *Fabrication of high hole-carrier density p-type ZnO thin films by N-Al co-doping*, Appl. Surf. Sci. 253(8), 3825 (2007)
212. U. Alver, T. Kılınc, E. Bacaksız, T. Küçükömeroğlu, S. Nezir, İ.H. Mutlu and F. Aslan, *Synthesis and characterization of spray pyrolysis Zinc Oxide microrods*, Thin Solid Films 515, 3448 (2007)
213. L. Castañeda and M. Terrones, *Synthesis and structural characterization of novel flower-like titanium dioxide nanostructures*, Matter 390, 143 (2007)
214. U. Alver, T. Kılınc, E. Bacaksız and S. Nezir, *Structure and optical properties of Zn_{1-x}FexO thin films prepared by ultrasonic spray pyrolysis*, Mater. Sci. & Eng. B 138, 74 (2007)
215. H. Liu, C. Song, Y. Tang, J. Zhang and J. Zhang, *High-surface-area CoTMPP/C synthesized by ultrasonic spray pyrolysis for PEM fuel cell electrocatalysts*, Electrochimica Acta 52, 4532 (2007)
216. D. Jugović, N. Cvjetičanin, V. Kusigerski, M. Mitrić, M. Miljković, D. Makovec and D. Uskoković, *Structural and magnetic characterization of LiMn_{1.825}Cr_{0.175}O₄ spinel obtained by ultrasonic spray pyrolysis*, Mater. Res. Bulletin 42, 515 (2007)
217. G.-H. An, H.-J. Wang, B.-H. Kim, Y.-G. Jeong, Y.-H. Choa, *Fabrication and characterization of a hydroxyapatite nanopowder by ultrasonic spray pyrolysis with salt-assisted decomposition*, Mater. Sci. & Eng. A 449-451, 821 (2007)
218. K.-J. Lee, J.-W. Park, J.-K. Yang, K.-S. Lee and Y.-H. Choa, *Synthesis and optimization of nano-porous La_{0.6}Sr_{0.4}CoO_{3-δ} on the oxygen separation membrane*, Mater. Sci. & Eng. A 449-451(25), 774 (2007)
219. J.-K. Yang, J.-H. Yu, J. Kim and Y.-H. Choa, *Synthesis and optimization of nano-porous La_{0.6}Sr_{0.4}CoO_{3-δ} on the oxygen separation membrane*, Mater. Sci. & Eng. A 449-451, 477 (2007)
220. A. Senol Aybek, Nihal Baysal, Muhsin Zor, Evren Turan and Metin Kul, *Optical properties of Cd_xZn_(1-x)O films deposited by ultrasonic spray pyrolysis method*, Thin Solid Films 515, 8590 (2007)
221. E. Turan, M. Zor, A. Senol Aybek and M. Kul, *Electrical properties of ZnO/Au/ZnS/Au films deposited by ultrasonic spray pyrolysis*, Thin Solid Films 515, 8017 (2007)
222. M. Kul, M. Zor, A. Senol Aybek, S. Irmak and E. Turan, *Some structural properties of CdO:F films produced by ultrasonic spray pyrolysis method*, Thin Solid Films 515, 8752 (2007)
223. X. Zhang, H. Fan, J. Sun and Y. Zhao, *Structural and electrical properties of p-type ZnO films prepared by Ultrasonic Spray Pyrolysis*, Thin Solid Films, (2007)
224. T. H. Teng, M. R. Yang, S. H. Wu and Y. P. Chiang, *Electrochemical properties of LiFe_{0.9}Mg_{0.1}PO₄/carbon cathode materials prepared by ultrasonic spray pyrolysis*, Solid State Commun. 142, 389 (2007)
225. J. Bian, W. Liu, J. Sun and H. Liang, *Synthesis and defect-related emission of ZnO based light emitting device*, J. Mater. Processing Technol 184,451 (2007)

226. M. Liu, H.L. Suo, Y. Zhao, Y.X. Zhang, D. He, L. Ma and M.L. Zhou, *Improvement of YBCO film properties by two-step deposition using pyrolysis method*, Physica C: Superconductivity 460-462, 1424 (2007)
227. S. W. Oh, H. J. Bang, Y. C. Bae and Y.-K. Sun, *Effect of calcinations temperature on morphology, crystallinity and electrochemical properties of nano-crystalline metal oxides*, J. Power Sources, 173, 502 (2007)
228. I. Akyuz, S. Kose, F. Atay and V. Bilgin, *Some physical properties of chemically sprayed Zn_{1-x}Cd_xS semiconductor films*, Mater. Sci. Semicond. Processing 10,103 (2007)
229. L. Castañeda, *Effect of palladium coatings on oxygen sensors of titanium dioxide thin films*, Mater. Sci. & Eng. B 139(2-3), 149 (2007)
230. K. Ernits, D. Brémaud, S. Buecheler, C.J. Hibberd, M. Kaelin, G. Khrypunov, U. Müller, E. Mellikov and A.N. Tiwari, *Characterization of ultrasonically sprayed In_xS_y buffer layers for Cu(In,Ga)Se₂ solar cells*, Thin Solid Films 515(15), 6051 (2007)
231. M. Kul, M. Zor, A. S. Aybek, S. Irmak and E. Turan, *Electrical and optical properties of fluorine-doped CdO films deposited by ultrasonic spray pyrolysis*, Solar Energy Mater. & Solar Cells 91(10), 882 (2007)
232. J. Wienke and A.S. Booij, *ZnO:In deposition by spray pyrolysis – Influence of the growth conditions on the electrical and optical properties*, Thin Solid Films, (2007)
233. U. Alver, T. Kılınç, E. Bacaksız and S. Nezir, *Temperature dependence of ZnO nanorods produced by ultrasonic spray pyrolysis*, Mater. Chem.& Phys. 106, 227 (2007)
234. Y. Luo, J. Bian, J. Sun, H. Liang and W. Liu, *Deposition and tunable photoluminescence of Zn_{1-x}(Mg,Cd)_xO*, J. Mater. Processing Technol. 189 (1-3), 473(2007)
235. V. Jokanović, M.D. Dramićanin, Ž. Andrić, T. Dramićanin, M. Plavšić, S. Pašalić and M. Miljković, *Nanostructure designed powders of optical active materials Me_xSiO_y obtained by ultrasonic spray pyrolysis*, Optical Mater. 30, 1168 (2007)
236. I. Lj.Validžić, V. Jokanović, D. P. Uskoković and J. M. Nedeljković, *Influence of solvent on the structural and morphological properties of AgI particles prepared using ultrasonic spray pyrolysis*, Mater. Chem. & Phys. 107, 28 (2007)
237. P. Singh, A. Kumar, D. Kumar and D. Kaur, *Growth and characterization of ZnO nanocrystalline thin films and nanopowders via a low-cost ultrasonic spray pyrolysis*, J. Cryst. Growth 306(2), 303 (2007)
238. X.D. Zhang, H.B. Fan, J. Sun and Y. Zhao, *Effect of substrates on the properties of p-type ZnO films* Physica E: Low-dimensional Systems and Nanostructures 39(2), 267 (2007)
239. S. H. Park, S.-W. Oh, S.H. Kang, I. Belharouak, K. Amine and Y.-K. Sun, *Comparative study of different crystallographic structure of LiNi_{0.5}Mn_{1.5}O_{4-δ} cathodes with wide operation voltage (2.0-5.0V)*, Electrochimica Acta 52(25), 7226 (2007)
240. J. C. Chen, C. L. Chang, C. S Hsu and B. H. Hwang, *Deposition of Ni-CGO composite anodes by electrostatic assisted ultrasonic spray pyrolysis method*, Mater Res. Bulletin 42(9), 1674 (2007)
241. M. M. Bučko, J. Obłakowski, J. Eur. Ceram. Soc. 27, 3625 (2007)
242. M. T. Htay, Y. Hashimoto, K. Ito, *ZnO nanostructures by ultrasonic spray pyrolysis*, Jpn. J. Appl. Phys. 46, 440 (2007)
243. B. W. Mwakikunga, Elias Sideras-Haddad and Malik Maaza, *First synthesis of vanadium dioxide by ultrasonic nebula spray pyrolysis*, Optical Mater. 29(5), 481 (2007)
244. B. W. Mwakikunga, A. Forbes, E. Sideras-Haddad, R M Erasmus, G. Katumba, B. Masina, *Synthesis of tungsten oxide nanostructures by laser pyrolysis* Int. J. Nanoparticles 1, 3 (2008) doi:10.1504/IJNP.2008.020895
245. B. W. Mwakikunga, A. Forbes, E. Sideras-Haddad, C. Arendse, *Raman spectroscopy of WO₃ nanowires and thermochromism study of VO₂ nanobelts produced by laser pyrolysis*, Phys. Stat. Solidi (a) 205, 150 (2008)
246. B. W. Mwakikunga, E. Sideras-Haddad, M. Witcomb, C. Arendse, A. Forbes, *WO₃ nano-spheres into W₁₈O₄₉ one-dimensional nanostructures by thermal annealing*, J. Nanosci. & Nanotechnol 8, 1 (2008)
247. B. W. Mwakikunga, A. Forbes, E. Sideras-Haddad, C. Arendse, *Optimization, yield studies and morphology of WO₃ nanowires synthesized by laser pyrolysis in C₂H₂ and O₂ ambients – validation of a new growth mechanism*, Nanoscale Res Lett 3, 272 (2008)

248. A. Djelloul, K. Bouzid, F. Guerrab, *Role of substrate temperature on the structural and morphological properties of ZnO thin films deposited by ultrasonic spray pyrolysis*, Turkish J. Physics 32 (1), 49-58 (2008)
249. J.-C. Chen, B.-H. Hwang, *Microstructure and properties of the Ni-CGO composite anodes prepared by the electrostatic-assisted ultrasonic spray pyrolysis method*, J. Am Ceram Soc. 91 (1), 97-102 (2008)
250. Z. Bakenov, M. Wakihara, I. Taniguchi, *Battery performance of nanostructured lithium manganese oxide synthesized by ultrasonic spray pyrolysis at elevated temperature*, J Solid State Electrochem 12 (1), 57-62 (2008)
251. L. Lj. Validžić, V. Jokanović, D. P. Uskoković, J. M. Nedeljković, *Influence of solvent on the structural and morphological properties of AgI particles prepared using ultrasonic spray pyrolysis*, Mater. Chem. & Phys. 107 (1), 28-32 (2008)
252. M. Aizawa, T. Ohno, N. Kanomata, K. Yano, M. Emoto, *Anti-tumorigenesis of hollow calcium-phosphate microsphere loaded with anti-angiogenic agent*, Key Eng. Mater. 361-363 II, 1215-1218 (2008)
253. S. U. Yuldashev, R. A. Nusretov, I. V. Khvan, V. Sh. Yalishev, T. W. Kang, *White light emission from ZnO/Zn_{0.9}Mg_{0.1}O heterostructures grown on Si substrates*, Japanese J. Appl. Phys. 47, 133-135 (2008)
254. M.T. Htay, M. Itoh, Y. Hashimoto, K. Ito, *Photoluminescence properties and morphologies of submicron-sized ZnO crystals prepared by ultrasonic spray pyrolysis* Japanese J. Appl. Phys. 47, 541-545 (2008)
255. C.-Y. Chen, T.-K. Tseng, C.-Y. Tsay, C.-K. Lin, *Formation of irregular nanocrystalline CeO₂ particles from acetate-based precursor via spray pyrolysis*, J. Mater. Eng. & Performance 17, 20-24 (2008)
256. Z. Jiao, X. Wan, B. Zhao, H. Guo, T. Liu, M. Wu, *Effects of electron beam irradiation on tin dioxide gas sensors*, Bull Mater Sci 31 (1), 83-86 (2008)
257. F. Atay, V. Bilgin, I. Akyuz, E. Ketenci, S. Kose, K. Ertuek, *The investigation of Cu doped CdS films produced by ultrasonic spray pyrolysis technique*, J Optoelectron & Adv Mater 10, 331-334 (2008)
258. A.S. Aybek, M. Kul, E. Turan, M. Zor, E. Gedik, *Thermally stimulated currents in CdS film produced by ultrasonic spray pyrolysis method*, J Phys Condensed Matter 20 (5), 055216 (2008)
259. V. Kusigerski, D. Marković, V. Spasojević, N. Cvjetičanin, M. Mitrić, D. Jugović, D. Uskoković, *Ground-state magnetism of chromium-substituted LiMn₂O₄ spinel*, J Magn & Magn Mater 320, 943-949 (2008)
260. H. Sun, Q. Zhang, J. Zhang, T. Deng, J. Wu, *Electroluminescence from ZnO nanowires with a p-ZnO film/n-ZnO nanowire homojunction*, Appl Phys B: Lasers & Optics 90 (3-4), 543-546 (2008)
261. S.H. Kim, K.-B. Shim, J.-P. Ahn, C.-S. Kim, *Structural stability during charge-discharge cycles in Zr-doped LiCoO₂ powders*, J Korean Ceram Soc 45, 167-171 (2008)
262. C.Y. Chen, T.K. Tseng, S.C. Tsai, C.K. Lin, H.M. Lin, *Effect of precursor characteristics on zirconia and ceria particle morphology in spray pyrolysis*, Ceram Int 34, 409-416 (2008)
263. Z. Bakenov, M. Nakayama, M. Wakihara, I. Taniguchi, *Lithium AlPO₄ composite polymer battery with nanostructured LiMn₂O₄ cathode*, J Solid State Electrochem 12, 295-302 (2008)
264. V. Jokanović, M.D. Dramićanin, Z. Andrić, T. Dramićanin, M. Plavšić, S. Pašalić, M. Miljković, *Nanostructure designed powders of optical active materials MexSiOy obtained by ultrasonic spray pyrolysis* Opt Mater 30, 1168-1172 (2008)
265. L. Li, C.-K. Tsung, Z. Yang, G.D. Stucky, L. Sun, J. Wang, C. Yan, *Rare-earth-doped nanocrystalline titania microspheres emitting luminescence via energy transfer*, Adv Mater 20, 903-908 (2008)
266. W.-N. Wang, A. Purwanto, I.W. Lenggoro, K. Okuyama, H. Chang, H.D. Jang, *Investigation on the correlations between droplet and particle size distribution in ultrasonic spray pyrolysis*, Ind & Eng Chem Res 47, 1650-1659 (2008)
267. P. Yao, Q. Jin, X. Chen, Y. Xing, D. Wang, *Ti/SnO₂-Sb electrodes for pollutant degradation prepared using ultrasonic spray pyrolysis*, Electrochem & Solid-State Lett 11, J37-J39 (2008)
268. G. Ye, T. Troczynski, *Hydroxyapatite coatings by pulsed ultrasonic spray pyrolysis*, Ceram Int 34, 511-516 (2008)
269. B.-C. Jiao, X.-D. Zhang, Y. Zhao, C.-C. Wei, J. Sun, J. Zhao, R.-X. Yang, *Study of electrical and structural properties of p-type ZnO films along to the growth direction*, J Optoelectron Laser 19, 482-485 (2008)
270. M.F. García-Sánchez, J. Peña, A. Ortiz, G. Santana, J. Fandiño, M. Bizarro, F. Cruz-Gandarilla, J.C. Alonso, *Nanostructured YSZ thin films for solid oxide fuel cells deposited by ultrasonic spray pyrolysis*, Solid State Ionics 179, 243-249 (2008)

271. M. H. Choi, T. Y. Ma, *Erbium concentration effects on the structural and photoluminescence properties of ZnO:Er films* Mater Lett 62, 1835-1838 (2008)
272. G. Alarcón-Flores, M. Aguilar-Frutis, M. García-Hipolito, J. Guzmán-Mendoza, M. A. Canseco, C. Falcony, *Optical and structural characteristics of Y₂O₃ thin films synthesized from yttrium acetylacetonate*, J Mater Sci 43, 3582-3588 (2008)
273. E. Andrade, E. B. Ramirez, J. C. Alonso, M. F. Rocha, *IBA of ZrO₂:Yb/Si thin films produced by the spray pyrolysis method*, Nuclear Instr & Methods Phys Res B: Beam Interactions with Materials and Atoms 266, 2433-2436 (2008)
274. J. K. Lee, J. K. Sung, J. H. Lee, Y. Kwon, S.-J. Kim, P.-R. Kim, J.-K. Kim, K. Park, *The effect of processing conditions on the photoluminescence properties of Ca(Y_{0.94}Eu_{0.06})BO₄ phosphors synthesized by ultrasonic spray pyrolysis*, J Phys & Chem Solids 69, 1509-1512 (2008)
275. D. Jadsadapattarakul, C. Euvananont, C. Thanachayanont, J. Nukeaw, T. Sooknoi, *Tin oxide thin films deposited by ultrasonic spray pyrolysis*, Ceram Int 34, 1051-1054 (2008)
276. C.-L. Chang, C.-S. Hsu, B.-H. Hwang, *Unique porous thick Sm_{0.5}Sr_{0.5}CoO₃ solid oxide fuel cell cathode films prepared by spray pyrolysis*, J Power Sources 179, 734-738 (2008)
277. J. Su, M. Li, L. Guo, *Characterization of ultrasonic spray pyrolysis deposited WO₃ thin film for photoelectrochemical splitting of water*, Journal of Xi'an Jiaotong University 42, 617-621+625 (2008)
278. K. Ye, Z.-Z. Ye, S.-H. Hu, B.-H. Zhao, H.-P. He, L.-P. Zhu, *Effect of substrate style on properties of Ga-N codoped ZnMgO thin films*, Chinese J Luminescence 29, 499-502 (2008)
279. B.-C. Jiao, X.-D. Zhang, Y. Zhao, J. Sun, C.-C. Wei, R.-X. Yang, *Fabrication of P type ZnO thin film and its application in solar cells*, J Synthetic Cryst 37, 602-605 (2008)
280. J.-W. Wang, J.-M. Bian, H.-W. Liang, J.-C. Sun, J.-Z. Zhao, G.-T. Du, *The effect of Ag doping on the optical and electrical properties of ZnO films*, Chinese J Luminescence 29, 460-464 (2008)
281. S. U. Yuldashev, H. C. Jeon, T. W. Kang, R. A. Nusretov, I. V. Khvan, V. O. Pelenovich, *Magnetic and optical properties of Zn_{1-x}Mn_xO thin films prepared by using ultrasonic spray pyrolysis*, J Korean Phys Soc 53, 192-195 (2008)
282. J. H. Bang, R. J. Helmich, K. S. Suslick, *Nanostructured ZnS:Ni²⁺ photocatalysts prepared by ultrasonic spray pyrolysis* Adv Mater 20 (13), 2599-2603 (2008)
283. A. Avila-García, M. García-Hipólito, *Characterization of gas sensing HfO₂ coatings synthesized by spray pyrolysis technique*, Sensors & Actuators, B: Chemical 133, 302-307 (2008)
284. K. Hieda, T. Hyodo, Y. Shimizu, M. Egashira, *Preparation of porous tin dioxide powder by ultrasonic spray pyrolysis and their application to sensor materials*, Sensors & Actuators, B: Chemical 133, 144-150 (2008)
285. J.-W. Wang, J.-M. Bian, J.-C. Sun, H.-W. Liang, J.-Z. Zhao, G.-T. Du, *Ag doped p-type ZnO films and its optical and electrical properties*, Acta Physica Sinica 57, 5212-5216 (2008)
286. P. Singh, R. N. Deepak, A. K. Pandey, D. Kaur, *Intrinsic magnetism in Zn_{1-x}Co_xO (0.03 ≤ x ≤ 0.10) thin films prepared by ultrasonic spray pyrolysis*, J Phys Cond Mat 20, 315005 (2008)
287. D. S. Jung, S. H. Lee, Y. C. Kang, *Effects of dopants on grain growth of nano-sized BaTiO₃ powders prepared by citric acid-assisted spray pyrolysis*, J Ceram Processing Res 9, 307-310 (2008)
288. L. Castañeda, A. Maldonado, M. de la L. Olvera, *Sensing properties of chemically sprayed TiO₂ thin films using Ni, Ir, and Rh as catalysts*, Sensors & Actuators, B 133, 687-693 (2008)
289. J.-W. Wang, J.-M. Bian, J.-M. Liang, J.-C. Sun, J.-Z. Zhao, L.-Z. Hu, Y.-M. Luo, G.-T. Du, *Enhanced p-type ZnO films through nitrogen and argentine codoping grown by ultrasonic spray pyrolysis*, Chinese Phys Lett 25, 3400-3402 (2008)
290. H. Y. Koo, S. H. Lee, Y. C. Kang, *Effects of N,N-dimethylacetamide as drying control chemical additive on characteristics of Zn₂SiO₄:Mn, Ba phosphor powders prepared by spray pyrolysis*, Japanese J Appl Phys 47, 7407-7411 (2008)
291. H. A. Hamedani, K.-H. Dahmen, D. Li, H. Peydaye-Saheli, H. Garmestani, M. Khaleel, *Fabrication of gradient porous LSM cathode by optimizing deposition parameters in ultrasonic spray pyrolysis*, Mater Sci & Eng B 153, 1-9 (2008)
292. L.-C. Chena, C.-N. Pan, *Photoresponsivity enhancement of ZnO/Si photodiodes through use of an ultrathin oxide interlayer*, EPJ Appl Phys 44, 43-46 (2008)
293. J.-G. Yoon, K. O. Jung, H. J. Kim, K. S. Kim, *Charge transfer at the interfaces of polycrystalline ZnO/Zn_{1-x}Mg_xO/ZnO heterostructures*, J Korean Phys Soc 53, 2033-2038 (2008)

294. Park, K., Lee, J.K., Kwon, Y., Kim, S.-J., Nahm, S. *Luminescence properties of Ca(Y_{0.915-x}Gd_xAl_{0.025}Eu_{0.06})BO₄ phosphors under VUV irradiation*, J Nanosci & Nanotechnol 8, 5503-5505 (2008)
295. R. Martínez-Martínez, M. García, A. Speghini, M. Bettinelli, C. Falcony, U. Caldiño, *Blue-green-red luminescence from CeCl₃- and MnCl₂-doped hafnium oxide layers prepared by ultrasonic spray pyrolysis* J Phys Cond Mat 20 (39), 395205 (2008)
296. V. Jokanović, B. Jokanović, *Nanodesigning of SiO₂ powders obtained from silica sols by ultrasonic spray pyrolysis*, J Optoelectronics & Adv Mater 10, 2684-2693 (2008)
297. B. Han, G.-M. Wu, G.-J. Xing, Y. Wang, W. Jiang, D.-L. Li, *Growth and characterization of N-In codoped ZnO films deposited on glass substrates*, J Mater Eng (10), 283-286 (2008)
298. S.-W. Wei, B. Peng, L.-Y. Chai, Y.-C. Liu, Z.-Y. Li, *Preparation of doping titania antibacterial powder by ultrasonic spray pyrolysis*, Trans Nonferrous Metals Soc China 18, 1145-1150 (2008)
299. Y. Kwon, J.K. Lee, S.J. Kim, S. Nahm, K. Park, *Photoluminescent properties of (La_{1-x}Y_x)_{0.94}Tb_{0.06}PO₄ phosphor powders prepared by ultrasonic spray pyrolysis*, J Nanosci & Nanotechnol 8, 5499-5502 (2008)
300. X.-F. Chen, L. Wang, D.-R. Yang, *Preparation of In₂S₃ thin films by ultrasonic spray pyrolysis and the influence of post rapid thermal process*, J Synthetic Cryst 37, 1069-1072 (2008)
301. S. Kose, F. Atay, V. Bilgin, I. Akyuz, *Some physical properties of copper oxide films: The effect of substrate temperature*, Mater Chem & Phys 111, 351-358 (2008)
302. Sh.U. Yuldashev, T.W. Kang, R.A. Nusretov, I.V. Khvan, P.K. Khabibullaev, Y.K. Yeo, R.L. Hengehold, *Electroluminescence of n-Zn_{1-x}Mg_xO/ZnO/p-Zn_{1-x}Mg_xO heterostructures grown on Si substrates*, J Korean Phys Soc 53, 2913-2916 (2008)
303. C.H. Lu, T.Y. Wu, H.C. Wu, M.H. Yang, Z.Z. Guo, I. Taniguchi, *Preparation and electrochemical characteristics of spherical spinel cathode powders via an ultrasonic spray pyrolysis process*, Mater Chem & Phys 112, 115-119 (2008)
304. C.L. Chang, B.H. Hwang, *Microstructure and electrochemical characterization of Sm_{0.5} Sr_{0.5}CoO₃ films as SOFC cathode prepared by the electrostatic-assisted ultrasonic spray pyrolysis method*, Int J Appl Ceram Technol 5, 582-588 (2008)
305. T. Brylewski, K. Przybylski, *Perovskite and spinel functional coatings for SOFC metallic interconnects* Mater Sci Forum 595-598, 813-822 (2008)
306. Z. Pang, X. Tan, R. Ding, Z. Gu, S. Liu, *Preparation, characterization and catalytic performance of SrTi_{0.9}Li_{0.1}O₃ ultrafine powders*, Ceram Int 34, 1805-1810 (2008)
307. M. Hashimoto, H. Inoue, T. Hyodo, Y. Shimizu, M. Egashira, *Preparation and gas sensor application of ceramic particles with submicron-size spherical macropores* Sensor Lett 6, 887-890 (2008)
308. N. Bian, X.D. Zhang, X. Zhang, Y. Zhao, R.X. Yang, *Fabrication of wide band-gap semiconductor Zn_{1-x}Mg_xO thin film*, J Synthetic Cryst 37, 1361-1364 (2008)
309. V. Jokanović, Z. Nedić, B. Čolović, *Modelling and experimental investigations of thin films of Mg phosphorus-doped tungsten bronzes obtained by ultrasonic spray pyrolysis*, J Microscopy 232, 623-628 (2008)
310. M. Konarova, I. Taniguchi, *Preparation of LiFePO₄/C composite powders by ultrasonic spray pyrolysis followed by heat treatment and their electrochemical properties*, Mater Res Bull 43, 3305-3317 (2008)
311. J.M. Han, D.S. Jung, Y.C. Kang, *LaPO₄: Tb phosphor powders prepared by spray pyrolysis using two different spray generators*, J Ceram Processing Res 9, 495-499 (2008)
312. K. Liu, B.F. Yang, H. Yan, Z. Fu, M. Wen, Y. Chen, J. Zuo, *Strong room-temperature ultraviolet emission from nanocrystalline ZnO and ZnO:Ag films grown by ultrasonic spray pyrolysis*, Appl Surf Sci 255, 2052-2056 (2008)
313. W. Vonau, F. Gerlach, U. Enseleit, J. Spindler, T. Bachmann, *New solid-state glass electrodes by using zinc oxide thin films as interface layer*, J Solid State Electrochem 13, 91-98 (2009)
314. T. Adachi, N. Wakiya, N. Sakamoto, O. Sakurai, K. Shinozaki, H. Suzuki, *Spray pyrolysis of Fe₃O₄-BaTiO₃ composite particles*, J Am Ceram Soc 92, S177-S180 (2009)
315. W. Bin, W., Yue, Z., Jiahua, M., Wenbin, S. *Ag-N dual-accept doping for the fabrication of p-type ZnO*, Appl Phys A 94, 715-718 (2009)
316. Bouzid, K., Djelloul, A., Bouzid, N., Bougdira, J. *Electrical resistivity and photoluminescence of zinc oxide films prepared by ultrasonic spray pyrolysis* Physica Status Solidi (A) Applications and Materials 206 (1), pp. 106-115 (2009)

317. M.T. Htay, M.T., Tani, Y., Hashimoto, Y., Ito, K. *Synthesis of optical quality ZnO nanowires utilizing ultrasonic spray pyrolysis*, J Mater Sci, pp. S341-S345 (2009)
318. C.Y. Zhang, *The influence of substrate and annealing temperatures on electrical properties of p-type ZnO films*, Physica B 404, 138-142 (2009)
319. H. Yamada, T. Okawa, T. Ogihara, *Sintering and dielectric properties of Ba(Mg_{1/3}Ta_{2/3})O₃ particle prepared by spray pyrolysis*, Key Eng Mater 388, 245-248 (2009)
320. H. Liu, Z. Shi, J. Zhang, L. Zhang, J. Zhang, *Ultrasonic spray pyrolyzed iron-polypyrrole mesoporous spheres for fuel cell oxygen reduction electrocatalysts*, J Mater Chem 19, 468-470 (2009)
321. X. Zhang, X.D. Zhang, N. Bian, R.X. Yang, Y. Zhao, *Influence of substrate temperature on the performance of ZnO nanostructure*, J Optoelectronics Laser 20, 200-203 (2009)
322. N. Bian, X.D. Zhang, X. Zhang, Y. Zhao, R.X. Yang, *Fabrication of P type Zn_{1-x}Mg_xO thin film by ultrasonic spray pyrolysis*, J Optoelectronics Laser 20, 196-199 (2009)
323. I. Khatri, T. Soga, T. Jimbo, S. Adhikari, H.R. Aryal, H.R., Umeno, M. *Synthesis of single walled carbon nanotubes by ultrasonic spray pyrolysis method* Diamond and Related Materials 18, 319-323 (2009)
324. S. Buecheler, D. Corica, D. Guettler, A. Chirila, R. Verma, U. Müller, T.P. Niesen, A.N. Tiwari, *Ultrasonically sprayed indium sulfide buffer layers for Cu(In,Ga)(S,Se)₂ thin-film solar cells*, Thin Solid Films 517, 2312-2315 (2009)
326. N. Kavasoglu, A.S. Kavasoglu, S. Oktik, *Observation of negative photoconductivity in (ZnO)_x(CdO)_{1-x} films*, J Phys & Chem Solids 70, 521-526 (2009)
327. L. Zhang, T. Yabu, I. Taniguchi, *Synthesis of spherical nanostructured LiM_xMn_{2-x}O₄ (M = Ni²⁺, Co³⁺, and Ti⁴⁺; 0 ≤ x ≤ 0.2) via a single-step ultrasonic spray pyrolysis method and their high rate charge-discharge performances*, Mater Res Bull 44, 707-713 (2009)
328. P. Singh, A. Kaushal, D. Kaur, *Mn-doped ZnO nanocrystalline thin films prepared by ultrasonic spray pyrolysis*, J Alloys & Comp 471, 11-15 (2009)
329. Y. Huang, K. Deng, Z. Ai, L. Zhang, *Ultrasonic spray pyrolysis synthesis and visible light activity of carbon-doped Ti_{0.9}Zr_{0.09}O₂ solid solution photocatalysts*, Mater Chem & Phys 114, 235-241 (2009)
330. J.H. Lee, M.H. Heo, S.J. Kim, S. Nahm, K. Park, *Photoluminescence properties of (Y_{1-x-y}M_xEu_y)BO₃ (M = Al, Zn, and La) phosphors prepared by ultrasonic spray pyrolysis under VUV excitation*, J Alloys & Comp 473, 272-274 (2009)
331. X. Chen, P. Yao, D. Wang, X. Wu, *Antimony and cerium co-doped tin oxide electrodes for pollutant degradation*, Chem Eng J 147, 412-415 (2009)
332. W. Bin, Z. Yue, M. Jiahua, S. Wenbin, *Photoluminescence in ZnO film prepared by electrostatic-enhanced ultrasonic spray pyrolysis*, Optoelectron & Adv Mater: Rapid Commun 3, 450-454 (2009)
333. B.W. Mwakikunga, E. Sideras-Haddad, C. Arendse, M.J. Witcomb, A. Forbes, *WO₃ nano-spheres into w18049 one-dimensional nano-structures through thermal annealing*, J Nanosci & Nanotechnol 9, 3286-3294 (2009)
334. H.C. Jang, S.H. Ju, Y.C. Kang, *Properties of lithium cobaltate powders prepared by FEAG and ultrasonic spray pyrolysis process*, J Ceram Soc Japan 117, 709-712 (2009)
335. J.Y. Kim, U. Kim, W.-S. Cho, *Synthesis of ceria nanosphere by ultrasonic spray pyrolysis*, J Korean Ceram Soc 46, 249-252 (2009)
336. E. Zaleta-Alejandre, M. Zapata-Torres, M. García-Hipólito, M. Aguilar-Frutis, G. Alarcón-Flores, J. Guzmán-Mendoza, C. Falcony, *Structural and luminescent properties of europium doped TiO₂ thick films synthesized by the ultrasonic spray pyrolysis technique*, J Phys D: Appl Phys 42, 095102 (2009)
337. G.-S. Zhao, K. Liang, T.-Y. Guo, Q.-Z. Wang, *Effects of substrate temperature on the characteristics of large-area textured SnO₂:F films prepared by ultrasonic spray deposition method*, J Optoelectron Laser 20, 758-761 (2009)
338. T. Özer, S. Köse, *Some physical properties of Cd_{1-x}Sn_xS films used as window layer in heterojunction solar cells*, Int J Hydrogen Energy 34, 5186-5190 (2009)
339. S. Kose, F. Atay, V. Bilgin, I. Akyuz, *In doped CdO films: Electrical, optical, structural and surface properties*, Int J Hydrogen Energy 34, 5260-5266 (2009)
340. M. Engin, F. Atay, S. Kose, V. Bilgin, I. Akyuz, *Growth and characterization of Zn-incorporated copper oxide films*, J Electron Mater 38, 787-796 (2009)
341. B. Ergin, E. Ketenci, F. Atay, *Characterization of ZnO films obtained by ultrasonic spray pyrolysis technique*, Int J Hydrogen Energy 34, 5249-5254 (2009)

342. L. Castañeda, *Influence of Colloidal Silver Nanoparticles on the Performance of Novel Flower-Like Titanium Dioxide Oxygen Sensor*, *Sensors & Mater* 21, 25-36 (2009)
343. B. Wang, J. Min, Y. Zhao, W. Sang, C. Wang, *The grain boundary related p -type conductivity in ZnO films prepared by ultrasonic spray pyrolysis*, *Appl Phys Lett* 94, 192101 (2009)
344. R. Zheng, X. Meng, F. Tang, *High-density magnetite nanoparticles located in carbon hollow microspheres with good dispersibility and durability: Their one-pot preparation and magnetic properties*, *Eur J Inorganic Chem* 20, 3003-3007 (2009)
345. V.Sh. Yalishev, S.H. Hong, B.H. Park, V. Pelenovich, S.U. Yuldashev, *Influence of Mn-oxide nanoclusters on the electric properties of ZnO:Mn films*, *J Kor Phys Soc* 55, 20-23 (2009)
346. Y. Kwon, J.K. Lee, J.K. Sung, J.H. Lee, S.-J. Kim, Y.S. Shin, K. Park, *Synthesis and photoluminescence properties of spherical fine red $(Y_{1-x-y}Gd_xEu_y)BO_3$ ($0 \leq x \leq 0.36$, $0.06 \leq y \leq 0.13$) phosphors using ultrasonic spray pyrolysis*, *J Nanosci & Nanotechnol* 9, 4202-4206 (2009)
347. Zhang, Y., Sun, X., Pan, L., Li, H., Sun, Z., Sun, C., Tay, B.K. *Carbon nanotube-zinc oxide electrode and gel polymer electrolyte for electrochemical supercapacitors* *Journal of Alloys and Compounds* 480 (2), L17-L19 (2009)
348. S. Gurmen, B. Ebin, S. Stopić, B. Friedrich, *Nanocrystalline spherical iron-nickel (Fe-Ni) alloy particles prepared by ultrasonic spray pyrolysis and hydrogen reduction (USP-HR)*, *J Alloys & Comp* 480, 529-533 (2009)
349. J.-K. Chung, W.-J. Kim, Y.-J. Lim, S.-C. Park, C.-J. Kim, *Synthesis and characterization of MgB_2 films deposited by ultrasonic spray pyrolysis*, *Int J Modern Phys B* 23, 3515-3519 (2009)
350. S.S. Dunkle, R.J. Helmich, K.S. Suslick, *$BiVO_4$ as a visible-light photocatalyst prepared by ultrasonic spray pyrolysis* *J. Phys. Chem. C* 113 (28), 11980-11983 (2009)
351. S.E. Skrabalak, *Ultrasound-assisted synthesis of carbon materials* *Phys. Chem. Chem. Phys.* 11 (25), 4930-4942 (2009)
352. J.H. Bang, K.S. Suslick, *Dual templating synthesis of mesoporous titanium nitride microspheres*, *Adv Mater* 21, 3186-3190 (2009)
353. S. Gurmen, A. Guven, B. Ebin, S. Stopić, B. Friedrich, *Synthesis of nano-crystalline spherical cobalt-iron (Co-Fe) alloy particles by ultrasonic spray pyrolysis and hydrogen reduction* *J. Alloys & Comp.* 481, 600-604 (2009)
354. S. Choi, K. Kim, S. Nahm, H.-K. Jung, *Controlled synthesis and improved luminescent properties of $(Gd_{1-x}Eu_x)_3GaO_6$ phosphors fabricated via spray pyrolysis*, *Opt Mater* 31, 1684-1687 (2009)
355. R.N. Goyal, D. Kaur, A.K. Pandey, *Growth and characterization of iron oxide nanocrystalline thin films via low-cost ultrasonic spray pyrolysis*, *Mater Chem & Phys* 116, 638-644 (2009)
356. Z. Rongbo, M. Xianwei, T. Fangqiong, Z. Lin, R. Jun, *A general, one-step and template-free route to rattle-type hollow carbon spheres and their application in lithium battery anodes* *J. Phys. Chem. C* 113 (30), 13065-13069 (2009)
357. Y. Zhang, H. Li, L. Pan, T. Lu, Z. Sun, *Capacitive behavior of graphene-ZnO composite film for supercapacitors*, *J Electroanal Chem* 634, 68-71 (2009)
358. J.S. Cho, Y.C. Kang, *Synthesis of spherical shape borate-based bioactive glass powders prepared by ultrasonic spray pyrolysis* *Ceramics International* 35 (6), 2103-2109 (2009)
359. F.-T. Liu, S.-F. Gao, S.-K. Pei, S.-C. Tseng, C.-H.J. Liu, *ZnO nanorod gas sensor for NO_2 detection*, *J Taiwan Inst Chem Eng* 40, 528-532 (2009)
360. V. Bilgin, *Preparation and characterization of ultrasonically sprayed zinc oxide thin films doped with lithium*, *J Electron Mater* 38, 1969-1978 (2009)
361. K. Liu, B. Yang, H. Yan, Z. Fu, M. Wen, Y. Chen, J. Zuo, *Effect of Ag doping on the photoluminescence properties of ZnO films*, *J Luminescence* 129, 969-972 (2009)
362. C.-S. Kim, S.I. Hwang, S. Kim, *Electrochemical properties of $LiFePO_4/C$ composite improved by high energy milling*, *Mater Sci Forum* 620 622, 41-44 (2009)
363. S.H. Kim, C.-S. Kim, *Improving the rate performance of $LiCoO_2$ by Zr doping*, *J Electroceram* 23, 254-257 (2009)
364. D.S. Jung, H.Y. Koo, H.C. Jang, Y.C. Kang, *Effects of La content on the properties of $Ba_{1-x}La_xTiO_3$ powders prepared by spray pyrolysis*, *Metals & Mater Int* 15, 809-814 (2009)

365. Ž. Antić, R. Krsmanović, V. Dor.ević, T. Dramićanin, M.D. Dramićanin, *Optical properties of $Y_2O_3:Eu^{3+}$ red emitting phosphor obtained via spray pyrolysis*, Acta Phys Polonica A 116, 622-624 (2009)
366. D.J. Jovanović, I. Lj.validžić, M. Mitrić, J.M. Nedeljković, *Structure of disodium dimolybdate synthesized using thermodynamically stable molybdenum (VI) oxide clusters as precursors*, J Am Ceram Soc 92, 2467-2470 (2009)
367. M. Than Htay, Y. Hashimoto, N. Momose, K. Ito, *Position-selective growth of ZnO nanowires by ultrasonic spray pyrolysis*, J Cryst Growth 311, 4499-4504 (2009)
368. D. S. Jung, H.K. Koo, J.M. Han, Y.C. Kang, *Micrometre-sized zinc silicate phosphor powders prepared using a size-controllable droplet generator from a polyethylene glycol spray solution*, J Ceram Process Res 10, 423-427 (2009)
369. A. Avila-García, C. Torres-Fraustob, *Impedance response of franklinite films to humidity and propane*, Adv Mater Res 68,109-115 (2009)
370. A. Kaushal, P. Bansal, R. Vishnoi, N. Choudhary, D. Kaur, *Room-temperature ferromagnetism in $Sn_{1-x}Mn_xO_2$ nanocrystalline thin films prepared by ultrasonic spray pyrolysis*, Physica B: Cond Mat 404, 3732-3738 (2009)
371. M.A. Haider, S. McIntosh, *Evidence for two activation mechanisms in LSM SOFC cathodes*, J. Electrochem Soc 156, B1369-B1375 (2009)
372. Y. Zhang, X. Sun, L. Pan, H. Li, Z. Sun, C. Sun, B.K. Tay, *Carbon nanotube-ZnO nanocomposite electrodes for supercapacitors*, Solid State Ionics 180, 1525-1528 (2009)
373. J.Q. Zhang, F.S. Zhang, A.M. Liu, W.F. Liu, *Preliminary study on textured ZnO/Si heterojunction solar cells*, J Synthetic Cryst 38, 1344-1348 (2009)
374. L.A. Patil, M.D. Shinde, A.R. Bari, V.V. Deo, *Novel trapping system for size wise sorting of SnO_2 nanoparticles synthesized from pyrolysis of ultrasonically atomized spray for gas sensing*, Sensors & Actuators B 143, 316-324 (2009)
375. L.A. Patil, M.D. Shinde, A.R. Bari, V.V. Deo, *Highly sensitive and quickly responding ultrasonically sprayed nanostructured SnO_2 thin films for hydrogen gas sensing*, Sensors & Actuators, B 143, 270-277 (2009)
376. V.O. Pelenovich, Sh.U. Yuldashev, A.S. Zakirov, P.K. Khabibullaev, R.A. Nusretov, V.Yu. Sokolov, *Optical and magneto-optical properties of thin $Zn_{1-x}Mn_xO$ films doped by nitrogen*, Physica B 404, 5266-5268 (2009)
377. C.C. Lin, M.C. Chiang, Y.W. Chen, *Temperature dependence of fluorine-doped tin oxide films produced by ultrasonic spray pyrolysis*, Thin Solid Films 518, 1241-1244 (2009)
378. A. Kaushal, D. Pathak, R.K. Bedi, D. Kaur, *Structural, electrical and optical properties of transparent $Zn_{1-x}Mg_xO$ nanocomposite thin films*, Thin Solid Films 518, 1394-1398 (2009)
379. M.F. García-Sánchez, A. Ortiz, G. Santana, M. Bizarro, J. Peña, F. Cruz-Gandarilla, M.A. Aguilar-Frutis, J.C. Alonso, *Synthesis and characterization of nanostructured cerium dioxide thin films deposited by ultrasonic spray pyrolysis*, J Am Ceram Soc 93, 155-160 (2010)
380. N. Wakiya, M. Yamasaki, T. Adachi, A. Inukai, N. Sakamoto, D. Fu, O. Sakurai, H. Suzuki, *Preparation of hydroxyapatite-ferrite composite particles by ultrasonic spray pyrolysis*, Mater Sci & Eng B 173, 195-198 (2010)
381. V. Jokanovic, Z. Nedic, *Nano-designing of Mg doped phosphate tungsten bronzes and SiO_2 composite obtained by ultrasonic spray pyrolysis method*, Ultrasonics Sonochem 17, 228-233 (2010)
382. C.C. Lin, Y.W. Chen, M.C. Chiang, C.H. Lee, Y.L. Tung, S.Y. Chen, *Photoconductive enhancement of single-layer Tin oxide-coated ZnO nanowires*, J Electrochem Soc 157, H227-H230 (2010)
383. L. Castañeda, A. López-Suárez, A. Tiburcio-Silver, *Influence of colloidal silver nanoparticles on the novel flower-like titanium dioxide oxygen sensor performances*, J Nanosci & Nanotechnol 10, 1343-1348 (2010)
384. D. Jadsadapattarakul, C. Thanachayanont, J. Nukeaw, T. Sooknoi, *Improved selectivity, response time and recovery time by [0 1 0] highly preferred-orientation silicalite-1 layer coated on SnO_2 thin film sensor for selective ethylene gas detection*, Sensors & Actuators B 144, 73-80 (2010)
385. V.V. Kireev, L.N. Dem'Yanets, L.E. Li, V.V. Artemov, *Growth of thin ZnO films by ultrasonic spray pyrolysis*, Inorganic Mater 46, 154-162 (2010)

386. T. Nakamura, Y. Nakatani, T. Ogihara, H. Horikawa, M. Asahara, *Electrical properties of dye-sensitized solar cells prepared by blending SnO₂ micro particles and TiO₂ nano particles*, Key Eng Mater 421-422, 368-371 (2010)
387. T.N.L Doan, Z. Bakenov, I. Taniguchi, *Preparation of carbon coated LiMnPO₄ powders by a combination of spray pyrolysis with dry ball-milling followed by heat treatment*, Adv Powder Technol 21, 187-196 (2010)
388. M. Van Den Bossche, R. Matthews, A. Lichtenberger, S. McIntosh, *Insights into the fuel oxidation mechanism of La_{0.75}Sr_{0.25}Cr_{0.5}Mn_{0.5}O_{3-δ} SOFC anodes*, J Electrochem Soc 157, B392-B399 (2010)
389. K. Park, S.W. Nam, *Red-emitting (Y_{0.5}Gd_{0.5})_{0.94-x}Al_xEu_{0.06}VO₄ (0 ≤ x ≤ 0.04) phosphors for plasma display panel applications*, Opt Mater 32, 612-615 (2010)
390. R. Martínez-Martínez, E. Álvarez, A. Speghini, C. Falcony, U. Caldiño, *Cold white light generation from hafnium oxide films activated with Ce³⁺, Tb³⁺, and Mn²⁺ Ions*, J Mater Res 25, 484-490 (2010)
391. S. Gurmen, B. Ebin, *Production and characterization of the nanostructured hollow iron oxide spheres and nanoparticles by aerosol route*, J Alloys & Comp 492, 585-589 (2010)
392. M.E. Fortunato, M. Rostam-Abadi, K.S. Suslick, *Nanostructured carbons prepared by ultrasonic spray pyrolysis*, Chem Mater 22, 1610-1612 (2010)
393. J.H. Bang, K.S. Suslick, *Applications of ultrasound to the synthesis of nanostructured materials*, Adv Mater 22, 1039-1059 (2010)
394. J. Xu, H. Wang, L. Yang, M. Jiang, S. Wei, T. Zhang, *Low temperature growth of highly crystallized ZnO:Al films by ultrasonic spray pyrolysis from acetylacetone salt*, Mater Sci & Eng B 167, 182-186 (2010)
395. J.G. Mendoza, M.A. Aguilar Frutis, G.A. Flores, M.G. Hipólito, A. Maciel Cerda, J.A. Nieto, T.R. Montalvo, C. Falcony, *Synthesis and characterization of hafnium oxide films for thermo and photoluminescence applications*, Appl Rad & Isotopes 68, 696-699 (2010)
396. I. Akyuz, S. Kose, F. Atay, V. Bilgin, *Preparation and characterization of aluminum-incorporated cadmium oxide films*, Mater Sci Semicond Processing 13, 109-114 (2010)
397. D. Ragazzon, A. Nakaruk, C.C. Sorrell, *Deposition rate of anatase films by ultrasonic spray pyrolysis*, Adv Appl Ceram 109, 196-199 (2010)
398. A. Nakaruk, P.J. Reece, D. Ragazzon, C.C. Sorrell, *TiO₂ films prepared by ultrasonic spray pyrolysis*, Mater Sci & Technol 26, 469-472 (2010)
399. S. Kose, F. Atay, V. Bilgin, I. Akyuz, E. Ketenci, *Optical characterization and determination of carrier density of ultrasonically sprayed CdS:Cu films*, Appl Surf Sci 256, 4299-4303 (2010)
400. G. Kenanakis, Z. Giannakoudakis, D. Vernardou, C. Savvakis, N. Katsarakis, *Photocatalytic degradation of stearic acid by ZnO thin films and nanostructures deposited by different chemical routes*, Catalysis Today 151, 34-38 (2010)
401. Y. Huang, Z. Ai, W. Ho, M. Chen, S. Lee, *Ultrasonic spray pyrolysis synthesis of porous Bi₂WO₆ microspheres and their visible-light-induced photocatalytic removal of NO*, J Phys Chem C 114, 6342-6349 (2010)
402. M.A. García-Lobato, V.A. Hernández H.M. Hdz-García, A.I. Martíneza, M.I. Pech-Canul, *Fe₂O₃ thin films prepared by ultrasonic spray pyrolysis*, Mater Sci Forum 644, 105-108 (2010)
403. Lu, T., Zhang, Y., Li, H., Pan, L., Li, Y., Sun, Z. *Electrochemical behaviors of graphene-ZnO and graphene-SnO₂ composite films for supercapacitors*, Electrochimica Acta 55, 4170-4173 (2010)
404. A. Nakaruk, D. Ragazzon, C.C. Sorrell, *Anatase thin films by ultrasonic spray pyrolysis*, J Analytical & Appl Pyrolysis 88, 98-101 (2010)
405. A. Nakaruk, D. Ragazzon, C.C. Sorrell, *Anatase-rutile transformation through high-temperature annealing of titania films produced by ultrasonic spray pyrolysis*, Thin Solid Films 518, 3735-3742 (2010)
406. M. Yamada, T. Kodera, T. Ogihara, *Synthesis and electrochemical properties of C/Li₄Ti₅O₁₂ powders by spray pyrolysis using aqueous solution of organic acid*, Electrochem 78, 463-466 (2010)
407. S.H. Nam, M.H. Kim, J.Y. Lee, S.D. Lee, J.H. Boo, *Spray pyrolysis of manganese doped zinc silicate phosphor particles*, Functional Mater Lett 3, 97-100 (2010)
408. L.C. Chen, C.H. Tien, Y.Y. Hsu, *Optoelectronic properties of the p-MnZnO/n-Si structure photodiodes in a strong magnetic field*, Japanese J Appl Phys 49, 0630021-0630023 (2010)
409. A.K. Peterson, D.G. Morgan, S. Skrabalak, *Aerosol synthesis of porous particles using simple salts as a pore template* Langmuir 26, 8804-8809 (2010)

410. A.H. Zhong, J. Tan, S.C. Chen, L.M. Bao, F. Ai, F. Li, *Effect of substrate temperature on surface morphology and photoluminescence of N-Al co-doped ZnO thin films*, J Functional Mater 41, 1008-1011 (2010)
411. K. Itatani, T. Tsugawa, T. Umeda, Y. Musha, I.J. Davies, S. Koda, *Preparation of submicrometer-sized porous spherical hydroxyapatite agglomerates by ultrasonic spray pyrolysis technique* J Ceram Soc Japan 118, 462-466 (2010)
412. A.A. Firooz, T. Hyodo, A.R. Mahjoub, A.A. Khodadadi, Y. Shimizu, *Synthesis and gas-sensing properties of nano- and meso-porous MoO₃-doped SnO₂*, Sensors & Actuators B 147, 554-560 (2010)
413. J. Zhang, I. Khatri, N. Kishi, T. Soga, T. Jimbo, *Synthesis of carbon nanofibers using C60, graphite and boron*, Mater Lett 64, 1243-1246 (2010)
414. A. Nakaruk, G. Kavei, C.C. Sorrell, *Synthesis of mixed-phase titania films by low-temperature ultrasonic spray pyrolysis*, Mater Lett 64, 1365-1368 (2010)
416. Li, M., Jiang, J., Guo, L. *Synthesis, characterization, and photoelectrochemical study of Cd 1-xZnxS solid solution thin films deposited by spray pyrolysis for water splitting*, Int J Hydrogen Energy 35, 7036-7042 (2010)
417. Y. Guo, Y. Xia, M.J. Min, Y. Zhao, B. Wang, *Influence of polar tourmaline substrates on the growth of ZnO nanoplates*, J Inorganic Mater 25, 717-720 (2010)
418. K. Park, S.W. Nam, M.H. Heo, M.H. *VUV photoluminescence properties of Y1-xGdxVO 4:Eu phosphors prepared by ultrasonic spray pyrolysis*, Ceramics Inter 36, 1541-1544 (2010)
419. M. Li, L. Zhao, L. Guo, *Preparation and photoelectrochemical study of BiVO₄ thin films deposited by ultrasonic spray pyrolysis*, International Journal of Hydrogen Energy 35 (13), pp. 7127-7133 (2010)
420. X. Meng, T. Wen, S. Sun, R. Zheng, J. Ren, F. Tang, *Synthesis and Application of Carbon-Iron Oxide Microspheres' Black Pigments in Electrophoretic Displays*, Nanoscale Res Lett 5, 1664-1668 (2010)
421. M. Zhang, W. Luo, Z. Li, T. Yu, Z. Zou, *Improved photoelectrochemical responses of Si and Ti codoped α -Fe₂O₃ photoanode films*, Appl Phys Lett 97, 042105 (2010)
422. D. Mesguich, J.-M. Bassat, C. Aymonier, E. Djurado, *Nanopowder synthesis of the SOFC cathode material Nd₂NiO_{4+ δ} by ultrasonic spray pyrolysis*, Solid State Ionics 181 (21-22), pp. 1015-1023 (2010)
423. Q. Li, Y. Gao, Z. Liu, Z. Liu, Y. Li, *Preparation and characteristics of BaTiO₃ particles by ultrasonic spray pyrolysis*, Powder Metallurgy Technol 28, 292-296+301 (2010)
424. Q. Feng, *Oxygen sensing property of noble metal-doped TiO₂ films deposited by ultrasonic spray pyrolysis*, J Vac Sci & Technol 30, 385-389 (2010)
425. D. Torres-Torres, M. Trejo-Valdez, L. Castañeda, C. Torres-Torres, L. Tamayo-Rivera, R.C. Fernández-Hernández, J.A. Reyes-Esqueda, A. Oliver, *Inhibition of the two-photon absorption response exhibited by a bilayer TiO₂ film with embedded Au nanoparticles*, Opt Express 18, 16406-16417 (2010)
426. R. Martínez-Martínez, E. Álvarez, A. Speghini, C. Falcony, U. Caldiño, *White light generation in Al₂O₃:Ce³⁺:Tb³⁺:Mn²⁺ films deposited by ultrasonic spray pyrolysis*, Thin Solid Films 518, 5724-5730 (2010)
427. Y. Guo, X. Wei, B. Wang, Y. Zhao, J. Min, W. Sang, *A novel chrysanthemum-like ZnO nanostructure synthesized by the ultrasonic spray pyrolysis method*, Physica Status Solidi C 7, 1577-1579 (2010)
428. M. Benhaliliba, C.E. Benouis, M.S. Aida, F. Yakuphanoglu, A. Sanchez Juarez, *Indium and aluminium-doped ZnO thin films deposited onto FTO substrates: Nanostructure, optical, photoluminescence and electrical properties*, J Sol-Gel Sci & Technol 55, 335-342 (2010)
429. V. Bilgin, I. Akyuz, E. Ketenci, S. Kose, F. Atay, *Electrical, structural and surface properties of fluorine doped tin oxide films*, Appl Surf Sci 256, 6586-6591 (2010)
430. L.A. Patil, M.D. Shinde, A.R. Bari, V.V. Deo, *Highly sensitive ethanol sensors based on nanocrystalline SnO₂ thin films*, Curr Appl Phys 10, 1249-1254 (2010)
431. F. Atay, V. Bilgin, I. Akyuz, E. Ketenci, S. Kose, *Optical characterization of SnO₂:F films by spectroscopic ellipsometry*, J Non-Crystalline Solids 356, 2192-2197 (2010)
432. S.-M. Oh, S.W. Oh, S.-T. Myung, S.-M. Lee, Y.-K. Sun, *The effects of calcination temperature on the electrochemical performance of LiMnPO₄ prepared by ultrasonic spray pyrolysis*, J Alloys & Comp 506, 372-376 (2010)
433. N. Khatri, I. Kishi, J. Zhang, T. Soga, T. Jimbo, S. Adhikari, H.R. Aryal, M. Umeno, *Synthesis and characterization of carbon nanotubes via ultrasonic spray pyrolysis method on zeolite*, Thin Solid Films 518, 6756-6760 (2010)

434. A. Nautiyal, K.C. Sekhar, N. Pathak, R. Nath, *Study of ferroelectric properties of spray pyrolysis deposited cesium nitrate films*, Thin Solid Films 518, e143-e145 (2010)
435. K. Park, S.W. Nam, *VUV photoluminescence characteristics of (Y,Gd)VO₄:Eu,Zn phosphors produced by ultrasonic spray pyrolysis*, Mater Chem & Phys 123, 601-605 (2010)
436. C. Özgür, *Preparation and characterization of LiMn₂O₄ ion-sieve with high Li⁺ adsorption rate by ultrasonic spray pyrolysis*, Solid State Ionics 181, 1425-1428 (2010)
437. K. Marinkovic, L. Mancic, L.S. Gomez, M.E. Rabanal, M. Dramicanin, O. Milosevic, *Photoluminescent properties of nanostructured Y₂O₃:Eu³⁺ powders obtained through aerosol synthesis*, Opt Mater 32, 1606-1611 (2010)
438. S.-M. Oh, S.-W. Oh, C.-S. Yoon, B. Scrosati, K. Amine, Y. Sun, *High-performance carbon-LiMnPO₄ nanocomposite cathode for lithium batteries*, Adv Functional Mater 20, 3260-3265 (2010)
439. L.A. Patil, A.R. Bari, M.D. Shinde, V. Deo, *Ultrasonically synthesized nanocrystalline ZnO powder-based thick film sensor for ammonia sensing*, Sensor Rev 30, 290-296 (2010)
440. L. Liu, G.-Y. Kim, A. Chandra, *Fabrication of solid oxide fuel cell anode electrode by spray pyrolysis*, J Power Sources 195, 7046-7053 (2010)
441. B.J. Babu, A. Maldonado, S. Velumani, R. Asomoza, *Electrical and optical properties of ultrasonically sprayed Al-doped zinc oxide thin films*, Mater Sci & Eng B: Solid-State Mater Adv Technol 174, 31-37 (2010)
442. M. De La Garza, T. Hernández, R. Colás, I. Gómez, *Deposition of gold nanoparticles on glass substrate by ultrasonic spray pyrolysis*, Mater Sci & Eng B: Solid-State Mater Adv Technol 174, 9-12 (2010)
443. B. Jokić, S. Drmanić, T. Radetic, J. Krstić, R. Petrović, A. Orlović, D. Janačković, *Synthesis of submicron carbon spheres by the ultrasonic spray pyrolysis method*, Mater Lett 64, 2173-2176 (2010)
444. D.S. Jung, H.Y. Koo, Y.C. Kang, *Fine-sized Bi_{0.5}Na_{0.5}TiO₃ powders prepared by spray pyrolysis from polymeric precursors*, J Ceram Processing Res 11, 425-431 (2010)
445. A. Djelloul, M.-S. Aida, J. Bougdira, *Photoluminescence, FTIR and X-ray diffraction studies on undoped and Al-doped ZnO thin films grown on polycrystalline α -alumina substrates by ultrasonic spray pyrolysis* J Luminescence 130, 2113-2117 (2010)
446. C. Özgür, O. Şan, *Preparation of spherical and dense Na₂O-B₂O₃-SiO₂ glass powders by ultrasonic spray pyrolysis technique*, J Non-Crystalline Solids 356, 2794-2798 (2010)
447. T. Hyodo, H. Inoue, H. Motomura, K. Matsuo, T. Hashishin, J. Tamaki, Y. Shimizu, M. Egashira, *NO₂ sensing properties of macroporous In₂O₃-based powders fabricated by utilizing ultrasonic spray pyrolysis employing polymethylmethacrylate microspheres as a template* Sensors & Actuators B 151, 265-273 (2010)
448. H.-Y. Li, S.-H. Pang, J. Ma, S.-P. Ren, *Effect of Al-doped on optics and electricity of ZnO (ZnO: Al) thin films*, J Wuhan University Technol 32, 138-140+145 (2010)
449. A. Huczko, A. DaBrowska, D.K. Madhup, D.P. Subedi, S.P. Chimouriya, *Al-doped ZnO nanofilms: Synthesis and characterization* Phys Status Solidi (B) Basic Research 247, 3035-3038 (2010)
450. A. Meza-Rocha, L. Pérez-Arrieta, E. Zaleta-Alejandre, Z. Rivera, R. Balderas-Xicohtencatl, C. Falcony, *Synthesis of La_xAl_{2-x}O₃ films using ultrasonic spray pyrolysis technique*, ECS Transactions 33, 165-169 (2010)
451. M. Peker, D. Peker, M. Selami Klkaya, *Structural and optical properties of Cd_{1-x}Sn_xS semiconductor films produced by the ultrasonic spray pyrolysis method*, Physica B: Cond Mat 405, 4831-4837 (2010)
452. Z.-C. Yan, H.-M. Zhang, B. Gao, Y.-J. Zhu, *Preparation of Al Doped ZnO transparent conductive films by ultrasonic spray pyrolysis*, J Synthetic Cryst 39, 1376-1380 (2010)
453. K.-W. Lee, C.-W. Lee, S.-G. Kim, J.-S. Lee, *Real-time transformation of FePt nanoparticles to L10 phase by the gas phase synthesis*, J Korean Inst Metals & Mater 49, 46-51 (2011)
454. C. Özgür, F. Çolak, O. Şan, *Preparation, characterization and antimicrobial property of micro-nano sized Na-borosilicate glass powder with spherical shape*, J Non-Cryst Solids 357, 116-120 (2011)
455. A. Toriyama, K. Myoujin, T. Kodera, T. Oghihara, *Preparation and characterization of La_{0.8}Sr_{0.2}Ga_{0.8}Mg_{0.2}O_{3- δ} film by electrophoretic deposition method*, Key Eng Mater 445, 86-90 (2010)
456. R. Zheng, X. Guo, H. Fu, *One-step, template-free route to silver porous hollow spheres and their optical property*, Appl Surf Sci 257, 2367-2370 (2011)

457. Z.D., Yakinci, Y. Aydoğdu, *Thickness dependence of critical current density in MgB₂ films prepared by thermal evaporation method*, J. Supercond. & Novel Magnetism 24, 523-527 (2011)
458. D.-Y. Lee, J.Kim, *Deposition of CuInS₂ films by electrostatic field assisted ultrasonic spray pyrolysis*, Solar Energy Materials and Solar Cells 95 (1), 245-249 (2011)
459. N.C. Raut, T. Mathews, S. Rajagopalan, R.V. Subba Rao, S. Dash, A.K. Tyagi, A.K. *Secondary ion mass spectrometry and X-ray photoelectron spectroscopy studies on TiO₂ and nitrogen doped TiO₂ thin films*, Solid State Commun 151, 245-249 (2011)
460. X.-F. Zhou, L. Lin, W. Wang, S.-Y. Wang, *Shape evolution of NiS₂ minicrystals via thermodynamic controlled growth*, J Cryst Growth 314, 302-305 (2011)
461. M.-D. Yi, L.-H. Xie, Y.-Y. Liu, Y.-F. Dai, J.-Y. Huang, *Electrical characteristics of high-performance ZnO field-effect transistors prepared by ultrasonic spray pyrolysis technique*, Chinese Phys Lett 28, 017302 (2011)
462. M.E. Yakinci, Y. Aydogdu, M.A. Aksan, Y. Balci, S. Altin, *Effects of in-situ and ex-situ heat-treatment procedures on the transport properties of the MgB₂ superconducting thin films fabricated by Ultrasonic Spray Pyrolysis (USP) system*, Journal of Supercond & Novel Magn 24 (1-2), pp. 241-245(2011)
463. Z.D. Yakinci, Y. Aydoğdu, *Synthesis and characterization of MgB₂ thin films prepared by 2.4 MHz ultrasonic spray pyrolysis system*, J Supercond & Novel Magn 24, 529-534 (2011)
464. M.E. Yakinci, M.A. Aksan, Y.B. Alci, S. Altin, T. Onal, Y. Aydogdu, *Nano-sized spherical MgB₂ superconducting powder fabrication using MHz range ultrasonic spray pyrolysis (USP) system*, J Supercond & Novel Magn 24, 235-239 (2011)
465. G. Zhu, T. Lv, L. Pan, Z. Sun, C. Sun, *All spray pyrolysis deposited CdS sensitized ZnO films for quantum dot-sensitized solar cells*, J Alloys & Comp 509, 362-365 (2011)
466. F. Dong, Y. Huang, S. Zou, J. Liu, S.C. Lee, *Ultrasonic spray pyrolysis fabrication of solid and hollow PbWO₄ spheres with structure-directed photocatalytic activity* J Phys Chem C 115, 241-247 (2011)
467. J.D. Atkinson, M.E. Fortunato, S.A. Dastgheib, M. Rostam-Abadi, M.J. Rood, K.S. Suslick, *Synthesis and characterization of iron-impregnated porous carbon spheres prepared by ultrasonic spray pyrolysis*, Carbon 49, 587-598 (2011)
468. I. Khatri, N. Kishi, J. Zhang, T. Soga, T. Jimbo, *Simultaneous formation of both single-and multi-wall carbon nanotubes by ultrasonic spray pyrolysis*, Japanese J Appl Phys 50, 020213 (2011)
469. A.S. Aybek, N. Baysal, M. Zor, E. Turan, M. Kul, *Thermally stimulated current analysis of Zn_{1-x}Cd_xO alloy films*, J Alloys & Comp 509, 2530-2534 (2011)
470. Optical, structural and surface characterization of ultrasonically sprayed CdO:F films Akyuz, I., Kose, S., Ketenci, E., Bilgin, V., Atay, F. 2011 Journal of Alloys and Compounds 509 (5), pp. 1947-1952
471. R. Martínez-Martínez, A.C. Lira, A. Speghini, C. Falcony, U. Caldiño, *Blue-yellow photoluminescence from Ce³⁺ → Dy³⁺ energy transfer in HfO₂:Ce³⁺:Dy³⁺ films deposited by ultrasonic spray pyrolysis*, J Alloys & Comp 509, 3160-3165 (2011)
472. A. Zhong, J. Tan, H. Huang, S. Chen, M. Wang, S. Xu, *Thickness effect on the evolution of morphology and optical properties of ZnO films*, Appl Surf Sci 257, 4051-4055 (2011)
473. P. Yao, *Effects of Sb doping level on the properties of Ti/SnO₂-Sb electrodes prepared using ultrasonic spray pyrolysis*, Desalination 267, 170-174 (2011)
474. A.K.P Mann, S.E. Skrabalak, *Synthesis of single-crystalline nanoplates by spray pyrolysis: A metathesis route to Bi₂WO₆* Chem Mater 23, 1017-1022 (2011)
475. B. Zhang, Y. Tian, J.X. Zhang, W. Cai, *Structural, optical, electrical properties and FTIR studies of fluorine doped SnO₂ films deposited by spray pyrolysis*, J Mater Sci 46, 1884-1889 (2011)
476. T. Prabhakar, N. Jampana, *Effect of sodium diffusion on the structural and electrical properties of Cu₂ZnSnS₄ thin films*, Solar Energy Mater & Solar Cells 95, 1001-1004 (2011)
477. M. T. Htay, Y. Hashimoto, N. Momose, K. Sasaki, H. Ishiguchi, S. Igarashi, K. Sakurai, K. Ito, *A cadmium-free Cu₂ZnSnS₄/ZnO heterojunction solar cell prepared by practicable processes*, Japanese J. Appl Phys 50, 032301 (2011)
478. B.-C. Jiao, X.-D. Zhang, C.-C. Wei, J. Sun, J. Ni, Y. Zhao, *Double-layer indium doped zinc oxide for silicon thin-film solar cell prepared by ultrasonic spray pyrolysis*, Chinese Phys B 20 (3), 037306 (2011)

479. L. Liu, G.-Y Kim, A.C. Hillier, A. Chandra, *Microstructural and electrochemical impedance study of nickel-Ce_{0.9}Gd_{0.1}O_{1.95} anodes for solid oxide fuel cells fabricated by ultrasonic spray pyrolysis*, J Power Sources 196, 3026-3032 (2011)
480. B. Ebin, S. Gürmen, *Aerosol synthesis of nano-crystalline Iron particles from Iron (II) chloride solution*, Metall 65, 151-154 (2011)
481. C. Özgür, O. Şan, *Fabrication of superhydrophilic membrane filters using spherical glass particles obtained by ultrasonic spray pyrolysis* Ceram Int 37, 965-970 (2011)
482. A. Inukai, N. Sakamoto, H. Aono, O. Sakurai, K. Shinozaki, H. Suzuki, N. Wakiya, *Synthesis and hyperthermia property of hydroxyapatiteferrite hybrid particles by ultrasonic spray pyrolysis*, J Magn & Magn Mater 323, 965-969 (2011)
483. X. Zhang, H. Wang, J.-W. Xu, L. Yang, L. Ren, *Effect of substrate temperature on structure and properties of In₂S₃ films*, J Synth. Cryst. 40 (2), 415-418+434 (2011)
484. B.-C. Jiao, X.-D. Zhang, C.-C. Wei, J. Sun, Y. Zhao, *Effect of acetic acid on ZnO thin films fabricated by ultrasonic spray pyrolysis*, J Optoelectron Laser 22, 540-544 (2011)
485. Structure, optical, temperature dependent electrical properties of p-type conduction in N-Al codoped Zn_{1-x}Mg_xO films by ultrasonic spray pyrolysis Zhang, X., Liao, Q., Chen, H., Yan, Z., Yu, Z. 2011 Advanced Materials Research 217-218, pp. 1708-1715 0
486. Zhang, J., Khatri, I., Kishi, N., Mominuzzaman, S.M., Soga, T., Jimbo, T. *Low substrate temperature synthesis of carbon nanowalls by ultrasonic spray pyrolysis*, Thin Solid Films 519 (13), 4162-4165 (2011)
487. B. Zhang, Y. Tian, J. X. Zhang, W. Cai, *The FTIR studies of SnO₂:Sb(ATO) films deposited by spray pyrolysis*, Mater. Lett. 65 (8), 1204-1206 (2011)
488. F. Atay, I. Akyuz, S. Kose, E. Ketenci, V. Bilgin, *Optical, structural and surface characterization of CdO:Mg films*, J. Mater. Sci.: Materials in Electronics 22 (5), 492-498 (2011)
489. F. Chouikh, Y. Beggah, M. Aida, *Optical and electrical properties of Bi doped ZnO thin films deposited by ultrasonic spray pyrolysis* J. Mater. Sci.: Materials in Electronics 22 (5), 499-505 (2011)
490. X. Zhang, H. Wang, J. Xu, L. Yang, M. Ren, *Effect of different S/In ratio on properties of In₂S₃ films prepared by ultrasonic spray pyrolysis method*, Key Eng. Mater. 474-476, 998-1001 (2011)
491. R. Martínez-Martínez, S. Rivera, E. Yescas-Mendoza, E. Álvarez, C. Falcony, U. Caldiño, *Luminescence properties of Ce³⁺-Dy³⁺ codoped aluminium oxide films*, Opt. Mater. 33 (8), 1320-1324 (2011)
492. L. A. Patil, A. R. Bari, M. D. Shinde, V. Deo, *Effect of pyrolysis temperature on structural, microstructural and optical properties of nanocrystalline ZnO powders synthesised by ultrasonic spray pyrolysis technique*, J. Exp. Nanosci. 6 (3), 311-323 (2011)
493. L. Castañeda, A. Maldonado, A. Escobedo-Morales, M. Avendaño-Alejo, H. Gómez, J. Vega-Pérez, L. De La M. Olvera, *Indium doped zinc oxide thin films deposited by ultrasonic spray pyrolysis technique: Effect of the substrate temperature on the physical properties*, Mater. Sci. Semicond. Processing 14 (2), 114-119 (2011)
494. I. Singh, R.K. Bedi, *Studies and correlation among the structural, electrical and gas response properties of aerosol spray deposited self assembled nanocrystalline CuO*, Appl. Surf. Sci. 257 (17), 7592-7599 (2011)
495. J. Liu, Y. Zhang, M. I. Ionescu, R. Li, X. Sun, *Nitrogen-doped carbon nanotubes with tunable structure and high yield produced by ultrasonic spray pyrolysis*, Appl. Surf. Sci. 257 (17), 7837-784 (2011)
496. L.-C. Chen, K.-C. Cheng, *Growth and characteristics of gasb nanowires by catalysis-free ultrasonic spray pyrolysis*, Electrochem & Solid-State Lett 14, H288-H290 (2011)
497. W. Chung, J. Y. Hong, H. P. Sun, B.-H. Chun, J. Kim, H. K. Sung, *Spray pyrolysis synthesis of MA₂O₄:Eu₂ (M=Ba, Sr) phosphor for UV LED excitation*, J. Cryst. Growth 326 (1), 73-76 (2011)
498. G. Zhu, L. Pan, T. Xu, Q. Zhao, Z. Sun, *Cascade structure of TiO₂/ZnO/CdS film for quantum dot sensitized solar cells*, J. Alloys & Comp. 509 (29), 7814-7818 (2011)
499. Z. Yang, H. Nie, X. Zhou, Z. Yao, S. Huang, X. Chen, *Synthesizing a well-aligned carbon nanotube forest with high quality via the nebulized spray pyrolysis method by optimizing ultrasonic frequency* Nano 6, 343-348 (2011)
500. C.E. Benouis, M. Benhaliliba, F. Yakuphanoglu, A.T. Silver, M.S. Aida, A.S. Juarez, *Physical properties of ultrasonic sprayed nanosized indium doped SnO₂ films*, Synthetic Metals 161 (15-16), 1509-1516 (2011)

501. Characteristics of $\text{Li}_3\text{V}_2(\text{PO}_4)_3/\text{C}$ powders prepared by ultrasonic spray pyrolysis Ko, Y.N., Koo, H.Y., Kim, J.H., Yi, J.H., Kang, Y.C., Lee, J.-H. 2011 *Journal of Power Sources* 196 (16), pp. 6682-6687
502. Min, J., Liang, X., Wang, B., Zhao, Y., Guo, Y., Wang, L. *Sensitivity to NO_2 of ZnO film prepared by electrostatic-enhanced ultrasonic spray pyrolysis*, *Adv. Mater. Res.* 299-300, 475-479 (2011)
503. J. Min, X. Liang, B. Wang, Y. Zhao, Y. Guo, L. Wang, *Characterization of Ag doped P-type ZnO thin films prepared by electrostatic-enhanced ultrasonic spray pyrolysis*, *Adv. Mater. Res.* 299-300, 436-439 (2011)
504. S. Buecheler, F. Pianezzi, C. Fella, A. Chirila, K. Decock, M. Burgelman, A.N. Tiwari, *Interface formation between $\text{CuIn}_1 - \text{XGa}_x\text{Se}_2$ absorber and In_2S_3 buffer layer deposited by ultrasonic spray pyrolysis*, *Thin Solid Films* 519 (21), 7560-7563 (2011)
505. I. Singh, G. Kaur, R. K. Bedi, *CTAB assisted growth and characterization of nanocrystalline CuO films by ultrasonic spray pyrolysis technique* *Appl. Surf. Sci.* 257 (22), 9546-9555 (2011)
506. J. Li, H.-M. Zhang, Q. Li, B. Gao, Y.-J. Zhu, *Fabrication of ZnO: Eu thin films by ultrasonic spray pyrolysis method* *J. Optoelectronics Laser* 22 (9), 1367-1370 (2011)
507. M. Yang, X.W. Sun, H.Y. Yu, J. Li, J. Hu, *Low temperature polycrystalline silicon film formation by metal induced crystallization with nickel salt derived by ultrasonic spray pyrolysis*, *Crystal Research and Technology* 46 (9), 935-938 (2011)
508. K., Park, M.H. Heo, *Enhanced photoluminescence of $\text{GdPO}_4:\text{Tb}^{3+}$ under VUV excitation by controlling ZnO content and annealing temperature* *J. Alloys & Comp.* 509 (37), 9111-9115 (2011)
509. S. Aksay, M. Polat, T. Özer, S. Köse, Gürbüz, G. *Investigations on structural, vibrational, morphological and optical properties of CdS and CdS/Co films by ultrasonic spray pyrolysis* *Applied Surface Science* 257 (23), pp. 10072-10077 (2011)
510. Y. Ren, G. Zhao, J. Shen, *Preparation of fluorine doped tin oxide film by ultrasonic spray pyrolysis* *Mater. Sci. Forum* 695, 594-597 (2011)
511. B W Mwakikunga, A. E. Mudau, C Willers, N Brinks, *Flame temperature trends in reacting vanadium and tungsten ethoxide fluid sprays during CO_2 -laser pyrolysis*, *Appl Phys B* 105, 451-462 (2011)
512. D. Y. Medina, S. Orozco, I. Hernandez, R.T.Hernandez, C. Falcony, *Characterization of europium doped lanthanum oxide films prepared by spray pyrolysis* *J. Non-Crystalline Solids* 357 (22-23), 3740-3743 (2011)