

RSC Advances

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: A. T. Chidembo, S. H. Aboutalebi, K. Konstantinov, C. J. Jafra, H. Liu and K. I. Ozoemena, *RSC Adv.*, 2013, DOI: 10.1039/C3RA44973D.



This is an *Accepted Manuscript*, which has been through the RSC Publishing peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, which is prior to technical editing, formatting and proof reading. This free service from RSC Publishing allows authors to make their results available to the community, in citable form, before publication of the edited article. This *Accepted Manuscript* will be replaced by the edited and formatted *Advance Article* as soon as this is available.

To cite this manuscript please use its permanent Digital Object Identifier (DOI®), which is identical for all formats of publication.

More information about *Accepted Manuscripts* can be found in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics contained in the manuscript submitted by the author(s) which may alter content, and that the standard [Terms & Conditions](#) and the [ethical guidelines](#) that apply to the journal are still applicable. In no event shall the RSC be held responsible for any errors or omissions in these *Accepted Manuscript* manuscripts or any consequences arising from the use of any information contained in them.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

In-situ engineering of urchin-like reduced graphene oxide- $\text{Mn}_2\text{O}_3/\text{Mn}_3\text{O}_4$ nanostructures for supercapacitors

Alfred Tawirirana Chidembo,^a Seyed Hamed Aboutalebi,^a Konstantin Konstantinov,^{*a} Charl Jeremy Jafta,^b Hua Kun Liu^a and Kenneth Ikechukwu Ozoemena^{b,c}

Received (in XXX, XXX) Xth XXXXXXXXXX 20XX, Accepted Xth XXXXXXXXXX 20XX

DOI: 10.1039/b000000x

We report the use of spray pyrolysis method to synthesize high surface area (BET surface area of $139 \text{ m}^2\text{g}^{-1}$) self-organized, micron sized urchin-like composites made up of reduced graphene oxide and needle-shaped manganese oxide (rGO- $\text{Mn}_2\text{O}_3/\text{Mn}_3\text{O}_4$). Maximum capacitances of 425 Fg^{-1} at 5 mVs^{-1} from a three electrode set up and 133 Fg^{-1} at a current density of 0.2 Ag^{-1} and were recorded using an asymmetric two electrode set up with graphene as the anode. The composite material also showed a capacitance retention of 83% over 1000 cycles. We attribute this remarkable performance to the high specific surface area due to the urchin-like hollow structures and synergy between the manganese oxide and reduced graphene oxide materials within the composite. Furthermore, this synthesis technique can be exploited further in the bulk synthesis of cost effective graphene-metal oxide hybrid materials for energy storage applications.

Introduction

From the assortment of metal oxides used as pseudocapacitors, RuO_2 stands out as the best performer.¹⁻³ However, due to high cost and environmental concerns, manganese oxide which has a high theoretical capacitance of 1370 Fg^{-1} has been preferred.⁴ Many attempts have therefore been made to synthesize manganese oxides through a host of techniques such as combined sonochemical and solvothermal,⁵ chemical precipitation,⁶ sol-gel processes,⁷ mechanical milling processes,⁸ electrodeposition⁹ and hydrothermal synthesis.¹⁰ However, the preparation methods are less effective in controlling the crystal structure, microstructure and chemical state of manganese oxides.¹¹ In all these studies, the oxidation state of manganese has been reported to critically affect the electrochemical performance of the electrodes. The amount of research on Mn_2O_3 and Mn_3O_4 for supercapacitor studies has however been adversely affected due to their poor electrochemical activity. A transformation of γ - MnO_2 to α - Mn_2O_3 and Mn_3O_4 by mechanical grinding has been found to cause a linear decrease in the specific capacitance as the amount of γ - MnO_2 decreased.⁸ In a bid to improve the performance, researchers have synthesized Mn_2O_3 -carbon aerogel and Mn_3O_4 -graphene^{12, 13} composites although only a handful of such reports are available in literature. Recently, Wang and co-workers reported a solution based approach to synthesize Mn_3O_4 -graphene nanocomposites with a maximum capacitance of 236.7 Fg^{-1} in 2M NaOH.¹⁴ Elsewhere, a maximum capacitance of 256 Fg^{-1} was reported in 6M NaOH after the nanocomposites were synthesized by first mixing a graphene suspension in ethylene glycol with a MnO_2 organosol, followed by ultrasonication processing and heat treatment of the mixture.¹⁵ Lee and coworkers also reported

Mn_3O_4 nanorods mixed with graphene with a maximum capacitance of 121 Fg^{-1} .¹⁶ All these studies however, were carried out in the three electrode set up without testing the practicality of device fabrication in a two electrode set up.

Depending on the method of preparation and conditions, a variety of nanostructures have also been reported. We are aware of the many reports on MnO_x urchin-like structures in literature. These have been shown to possess high surface area and good electrochemical activity although their preparation time takes a considerably long time when compared to the spray pyrolysis method.^{17, 18}

In this work we use the in-situ spray pyrolysis method to produce for the first time, hybrid 3D urchin-like architectures of Mn_2O_3 and Mn_3O_4 anchored on a highly conductive reduced graphene oxide support with improved electrochemical performance. A total specific capacitance of 425 Fg^{-1} and 133 Fg^{-1} in three-electrode and two-electrode asymmetric set ups were recorded in 1M NaOH as an electrolyte respectively. In spite of the very limited time of heat treatment, the spray pyrolysis method proved to be effective in the reduction of graphene oxide (GO) to reduced graphene oxide (rGO), which offers a simple yet effective approach to design advanced graphene based hybrid materials with extraordinary capacitance. Due to the presence of rGO, high capacitance retention of 83% was observed over 1000 cycles.

The spray pyrolysis technique: while providing perfect homogeneity of the final products and productivity with industry up-scaling capabilities offers great flexibility regarding the type and use of initial solutions and/or suspensions. By controlling the fabrication process, it is possible to manufacture a wide range of materials with numerous shapes and structures. We therefore

suggest that this method can be further exploited to fabricate a wide range of graphene-metal oxide/hydroxide materials for different applications in energy storage devices.


Experimental Procedure

Two rGO-Mn₂O₃/Mn₃O₄ hybrid materials with different abbreviations are reported in this work as rGOMO1 and rGOMO2. These are a result of the spray pyrolysis of the following mixtures, 1:12 and 1:7 (GO: Mn(NO₃)₂·xH₂O), respectively. These ratios were chosen to study the electrochemical effect of GO loading in the composites.

Synthesis of GO and hybrid materials

The experimental setup and procedure for the synthesis of GO are similar to those described in our previous report on GO-MWCNT hybrid material.¹⁹ The preparation of the composites is outlined in the schematic diagram in Fig.1.

To investigate the effect of adding GO to the manganese oxide we prepared the first material without any GO present. This material was prepared by adding 27.39g of Manganese (II) nitrate hydrate (Mn(NO₃)₂·xH₂O, 98%, Sigma) powder into water resulting in a brown suspension, the same as Winkler test.²⁰



The red-brownish suspension was stirred for 30 minutes using a conventional magnetic stirrer and then sprayed at 600°C in air into a vertical-type spray-pyrolysis reactor (Note that this material was not mixed with graphene oxide). Following this, we prepared GO containing mixtures with varying amounts of GO with weight ratios of 1:12 and 1:7 (GO:Mn(NO₃)₂·xH₂O). Manganese (II) nitrate hydrate (Mn(NO₃)₂·xH₂O, 98%, Sigma) was diluted in a GO dispersion in water. The dispersion was stirred for 30 minutes using a conventional magnetic stirrer followed by spray-pyrolysis at 600°C into a vertical-type spray-pyrolysis reactor to obtain rGOMO1 and rGOMO2.

Electrode fabrication and analytical characterization methods

X-ray diffraction experiments were performed at room temperature using high resolution X-ray diffraction system (GBC MMA X-Ray diffraction (XRD) with Cu-Kα radiation). The elemental composition was characterised using the X-ray photoelectron spectroscopy (XPS, PHOIBOS 100 hemispherical analyser produced by SPECS GmbH) with pass energy of 26.00 eV, 45° take-off angle and a beam size of 100 μm. The morphologies of the hybrids were examined by field emission scanning electron microscope (FE-SEM) using JSM 7500F, JEOL instrument. The specific surface area was determined by the BET method using the Nova 1000 gas sorption instrument. High-resolution transmission electron microscopy (HRTEM) was performed on the JEOL F3000 machine. For the three electrode set-up, the working electrode was prepared by coating the GOMO1 and rGOMO2 materials on to stainless steel sheets (1cm × 1cm) previously polished with sand paper and ultrasonicated in ethanol for an hour.

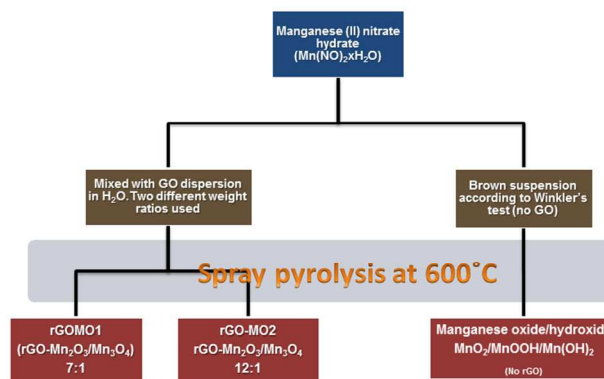


Fig.1 Schematic diagram showing the experimental procedure for the formation of the Mn₂O₃/Mn₃O₄-rGO composites from Manganese nitrate hydrate.

The electroactive material (rGOMO) were mixed with carbon black and PVDF binder at a mass ratio of 70:20:10 in an Agate mortar with (N-methyl pyrrolidinone) NMP solvent and ground to form a slurry.

This was then spread on to the polished stainless steel surface to achieve mass loadings between 1 and 2 mg and allowed to dry in a vacuum oven for 24 h. Electrochemical experiments were then performed at room temperature on the CHI660C (CH Instruments, Inc) electrochemical workstation using the three electrode system in a beaker type cell in 1M NaOH. An Ag|AgCl reference electrode and a platinum foil counter electrode were used for the cyclic voltammetry (CV) over a voltage range of -0.2 to 0.5 V at various scan rates (5 to 100 mVs⁻¹). Electrochemical impedance spectroscopy (EIS) measurements were carried out between 10 kHz and 0.01 Hz using a 5 mV rms sinusoidal modulation.

To fabricate the positive electrode for the coin cell asymmetric setup, a slurry of the active material (in this case rGOMO1) was prepared as described above but this time coated onto the nickel foam substrate, with an average mass loading of ~ 1.4 mgcm⁻². The same procedure was followed for the negative electrode made up of graphene. The electrodes were then dried at 80 °C for 8 hours in a vacuum oven and pressed to a thickness of ~ 0.5 mm. These electrodes were assembled in a coin cell (LIR 2032) separated by whatman© filter paper with 1M NaOH as electrolyte. A combined mass of 3.6 mg was used for both electrodes with a mass ratio (m+/m-) of ~ 2. The cell was then tested using Galvanostatic charge-discharge measurements and EIS on an Autolab potentiostat PGSTAT 302N (Eco Chemie, Utrecht, The Netherlands) driven by the General Purpose Electrochemical Systems data processing software (GPES and FRA software version 4.9).

Results and discussion

Structural characterization

From the onset, it is interesting to note that a mixture of phases exists in the composites after spray pyrolysis. A solution of Mn(NO₃)₂·xH₂O without any GO, when sprayed, resulted in a mixture of oxides and hydroxides with different phases as shown in Figure 2a. The limited time (less than 1s) at which the suspension was exposed to a maximum heat of 600°C resulted in


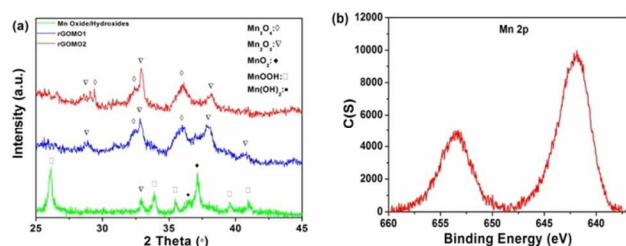


Fig. 2(a) XRD patterns of the manganese based composite showing the different phases present in the Mn Oxides/Hydroxides and the rGOMO materials spray pyrolyzed at 600°C. (b) XPS spectrum of rGOMO1 sample in the Mn region.

incomplete conversion to the more thermodynamically stable Mn_2O_3 and Mn_3O_4 . We therefore refer to this mixture as Manganese oxide-hydroxide. On the other hand, the XRD patterns of the hybrids made from nominal 1:12 and 1:7 (GO-Mn $(\text{NO}_3)_2 \cdot x\text{H}_2\text{O}$) ratios giving rise to rGOMO1 and rGOMO2 show mixtures of Mn_2O_3 and Mn_3O_4 with no traces of hydroxide after spray pyrolysis as the most intense peak of Mn Hydroxide (~26.3) is not present in both rGOMO1 and rGOMO2 samples. The XPS spectrum of Mn region is also given in Figure 2b. However it should be noted that due to the presence of a mixed valence state of 3 and 4, it is impossible to differentiate between hydroxide and oxide samples. These composites clearly demonstrate that the spray pyrolysis of $\text{MnO}(\text{OH})_2$ promotes the phase conversion according to the following pathway:



Nonetheless, the addition of graphene oxide (GO) to the suspension and spray pyrolysis results in the conversion of $\text{MnO}(\text{OH})_2$ to Mn_2O_3 and Mn_3O_4 . XRD patterns suggest that at higher concentration of GO, characteristic peaks of Mn_3O_4 emerge more sharply. Therefore, higher concentration of GO seems to increase the kinetics of phase transformation of Mn_2O_3 to Mn_3O_4 that usually needs heat-treatment at temperatures in excess of 800 °C.^{5, 21}

In the case of spray pyrolysis, due to the very short reaction time, the co-existence of Mn^{2+} and Mn^{3+} favours the formation of hausmannite (Mn_3O_4).^{22, 23} The addition of GO sheets, which exhibit oxygen functional groups in the form of carboxyl, hydroxyl or epoxy groups on their basal planes and edges and water molecules in between the GO sheets, can therefore promote faster kinetics of conversion to hausmannite (Mn_3O_4). These functional groups, which also contain hydrogen, might alleviate the decomposition of manganese hydroxide compounds and the reduction of Mn_2O_3 to Mn_3O_4 . Therefore, the existence of the higher percentage of Mn_3O_4 in rGOMO2 hybrid material compared to rGOMO1 can be attributed to the higher percentage of GO and consequently higher percentage of hydrogen containing functional groups. Field emission scanning electron microscopy (FE-SEM) was employed to investigate the morphology of the obtained samples. **Figure 3** shows FE-SEM micrographs of all three samples where unique urchin like microstructures with manganese oxide needles are observed to grow radially from the rGO core of the hollow spheres.

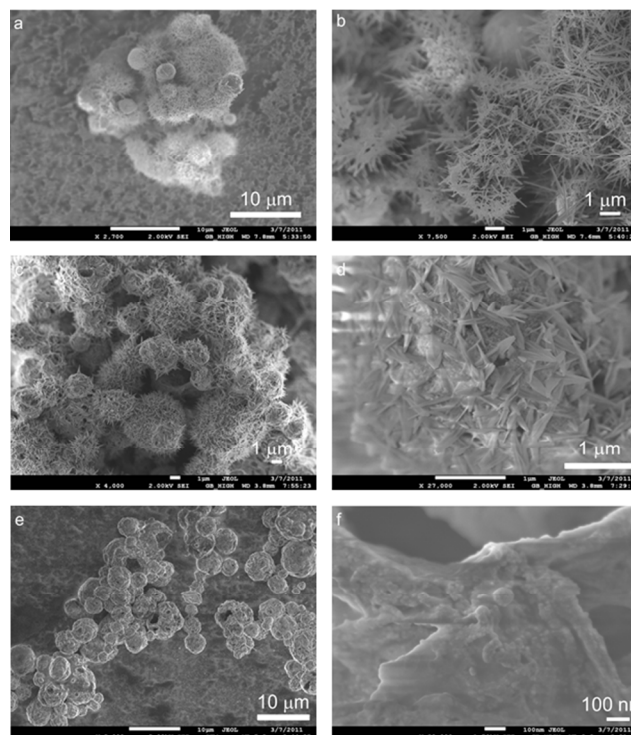


Fig. 3 (a) Low magnification and (b) high magnification FE-SEM micrographs of manganese oxide/hydroxide with no rGO present showing an interconnected network of urchin like microstructures of the manganese oxide/hydroxide. Low magnification (c) and (d) high magnification FE-SEM micrographs of rGOMO1 composite showing a decreased length in nanorods. (e) A further increase in the amount of rGO resulted in the complete absence of metal oxide nanorods but a homogeneous distribution of nanoparticles (f) on the rGO surface for rGOMO2.

Manganese oxides have the tendency to form nano rods or needle like structures.^{16, 24, 25} Though the formation mechanism of the nanorods requires further investigation, the particles originating from the sprayed suspension are believed to orient themselves to form one-dimensional nanorods on the rGO sheets. Through oriented attachment along the side surfaces, 1D nanorods enlarge their diameter to become bulky nanorods in order to minimize the surface energy according to Li et al.²⁶

In Figure 3a and 3b, the nanorods between adjacent microspheres are observed to be entangled, creating a network on the electrode surface. However, higher amounts of GO sheets decrease the solubility of the Mn species, which is in agreement with the decrease in the length of nanorods upon increasing the percentage of GO in the solution. Moreover, the addition of GO dispersion (with pH of around 3-4) to manganese suspension increases the acidity of the suspension which results in proton chemisorption which in turn stabilizes the surface of small particles and limits the growth stage²⁷ as observed in Figure 3c and 3d. A combination of the nano particles and spherically shaped graphene oxide sheets provide a porous network on the electrode surface ideal for charge storage.

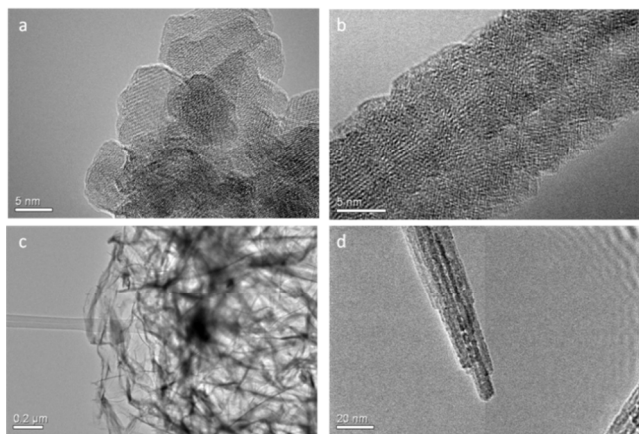


Fig. 4 HRTEM micrographs of Manganese oxide-hydroxide showing (a) an agglomeration of nanoparticles which results in nanorods as shown in (b). The combination of rGO and $\text{Mn}_2\text{O}_3/\text{Mn}_3\text{O}_4$ (c) and a high magnification, (d) rGOMO1.

FE-SEM micrographs (In Figure 3d and 3e) clearly suggest that an increase in the concentration of GO in rGOMO2, hinders further growth of manganese oxide needles upon keeping manganese oxide particles apart from each other. This is in agreement particularly with the BET results for the best performing rGOMO1 observed to be $139 \text{ m}^2\text{g}^{-1}$ while that of the manganese oxide-hydroxide was only $29 \text{ m}^2\text{g}^{-1}$.

To further investigate the formation process, HRTEM was performed on the samples to reveal an aggregation of different primary nanoparticles in **Figure 4a**. This suggests that the manganese oxide-hydroxide sample contains single crystal nanoparticles which are in good agreement with the formation mechanism suggested above. The attachment of these single crystal nanoparticles to form nanorods and further orientation of these 1D nanorods to form bulky nanorods is also illustrated in Figure 4b. The combination of manganese oxide nanorods with graphene oxide sheets is shown in Figure 4c suggesting the hollow nature of the spheres. Upon closer inspection it can be clearly seen in Figure 4d, that the nanorods are actually composed of a few primary nanorods aggregated along the lateral faces.²⁸

Typical C1s spectra of both as-prepared graphene oxide and spray pyrolyzed sample at 600°C obtained by XPS are shown in **Figure 5**. Deconvolution and curve fitting of C1s spectra were performed using CASAXPS software employing a Gaussian-Lorentzian peak shape after performing a Shirley background correction. The C1s spectra mainly consist of 5 individual peaks namely: Carbon sp², Carbon sp³, Epoxy/Hydroxyls, C=O groups and carboxylates. The significant increase in the ratio of carbon-carbon bonds to functional oxide groups (from 0.76 to 1.25) clearly suggests that spray pyrolysis can induce the graphene oxide to reduced graphene oxide transition in spite of the very limited time of heat treatment (less than 1 second). Cyclic voltammetry was used as the first diagnostic tool to electrochemically characterize the Manganese oxide-hydroxide and rGOMO composites as shown in **Figure 6a**. A large current separation was observed for the rGOMO1 electrode suggesting higher capacitance compared to rGOMO2 and Manganese oxide-hydroxide electrodes.


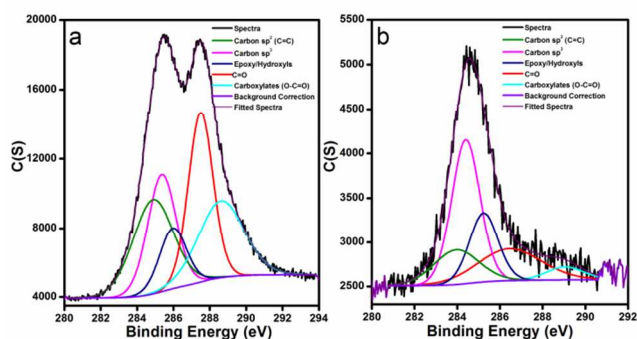


Fig. 5 Fitted XPS C1s spectra of (a) as-prepared GO sample and (b) spray pyrolyzed sample at 600°C .

The CV's deviate from the rectangular shape expected for an electrical double layer capacitor (EDLC) due to the pseudocapacitance contribution by the manganese oxides which is known to add to the overall capacitance due to the variable oxidation states exhibited by manganese. Individually, Mn_2O_3 and Mn_3O_4 have been meagrely reported in literature as supercapacitor electrodes with low capacitance due to poor conductivity.^{5, 29} However, a mixture of Mn_2O_3 and Mn_3O_4 mixed with multiwalled carbon nanotubes (MWCNT) has been reported by Lin et al. to give better performance due to the pseudocapacitance arising from electron transfer at Mn sites and EDLC contribution by the MWCNTs.³⁰ Similarly, we observed the same phenomenon this time using rGO. The Mn^{3+} in Mn_2O_3 has been described as going through an oxidation reaction giving rise to one electron being transferred and attaining a valence state of Mn^{4+} .⁵ Accordingly, the electrochemical reaction in equation 3 is expected to take place during the charge-discharge process involving OH^- chemisorption/intercalation into Mn_2O_3 structure.⁵



While the energy storage mechanism of Mn_3O_4 supercapacitor electrode materials has been recorded previously as a proton-electron mechanism, the CV peaks in Figure 6a cannot be assigned specifically to a particular phase since rGO also possesses some oxide groups on its surface that are capable of participating in redox reactions. However, the overall effect is an enhanced capacitance due to the pseudocapacitance effect arising from all the constituent materials in the composite. The following formula was therefore used to calculate the specific capacitance of the electrode materials at different scan rates³¹.

$$C = \frac{1}{mv(0.5 - (-0.2))} \int_{-0.2}^{0.5} I(V)dV \quad (4)$$

where m is the mass (g), v the scan rate (mV/s), i the current (A) and V the voltage. The highest capacitance at 425 Fg^{-1} was recorded for the rGOMO1, followed by 388 Fg^{-1} for the rGOMO2 and 336 Fg^{-1} for the Manganese oxide-hydroxide at 5 mVs^{-1} . The highest specific capacitance for the RGOMO1 composite is much higher than that reported by Wang and co-workers for $\text{Mn}_3\text{O}_4/\text{graphene}$ (256 Fg^{-1}) in alkaline solution.¹⁵ Figures 6b and 6c show the variation in specific capacitance with increase in scan rate.

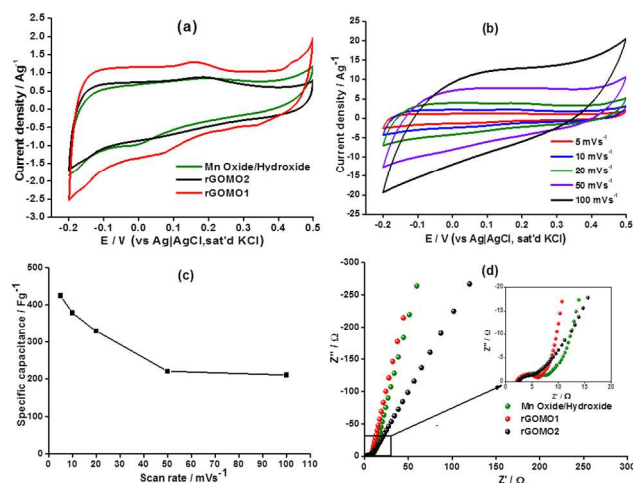


Fig. 6 (a) Cyclic voltammograms of the composites at 5 mVs^{-1} . (b) Effect of scan rate on the shape of CV's of the best performing rGOMO1 electrode. (c) Variation of specific capacitance of the rGOMO1 composite electrode with scan rate. (d) Nyquist plots of the different composites showing the difference in charge transfer resistance in the high frequency region (inset). All experiments performed in 1 M NaOH.

As scan rate is increased, a drop in specific capacitance can be noted. This is due to the less effective interaction between electrolyte ions and the electrode at high scan rates. However, the 3D structure of the rGOMO1 material is essentially an ensemble of concealed interfaces which become accessible at low scan rates thereby increasing the electroactive surface area available for charge storage.³² We therefore established that at 5 mVs^{-1} , the chemisorption and/or intercalation of OH^- into the microstructure is facilitated by the low scan rate hence the more pronounced peaks and higher capacitance. At high scan rates, the peaks become less pronounced (see figure 6b) due to the limited time for ions to reach some of the buried interfaces mentioned earlier.

Further tests to investigate mechanistic effects on the electroactive material such as ion transfer, conduction and capacitive behaviour were carried out using EIS. Figure 6d shows comparative Nyquist plots for the three electrodes in the three electrode set-up. The Nyquist plot is made up of two regions: the high frequency and low frequency regions with each point on the Nyquist plot representing a particular measurement taken at a specific frequency. From the inset in Figure 6d, the small semi-circle observed in the high frequency region is due to charge transfer resistance (R_{ct}) on the electrode/electrolyte interface. The intercept between the plots and the Z' axis represents the ohmic resistance (R_s). From the plot, the manganese oxide/hydroxide material is observed to have a small R_{ct} (5.80Ω) possibly due to the large number of nanorods that enhance the electrode surface area.³³ An addition of rGO clearly enhances the conductivity of the composite as can be observed from the reduction in the R_{ct} with increase in graphene oxide content in rGOMO2. The rGOMO1 hybrid material shows an R_{ct} value of 4.53Ω while that of rGOMO2 is only 3.7Ω . rGO therefore acts both as a conductive support as well as an agent for the uniform dispersion of manganese oxide nanoparticles in the composite thereby enhancing charge transfer within both electrode materials.

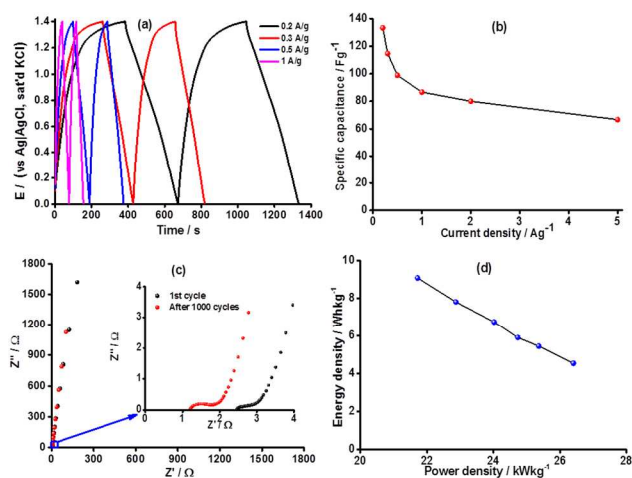


Fig. 7 (a) Charge discharge profiles of the asymmetric supercapacitor device at different current densities. (b) Effect of current density on the specific capacitance. (c) Nyquist plots of before and after 1000 cycles showing differences in the high frequency region (Inset). (d) Ragone plot showing the relationship between energy density and power density.

The specific capacitance values calculated from the charge-discharge method using equation 5 are in agreement with those from CV with the rGOMO1 achieving a specific capacitance of 356 Fg^{-1} followed by rGOMO2 with a specific capacitance of 249 Fg^{-1} and 178 Fg^{-1} for the Manganese oxide-hydroxide at 0.35 Ag^{-1} .

$$C = i(A) \times \Delta t(s) / m(g) \times \Delta E(V) \quad (5)$$

where i , is the discharge current in amperes, t , the discharge time in seconds, m , the mass of the active material in grams and ΔE , the potential window in volts.

From the values achieved, we can attribute the outstanding performance to the distinctive 3D network (combination of nanotubular whiskers and nanoparticles homogeneously distributed on the surface of microspheres), synergy between metal oxide and the transition from GO to rGO after the spray pyrolysis. The rGO has been reported to be more conducting and also more capacitive than GO also showing good power capabilities.³⁴

Asymmetric supercapacitor

An asymmetric supercapacitor was fabricated using the rGOMO1 as the cathode and graphene as the anode in 1M NaOH electrolyte. A maximum value of 133 Fg^{-1} was recorded at 0.2 Ag^{-1} using the charge discharge results in **Figure 7a** and calculated using the formula:³⁵

$$Cs = 4 \times \frac{i \times t}{V \times m_{\pm}} \quad (6)$$

Where i , is the current in Amperes, t , the discharge time in seconds, V the voltage and m_{\pm} the total active mass of the positive and negative electrodes in grams. A factor of 4 was used to translate the specific capacitance of the asymmetric capacitor to that of the single electrode.³⁶ The specific capacitance was also calculated for higher current densities yielding 115, 99, 87, 80, and 67 Fg^{-1} at 0.3, 0.5, 1, 2 and 5 Ag^{-1} respectively as shown in figure 6b. This is higher than the

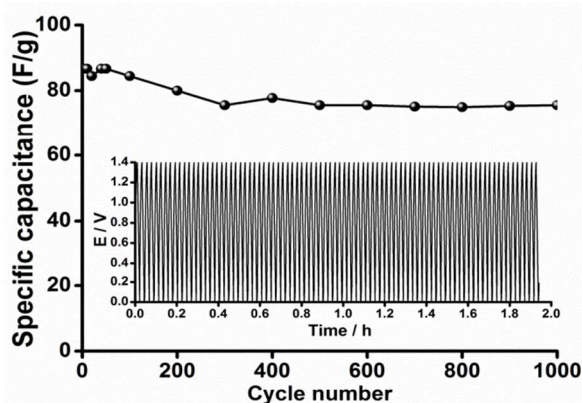


Figure 8. Cycle life of the assembled asymmetric supercapacitor device tested over 1000 cycles at a current density of 0.2 Ag^{-1} within a potential window of 1.4 V.

specific capacitance of 70 Fg^{-1} at 10 mVs^{-1} recorded for a graphene/ MnO_2 /CNT device fabricated by Cheng et al.³⁷ These high values are due to the pseudocapacitance and EDLC contributions of the materials in the hybrid material as mentioned earlier. The shape of the charge-discharge curves in figure 7a slightly deviate from the linear profiles expected for EDLC due to the strong pseudocapacitance contribution by the combination of manganese oxide phases within the composite. This is in agreement with the CV's in Figure 6a which also show a distorted rectangular shape.

So far we have shown that the composite electrode material between manganese oxides and rGO results in enhanced capacitance. Following this, high energy and power densities of the asymmetric supercapacitor assembly should be expected due to the high surface area of rGO implying high power density while the manganese oxide has a high energy density. This synergy between the constituent materials results in a robust asymmetric device with an energy density of 9.07 Whkg^{-1} and a power density of 26.4 kWkg^{-1} . These values were calculated using equations 7 and 8 from the galvanostatic data.

$$SE(\text{Wh/kg}) = i(\text{A}) \times \Delta t(\text{s}) \times \Delta E(\text{V})/m(\text{kg}) \quad (7)$$

$$SP(\text{W/kg}) = SE/t \quad (8)$$

where i is the current in amperes, Δt , the discharge time in seconds, ΔE , the voltage window and m , the mass in kg. A Ragone plot (see Figure 7d) was generated which shows a clear relationship between the energy density and the power density as an efficient way to evaluate the electrochemical performance of supercapacitor device.

One of the characteristics that make supercapacitors more attractive energy storage devices when compared to batteries is the long cycle life of these devices. In light of this, a cycle life test was performed over 1000 cycles with the capacitance retention recorded at 2 Ag^{-1} using charge-discharge. A capacitance retention of 83% shown in figure 8 can be attributed to the presence of the more stable rGO support and graphene anode in the device. Carbonaceous materials are well known to possess remarkable cycling stability which renders the supercapacitor device appropriate for practical applications. Accordingly, the excellent interfacial contact between the Mn_2O_3

and Mn_3O_4 and formation of nanorods effectively prevent the agglomeration and restacking of graphene sheets thereby enhancing the electrochemical activity of the composites. Additionally, the presence of rGO in the final electrode materials assists in improving the conductivity of the poorly conducting Mn_2O_3 and Mn_3O_4 resulting in an enhanced electrical double layer capacitance to the overall specific capacitance, resulting in rapid charge/discharge process.

Conclusions

Hybrid structures of nanoneedle-shaped manganese oxide and spherical graphene oxide have been synthesized using an in-situ spray pyrolysis strategy. The resulting urchin-like morphologies with high surface area ($139 \text{ m}^2\text{g}^{-1}$) form a network on the electrode surface. The combination of reduced graphene oxide with manganese oxide clearly results in very good electrochemical performance (425 Fg^{-1} and 9.07 Whkg^{-1}) of the hybrid material. This is due to the electrical double layer capacitance from graphene oxide and pseudocapacitance from manganese oxide, which is in agreement with a recent report on GO/ MnO_2 asymmetric capacitor.³⁸ The overall capacitance retention (83%) over 1000 cycles is high enough for the material to be considered as a potential candidate for supercapacitor electrodes and other energy devices. The method and approach can be used for synthesis of other graphene-metal oxide electrodes for energy storage.

Acknowledgment

The authors thank the Australian Research Council for the financial support provided through DP (1093952).

Notes and references

- ^a Institute for Superconducting & Electronic Materials (ISEM), Innovation Campus, University of Wollongong, Wollongong, NSW 2519, Australia, Fax: 0061242215731; Tel: 0061242215730; E-mail: atc987@uowmail.edu.au, konstan@uow.edu.au
- ^b Energy Materials Unit, Materials Science and Manufacturing, Council for Scientific & Industrial Research (CSIR), Pretoria 0001, South Africa. E-mail: kozoemena@csir.co.za
- ^c Department of Chemistry, University of Pretoria, Pretoria 0002, South Africa. E-mail: kozoemena@csir.co.za
- J. P. Zheng and T. R. Jow, *Journal of The Electrochemical Society*, 1995, **142**, L6-L8.
- C. D. Lokhande, D. P. Dubal and O.-S. Joo, *Current Applied Physics*, 2011, **11**, 255-270.
- V. D. Patake, S. M. Pawar, V. R. Shinde, T. P. Gujar and C. D. Lokhande, *Current Applied Physics*, 2010, **10**, 99-103.
- J.-H. Kim, K. H. Lee, L. J. Overzet and G. S. Lee, *Nano Letters*, 2011, **11**, 2611-2617.
- T. Nathan, M. Cloke and S. R. S. Prabakaran, *J. Nanomaterials*, 2008, **2008**, 1-8.
- M. Toupin, T. Brousse and D. Bélanger, *Chemistry of Materials*, 2002, **14**, 3946-3952.
- R. N. Reddy and R. G. Reddy, *Journal of Power Sources*, 2003, **124**, 330-337.
- A. Taguchi, S. Inoue, S. Akamaru, M. Hara, K. Watanabe and T. Abe, *Journal of Alloys and Compounds*, 2006, **414**, 137-141.

9. Y.-C. Chen, Y.-K. Hsu, Y.-G. Lin, Y.-K. Lin, Y.-Y. Horng, L.-C. Chen and K.-H. Chen, *Electrochimica Acta*, 2011, **56**, 7124-7130.
10. H. Jiang, T. Zhao, C. Yan, J. Ma and C. Li, *Nanoscale*, 2010, **2**, 2195-2198.
11. G. Wang, L. Zhang and J. Zhang, *Chemical Society Reviews*, 2012, **41**, 797-828.
12. Y. Wu, S. Liu, H. Wang, X. Wang, X. Zhang and G. Jin, *Electrochimica Acta*, 2013, **90**, 210-218.
13. Q. Jiangying, G. Feng, Z. Quan, W. Zhiyu, H. Han, L. Beibei, W. Wubo, W. Xuzhen and Q. Jieshan, *Nanoscale*, 2013, **5**, 2999-3005.
14. D. Wang, Y. Li, Q. Wang and T. Wang, *European Journal of Inorganic Chemistry*, 2012, **2012**, 628-635.
15. B. Wang, J. Park, C. Wang, H. Ahn and G. Wang, *Electrochimica Acta*, 2010, **55**, 6812-6817.
16. J. W. Lee, A. S. Hall, J.-D. Kim and T. E. Mallouk, *Chemistry of Materials*, 2012, **24**, 1158-1164.
17. M. Xu, L. Kong, W. Zhou and H. Li, *The Journal of Physical Chemistry C*, 2007, **111**, 19141-19147.
18. L. Ni, X. Cheng, X. Wang, Y. Tao, Y. Shen, T. Zhang, H. Sun and A. Xie, *Ionics*, 2013, **19**, 259-264.
19. S. H. Aboutalebi, A. T. Chidembo, M. Salari, K. Konstantinov, D. Wexler, H. K. Liu and S. X. Dou, *Energy & Environmental Science*, 2011, **4**, 1855-1865.
20. L. W. Winkler, *Berichte der deutschen chemischen Gesellschaft*, 1888, **21**, 2843-2854.
21. N. N. Greenwood and A. Earnshaw, *Chemistry of the Elements* Oxford: Butterworth-Heinemann, 1997.
22. C.-C. Hu, Y.-T. Wu and K.-H. Chang, *Chemistry of Materials*, 2008, **20**, 2890-2894.
23. H. Zhang, C. Liang, Z. Tian, G. Wang and W. Cai, *CrystEngComm*, 2011, **13**, 1063-1066.
24. S. Chen, J. Zhu, X. Wu, Q. Han and X. Wang, *ACS Nano*, 2010, **4**, 2822-2830.
25. D. Portehault, S. Cassaignon, E. Baudrin and J.-P. Jolivet, *Journal of Materials Chemistry*, 2009, **19**, 7947-7954.
26. Y. Li, H. Tan, O. Lebedev, J. Verbeeck, E. Biermans, G. Van Tendeloo and B.-L. Su, *Crystal Growth & Design*, 2010, **10**, 2969-2976.
27. D. Portehault, S. Cassaignon, E. Baudrin and J.-P. Jolivet, *Chemistry of Materials*, 2007, **19**, 5410-5417.
28. S. Chen, J. Zhu, Q. Han, Z. Zheng, Y. Yang and X. Wang, *Crystal Growth & Design*, 2009, **9**, 4356-4361.
29. X. Cui, F. Hu, W. Wei and W. Chen, *Carbon*, 2011, **49**, 1225-1234.
30. C.-K. Lin, K.-H. Chuang, C.-Y. Lin, C.-Y. Tsay and C.-Y. Chen, *Surface and Coatings Technology*, 2007, **202**, 1272-1276.
31. J. Yan, T. Wei, B. Shao, F. Ma, Z. Fan, M. Zhang, C. Zheng, Y. Shang, W. Qian and F. Wei, *Carbon*, 2010, **48**, 1731-1737.
32. D. R. Rolison, J. W. Long, J. C. Lytle, A. E. Fischer, C. P. Rhodes, T. M. McEvoy, M. E. Bourg and A. M. Lubers, *Chemical Society Reviews*, 2009, **38**, 226-252.
33. M.-S. Wu, *Applied Physics Letters*, 2005, **87**, 153102-153103.
34. K. Zhang, L. L. Zhang, X. S. Zhao and J. Wu, *Chemistry of Materials*, **22**, 1392-1401.
35. J. N. Lekitima, K. I. Ozoemena, C. J. Jafta, N. Kobayashi, Y. Song, D. Tong, S. Chen and M. Oyama, *Journal of Materials Chemistry A*, 2013, **1**, 2821-2826.
36. Y. Zhu, S. Murali, M. D. Stoller, K. J. Ganesh, W. Cai, P. J. Ferreira, A. Pirkle, R. M. Wallace, K. A. Cychoz, M. Thommes, D. Su, E. A. Stach and R. S. Ruoff, *Science*, 2011, **332**, 1537-1541.
37. Y. Cheng, S. Lu, H. Zhang, C. V. Varanasi and J. Liu, *Nano Letters*, 2012, **12**, 4206-4211.
38. C. J. Jafta, F. Nkosi, L. le Roux, M. K. Mathe, M. Kebede, K. Makgopa, Y. Song, D. Tong, M. Oyama, N. Manyala, S. Chen and K. I. Ozoemena, *Electrochimica Acta*, 2013, **110**, 228-233.