

The Fibre, Yarn and Fabric Properties of the Cashmere Component of South African Indigenous Goat Hair

A.F, BOTHA and J.A. ROUX*

CSIR Materials Science and Manufacturing, PO Box 1124, Port Elizabeth, 6001

Email: afbotha@csir.co.za

*Cradock Experimental Station, Eastern Cape Department of Agriculture, PO Box 287, Cradock, 5880

Tel +27 48 8814513

Abstract

South Africa has over 4 million indigenous goats (Boer, Savannah and Nguni/Mbusi breeds), many of which have two coats of fibre, namely a cashmere-like fine down and a coarse guard hair. These goats are primarily kept for their meat, milk and skin products and for other traditional purposes, including controlling bush encroachment. A programme was launched 10 years ago aimed at establishing and improving the cashmere fibre production and associated value addition potential of these indigenous goats. Against this background, this paper discusses the joint project between the CSIR and the Eastern Cape Department of Agriculture aimed at the utilization and promotion of fine down (cashmere) fibre production from indigenous goats. This paper reports on studies undertaken to determine the ability of South African indigenous goats to produce cashmere-like fibres and presents some of the results obtained on fleece samples tested during the past 10 years. Reference is made to the fibre quality, yield and profile of the down component of the samples and to the properties of yarn and fabric produced from the fine down fibres.

Introduction

The traditional cashmere producing countries of Asia account for the bulk of dehaired cashmere produced in the world (6000 tonnes/year), with China the main producer. Outside Asia, the combined Australian and New Zealand production is less than 20 tonnes/year of dehaired cashmere and the estimated production in Scotland for 1996 was 1 tonne (Phan & Wortmann 1996). South Africa does not produce cashmere commercially, and presently there is no local cashmere industry. In South Africa, the bulk (\pm 6.4 million, see Table 1) of indigenous goats, such as the Boer, Savannah and other traditional goats (Nguni/Mbusi type) owned by small farmers are primarily kept for their meat, milk and skin products and for other

traditional purposes, as well as for controlling bush encroachment. There is considerable potential for further value-addition by utilising the fine down fibres present in certain of the breeds. Most South African indigenous breeds possess two distinct coats, cashmere (i.e. a fine down finer than 18.5 μ m) and guard hair (see Table 2). It was felt that if the yield of the highly priced cashmere type of down fibre could be increased and exploited, this could lead to the possibility of creating a viable cashmere industry in South Africa, thereby adding value to the indigenous goats. Because many of the indigenous goats are found in the Eastern Cape Province (Table 1), the Eastern Cape Department of Agriculture and the Council for Scientific and Industrial Research (CSIR) initiated a programme to establish and improve the fine down fibre (cashmere) production potential of indigenous goats.

In 2006, the Eastern Cape Provincial Government identified goat production as one of its strategies to address the socio-economic development of the rural areas. It is within this context that the production of high-value fibres, such as cashmere, has received favourable attention from provincial government officials. As a result of this, a joint project between the Eastern Cape Department of Agriculture (ECDoA) and CSIR Materials Science and Manufacturing's Fibres and Textiles competence area, based in Port Elizabeth, has been created to drive the cashmere initiative. The ECDoA responsibility includes the breeding trials, collecting the cashmere fibre and increasing the cashmere production within the EC. The CSIR has the responsibility to analyse and evaluate the quality and processing of the fibres so produced.

**Table 1 : Distribution of goats in South Africa
(Trends in the Agriculture Sector, 2006)**

Province	Goat numbers
Gauteng	42 542
Mpumalanga	97 666
Western Cape	234 602
Free State	263 430
Northern Cape	576 702
North West	782 860
Limpopo	1 062 814
Eastern Cape	2 483 811
KwaZulu-Natal	855 426
Total	6 399 853

Table 2 : Down fibre quality and yield for South African double-coated and Gorno Altai goat breeds (Braun & Roux, 2005)

	Boer goats	Savannah goats	Traditional goats	Gorno Altai goats
Fibre diameter (µm)*	16.0 – 18.5	16.0 – 18.5	14.0 – 16.5	18.5 – 19.0
Fibre length (mm)	20-31	20-31	15 – 30	28 – 45
Fibre crimp	Good	Good	Good	Poor
Fibre style	Good	Good	Good	Poor
Down Fibre weight per goat (g)	10 - 50	10 – 50	5 – 15	100 – 500
Fibre yield (%)* (Combed fleeces)	50 - 70	50 – 70	40 – 60	50 – 70
Fibre colour	White and White/Colour	White	White and White/Colour	Brown
Other comments	-	-	-	Silky handle, very matted, intermediate fibres

*-Measured by means of an OFDA instrument (IWTO 1995; Hermann & Wortmann 1995, 1996, 1997).

Although some results of the properties of the down fibres have been published, no results have been published on the properties of yarns and fabrics produced from the fine down of South African indigenous goats. This paper reports such results.

Materials and Methods

The fibres (mostly white) used in these trials were collected over the years from indigenous goats and were dehaired in the UK, the CSIR only recently having acquired a dehairing machine (Dawson type). These samples were tested for fibre diameter and other attributes using the OFDA (IWTO 1995; Hermann & Wortmann 1995, 1996, 1997) and the results of the fibres used in the present study are shown in Table 3a. Lambswool, in the form of broken top (Table 3a), was blended with the cashmere fibre in a 60% cashmere/ 40% lambswool blend and then mule spun into a singles yarn of 83.5 tex (yarn linear density). The yarn was spun and waxed by La Lionne Textiles in KwaZulu-Natal (South Africa).

A 4.5 ktex carded sliver of a 50%/50% cashmere/cotton blend was produced on a Trützschler TC03, followed by two passages on a TD03 draw frame to produce a draw frame sliver which was spun at the CSIR on a Schlafhorst Autocoro 312 open-end rotor spinning machine (open roller type D174DN) fitted with automatic piecing, to create another set of experimental yarns, namely 20 tex, 28 tex and 35 tex, respectively. These yarns were also plied to produce two-ply yarns and waxed. The cotton characteristics were measured with an Uster AFIS and are shown in Table 3b.

The evenness properties of both the singles and two-ply yarns were measured on an Uster Tester 3 and the tensile properties on an Instron according to EN ISO 2062 (500 mm/min). The properties of the various yarns are given in Table 4. The yarns were knitted into a single jersey structure on a 10 gauge flat-bed knitting machine (Flying Tiger), with a constant stitch length according to the Woolmark knitting test method for washing performance of wool textiles (Woolmark 2000). The physical properties of the different sets of fabrics are given in Table 5.

Both the yarn and fabrics properties were measured under standard atmospheric conditions (20°C and 65 per cent Relative Humidity) allowing sufficient time for the samples to reach equilibrium (at least 24 hours).

Table 3a : Properties of the cashmere and lambswool fibres used to produce the 60% cashmere/40% lambswool blend yarns

	Down Fibre					Guard Hair		Percentage Of Down Fibres In Specific Diameter Classes				
	Fibre length (mm)	MFD (µm)	CV _D (%)	Curvature (deg/mm)	Yield (%)	MFD (µm)	CV _D (%)	1-20 µm	21-25 µm	26-30 µm	31-60 µm	61-300 µm
Indigenous goats (Cashmere)	30-40	15.9	20.7	62.6	69.3	70.2	38.4	85.9	9.4	1.2	1.7	1.7
Lambswool (broken top)	40-42	17.5	-	-	-	-	-				-	

MFD – Mean fibre diameter; CV_D – Coefficient of variation of diameter

Table 3b : Properties of the cotton fibre used to produce the 50% cashmere/50% cotton blend yarns

MFD (µm)	CV _D (%)	L(w) (mm)	L (w) (%CV)	SFC (n) (%)	Trash (count/g)	VFM (%)	Neps (count/g)
14.5	0.8	26.5	29.8	20.6	16	0.52	91

MFD- Mean fibre diameter, CV_D-Coefficient of variation of diameter, L (w) – Mean Length by weight, SFC (n) – Short fibre content by number, VFM – visible foreign matter by weight

Results and Discussion

The grease content of SA cashmere was found to be between 2.0 and 3.0%, McGregor (2001) having reported that the grease content for Australian cashmere varied from 0.14% to 8% compared to that of Chinese cashmere, namely 2.0% to 7.2%.

McGregor (2001) showed that fibre curvature (bending of the fibre at a point) is a good method for identifying cashmere. The relationship between the MFD and curvature for South African cashmere is shown in Figure 1, curvature decreasing as MFD increases, which is similar to the findings of McGregor (2001). The average curvature values

for the SA cashmere (Table 3a) were very similar to those of the Australian cashmere given by McGregor (2001) (see Figure 2), although the range was wider. The Chinese cashmere had a higher average curvature value (McGregor 2001) and a lower curvature range than the SA cashmere.

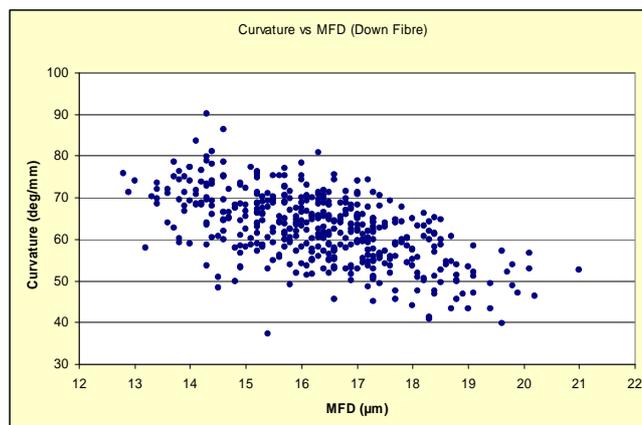


Figure 1 : Curvature as a function of MFD for the down cashmere type fibre of Indigenous goats

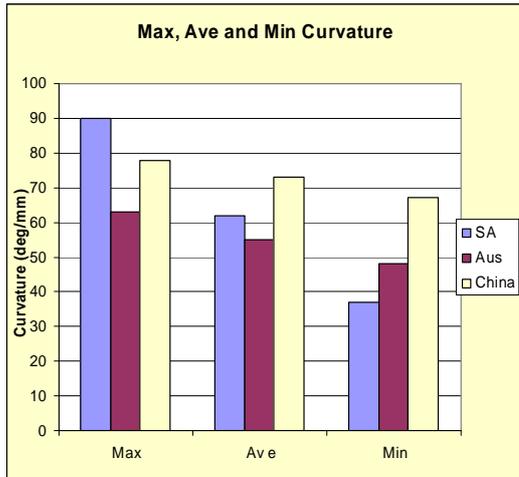


Figure 2 : Curvature values for dehaired cashmere from different origins

From Table 4 it can be seen that, as expected, the evenness properties and strength of the cashmere/cotton blend yarns improved with increasing linear yarn density (singles and two-ply, respectively), and also with plying. Spinning of the cashmere/cotton blends did not create any undue problems, except for the 20 tex single yarn which was difficult to spin.

From Table 5 it is clear that all the knitted fabrics had a very poor pill rating and appearance after the pilling test, with loose pills/debris (small felted balls appearing on fabric) being left behind in the drum after testing. A number of factors could be responsible for the pilling, with the low cover factor and twist factor used and the relatively short fibre length probably playing a major role. Ways of improving pilling performance need to be investigated. The length and width shrinkage values (dimensional change) differed significantly, indicating that much of the observed shrinkage can be attributed to relaxation shrinkage resulting from loop (fabric) distortion introduced on the knitting machine. The 60/40 cashmere/lambswool exhibited the highest shrinkage in both directions, the appearance indicating that felting occurred. This can largely be explained by the fact that the lambswool was not shrink-resist treated.

Conclusions

Results obtained during a joint project between the CSIR and the Eastern Cape Department of Agriculture, aimed at the utilisation and promotion of the fine down (cashmere) fibre production from indigenous goats, are presented. It was found that the properties of the cashmere from the South African indigenous goats compared favourably with those of the Chinese and Australian cashmere fibre and that acceptable yarns could be spun from the dehaired cashmere when blended with lambswool or cotton, using either mule spinning or rotor spinning. Pilling and washing shrinkage of the knitted products are currently not of an acceptable standard and further work to improve these properties needs to be carried out.

The study indicated that the potential exists to establish a cashmere industry in South Africa. Apart from rearing goats for just meat production, the fine down component of the goat can be used to produce high-quality knitted products. This value-addition opportunity could have a major impact on the rural communities and the textile and clothing industries in general.

Acknowledgements

The Eastern Cape Department of Agriculture is acknowledged for funding this project. The staff of the Fibres and Textiles Competence Area are thanked for assisting in the processing of the yarns and for testing the yarns and fabrics.

Table 4 : Yarn properties of different types of yarn blends

	Mule spun	Rotor-spun					
	60/40 Cashmere /Lambswool	50/50 Cashmere/Cotton					
Yarn linear density	83.5 tex	20 tex	28 tex	35 tex	R40 tex/2	R56 tex/2	R70 tex/2
Twist (turns/m)	400	1195	1009	907	-	-	-
Irregularity [†] (CVm %)	11.9	16.5	14.5	13.4	11.4	10.6	10.3
Thin Places** (-50%)/km	2	115	11	5	1	0	0
Thick Places** (+50%)/km	4	126	41	21	4	1	1
Neps (+200%)/km	13	498	112	52	12	7	2
Neps (+280%)/km	3	45	9	3	0	1	0
Hairiness (hairs/m)	12.4	5.5	6.1	6.5	6.7	7.3	7.7
Tenacity (cN/tex)	3.8	6.6	6.5	6.6	6.9	6.9	8.0
Extension (%)	18.4	5.2	6.5	7.5	7.2	6.6	7.1

† - Unevenness (irregularity) of the yarn given as a percentage

** - The number of thin and thick places in the yarn

Table 5 : Knitted fabric properties

	60/40		50/50					
	Cashmere /Lambswool		Cashmere/Cotton					
Yarn linear Density	83.5 tex		R40 tex/2		R56 tex/2		R70 tex/2	
Mass per unit area (g/m ²)#	246		109		158		203	
Dimensional Change (%)*	Length	Width	Length	Width	Length	Width	Length	Width
	-32.8	-16	-18.8	9.6	-18.2	2.8	-15.8	-4.4
Pilling (Rating)***	1		1		1		1	
Spirality (mm)****	64		14		19.5		97	

- AS 2001.2.13 (1987)

* - Woolworths P1A (2003) with a negative sign indicating shrinkage

*** - IWS Test Method 152 (ICI Pillbox method) (1996b)

**** - Woolworths P1B (2003)

References

- Standards Association of Australia, 1987: Physical tests – Determination of mass per unit area and mass per unit length of fabrics. Melbourne: Standards Association of Australia (AS 2001.2.13)
- Braun, A.L. and Roux, J.A., 2005. Progress in the utilization and promotion of South African indigenous goats for cashmere production, Poster at the 8th International Goat Congress in Pretoria.
- Hermann, S. and Wortmann, F.J., 1995. Development of models for the simultaneous estimation of fibre quality and yield in raw cashmere fleeces. *Fine Fibre News*, No. 5, 5-10.
- Hermann, S. and Wortmann, F.J., 1996. Simultaneous estimation of Cashmere yield and Fibre Quality using Optical Fibre Diameter Analyser. In: *Proceedings of the Vith International Conference on Goats*, Beijing, May 1996, 908-911.
- Hermann, S. and Wortmann, F.J., 1997. Opportunities for the Simultaneous Estimation of Essential Fleece Parameters in Raw Cashmere Fleeces. *Livestock Production Science*. **48**, 1-12.
- International Wool Secretariat, 1996. Rapid test method for resistance to pilling and change in fabric appearance (ICI Pillbox method). Test Method 152. Melbourne.
- International Wool Textile Organisation, 1995.. Measurement of the mean and distribution fibre diameter of wool using an optical fibre diameter analyser (OFDA). IWTO-47-95 Ilkley, Yorkshire, UK.
- McGregor, B.A., 2001. The Quality of cashmere and its influence on textile materials produced from cashmere and blends with superfine wool, PhD. , Sydney, Australia: University of New South Wales.
- Phan, K.H. and Wortmann, F.J., 1996. Identification and classification of cashmere, European Fine Fibre Network, Occasional Publication, No 5, 45.
- Trends in the Agricultural Sector, 2006. Pretoria: Department of Agriculture
- Woolmark, 2000. (Aug. 2000) : Product specification – Knitted apparel products (WM K1)(The Woolmark Company)
- Woolworths, 2003a. Measurement of spirality of weft knitting fabrics and garments. Woolworths performance standards and test methods (P1B).
- Woolworths, 2003b.: Wascator stability washes – To determine stability to fabrics to washing Woolworths performance standards and test methods (P1A))